



IfBB

Institute for Bioplastics
and Biocomposites



Biopolymers


facts and statistics

2025

Production capacities,
processing routes, feedstock,
land and water use

**HOCHSCHULE
HANNOVER**
UNIVERSITY OF
APPLIED SCIENCES
AND ARTS

–
*Fakultät II
Maschinenbau und
Bioverfahrenstechnik*



1	Introduction and background	3
2	Process routes	5
	Glossary	6
2.1	Bio-based polyesters	8
2.1.1	Poly(lactic acid) (PLA)	8
2.1.2	Poly(hydroxybutyrate) (PHB)	10
2.1.3	Poly(butylene succinate) (PBS)	12
2.1.4	Poly(butylene succinate adipate) (PBSA)	15
2.1.5	Poly(trimethylene terephthalate) (PTT)	18
2.1.6	Poly(ethylene terephthalate) (Bio-PET)	21
2.1.7	Poly(ethylene furanoate) (PEF)	24
2.1.8	Poly(butylene terephthalate) (Bio-PBT)	26
2.1.9	Poly(butylene adipate terephthalate) (Bio-PBAT)	29
2.2	Bio-based polyolefins	32
2.2.1	Poly(ethylene) (Bio-PE)	32
2.2.2	Poly(propylene) (Bio-PP)	34
2.3	Bio-based polyamides (Bio-PA)	36
2.3.1	Homopolyamides	36
2.3.1.1	Bio-PA 6	36
2.3.1.2	Bio-PA 11	38
2.3.2	Copolyamides	39
2.3.2.1	Bio-PA 4.10 – Bio-PA 5.10 – Bio-PA 6.10	39
2.3.2.2	Bio-PA 10.10	40
2.4	Polyurethanes	42
2.5	Polysaccharide polymers	44
2.5.1	Cellulose-based polymers (Cellulosics)	44
2.5.1.1	Regenerated cellulose	44
2.5.1.2	Cellulose diacetate	45
2.5.2	Starch-based polymers	47
2.5.2.1	Thermoplastic starch (TPS)	47
2.5.2.2	Starch blends	48
2.6	Poly(vinyl chloride) (Bio-PVC)	50
2.7	Bio-based polyacrylates	54
2.7.1	Poly(methyl methacrylate) (Bio-PMMA)	54
3	Market data and land use facts	56
3.1	Global production capacities of bioplastics	58
3.2	Global production capacities of bioplastics (by material type)	59
3.3	Global production capacities of bioplastics (by region)	60
3.4	Global production capacities of bioplastics (by market segment)	63
3.5	Land use for bioplastics 2025 and 2030	66
4	References	68


Introduction and background

The IfBB – Institute for Bioplastics and Biocomposites is a research institute within the Hochschule Hannover, University of Applied Sciences and Arts. The IfBB was established in 2011 after more than a decade of on-going research activities in the field of bioplastics to respond to the growing need for expert knowledge in this area. With its practice-oriented research and its collaboration with industrial partners, the IfBB is able to shore up the market for bioplastics and, in addition, foster unbiased public awareness and understanding of the topic.

As an independent research-led expert institution for bioplastics, the IfBB is willing to share its expertise, research findings and data with any interested party via online and offline publications or at fairs and conferences. In carrying on these efforts, substantial information regarding market trends, processes and resource needs for bioplastics are being presented here in a concise format, in addition to the more detailed and comprehensive publication "Engineering Biopolymers" (cf. Endres & Siebert-Raths 2011). If figures or data from this or other publication of IfBB is being used, we kindly ask any person or institution to quote IfBB's authorship.

One of our main concerns is to furnish a more rational basis for discussing bioplastics and use fact-based arguments in the public discourse. Furthermore, "Biopolymers, facts and statistics" aims to easily and quickly provide specific, qualified answers for decisionmakers in particular from public administration and the industrial sector. Therefore, this publication is made up like a set of rules and standards and largely foregoes textual detail. It offers extensive market-relevant and technical facts presented in graphs and charts, which means that the information is much easier to grasp. The reader can expect comparative market figures for various materials, regions, applications, process routes, agricultural land use or resource consumption, production capacities, geographic distribution, etc.

In recent years, many new types of bioplastics have emerged and innovative polymer materials are pushing into the plastics market. All the same, bioplastics by no means constitute a completely new class of materials but rather one that has been rediscovered from among the large group of plastic materials.

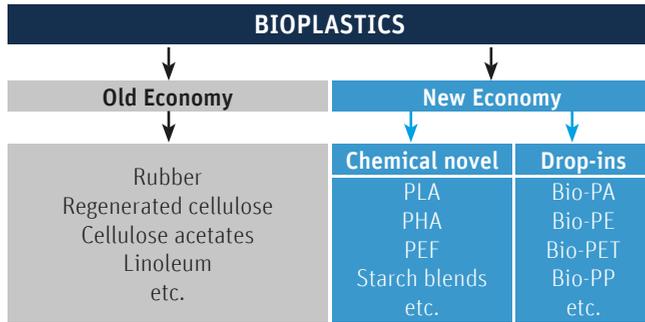

The first man-made polymer materials were all based on modified natural materials (e.g., casein, gelatine, shellac, celluloid, cellophane, linoleum, rubber, etc.). That means they were bio-based since petrochemical materials were not yet available at that time. Ever since the middle of the 20th century, these early bio-based plastics, with a few exceptions (cellulose and rubber-based materials), have almost been replaced by petrochemical materials.

By now, due to ecological concerns, limited petrochemical resources and sometimes new property profiles, bioplastics have undergone a remarkable revival and are taken more and more into focus by the general public, politics, the industrial sector and in particular the research community.

Of particular interest today are new types of bioplastics, which were developed in the past 30 years. The publication presented here refers to the so-called “New Economy” bioplastics as opposed to “Old Economy” bioplastics which indicate earlier materials developed before petrochemical bioplastics emerged, yet still exist on the market today (e.g., rubber, cellophane, viscose, celluloid, cellulose acetate, linoleum).

“New Economy” bioplastics divide up into two main groups. On the one hand, there are those biopolymers which have a new chemical structure virtually unknown in connection with plastics until a few years ago (e.g. new bio-based polyesters such as PLA), on the other hand so-called “drop-ins”, with the same chemical structure yet bio-based. The most prominent drop-ins at this point are bio-based PET (Bio-PET) and bio-based polyethylene (Bio-PE).

For detailed calculations of resource consumption for the production of various bio-based plastics:

<https://biopolydat.ifbb-hannover.de>.

Process routes

Process routes depict the manufacturing steps from the raw material to the finished product, specifying the individual process and conversion steps, intermediate products, and input-output streams. So they serve as a guide for all considerations and calculations around the production of bioplastics, in particular also with regard to their resource consumption.

The following methodical approach was chosen to establish the process routes:

The mass flows were first calculated without assuming allocations (especially no feedstock allocation) and using a molar method based on the chemical process, with the introduction of known rates and conversion factors. The routes so established were confirmed with polymer manufacturers and the industry. In so far as no loss rates due to the chemical processes or the process stages were included, the calculations were made basically assuming no losses. The mass flows show feedstocks and resulting requirements in hectare (ha) or the production of one metric ton (t) of bioplastics. Feedstock requirements were calculated for the use of different crops. Yields of the most important crops and renewable raw materials used for feedstocks are shown in the chart below on page 6.

Please note that the yields in this context refer to the crop itself, which contains the raw material for processing, and not to the harvested whole plant.

The conservative calculation used in this publication delivers a resilient approach for adjustments to be made out of individual needs.

For calculating water use data, information on water use for different raw materials originally collected by the 'Water Footprint Network' has been used (cf. Hoekstra et al. 2011; Mekonnen & Hoekstra 2011). It is based on FAOSTAT crop definitions (Food and Agriculture Organization of UN (cf. FAOSTAT 2022, Online Data)) which are also used for land use calculations. This means, water use is only available from "seed to market place". Only water, such as rainwater, irrigation and to somewhat extent process water to clean agricultural products, e.g., used/needed to grow the whole plant is included here. On the other side the water use for the processing like polymerization is neglected. This is part of an ongoing research, but this first simplified approach gives a good indication and delivers first data to the issue of water use of bioplastics.

Feedstock	Crop	Raw material	Global mean yield ¹ (Crop)	Average content of raw material	Resulting amount (raw material)	
Calculations			->	X	->	=
Sugar cane	Sugar cane (without cane tops)	Fermt. Sugar	73.1 t/ha	13 % ^{3, 4, 5, 6}	9.5 t sugar/ha	
Sugar beet	Beet (without leaves)	Fermt. Sugar	62.7 t/ha	16 % ^{3, 6, 7}	10.03 t sugar/ha	
Corn	Maize kernel	Starch	7 t/ha	70 % ⁸	4.9 t starch/ha	
Potatoes	Potato tuber	Starch	24 t/ha	18 % ^{8, 9}	4.32 t starch/ha	
Wheat	Wheat grains	Starch	3.97 t/ha	46 % ⁸	1.83 t starch/ha	
Wood	Standing timber, residual wood	Cellulose	1.64 t atro ² /ha	40 % ¹³	0.66 t cellulose/ha	
Castor oil plant	Castor bean (seeds)	Castor oil	1.5 t seeds/ha (given one harvest per year)	40 % ^{10, 11, 12}	0.6 t oil/ha (given one harvest per year)	

¹ Global mean yield over a period of 10 years (2010 - 2019), weighted by respective production amount (based on FAOSTAT 2010 - 2019).

² Absolutely dry.

³ Cf. FAO 1994.

⁴ Cf. Perez 1997.

⁵ Cf. Alexander 1988.

⁶ Cf. Li & Yang 2015.

⁷ Cf. FAO 1999.

⁸ Cf. BeMiller & Whistler 2009.

⁹ Cf. Jang & Lim 2011.

¹⁰ Cf. Rojas-Barros et al. 2004.

¹¹ Cf. Anjani 2012.

¹² Cf. Yeboah et al. 2020.

¹³ Calculated from various forest statistics and reports, Federal Forest Inventory (Germany).

Glossary

Abbreviations used:

atro = bone dry

bb = bio-based

BDO = Butanediol

DMDA = Decamethylene diamine

Fermt. = fermentable

ha = hectare = 0,01 km²

HMDA = Hexamethylene diamine

m³ = cubic metres = 1 000 litres

MEG = Monoethylene glycol

PDO = Propanediol

PMDA = Pentamethylene diamine

PTA = Purified terephthalic acid

SCA = Succinic acid

t = metric ton = 1 000 kg

TMDA = Tetramethylene diamine

red coloured resources have a petro-based origin

A large amount of additional information is also available at:

www.ifbb-hannover.de and <https://biopolydat.ifbb-hannover.de>.

ifbb-hannover.de




biopolydat



Sample process route


select desired feedstock/crop, i.e. sugar cane or sugar beet

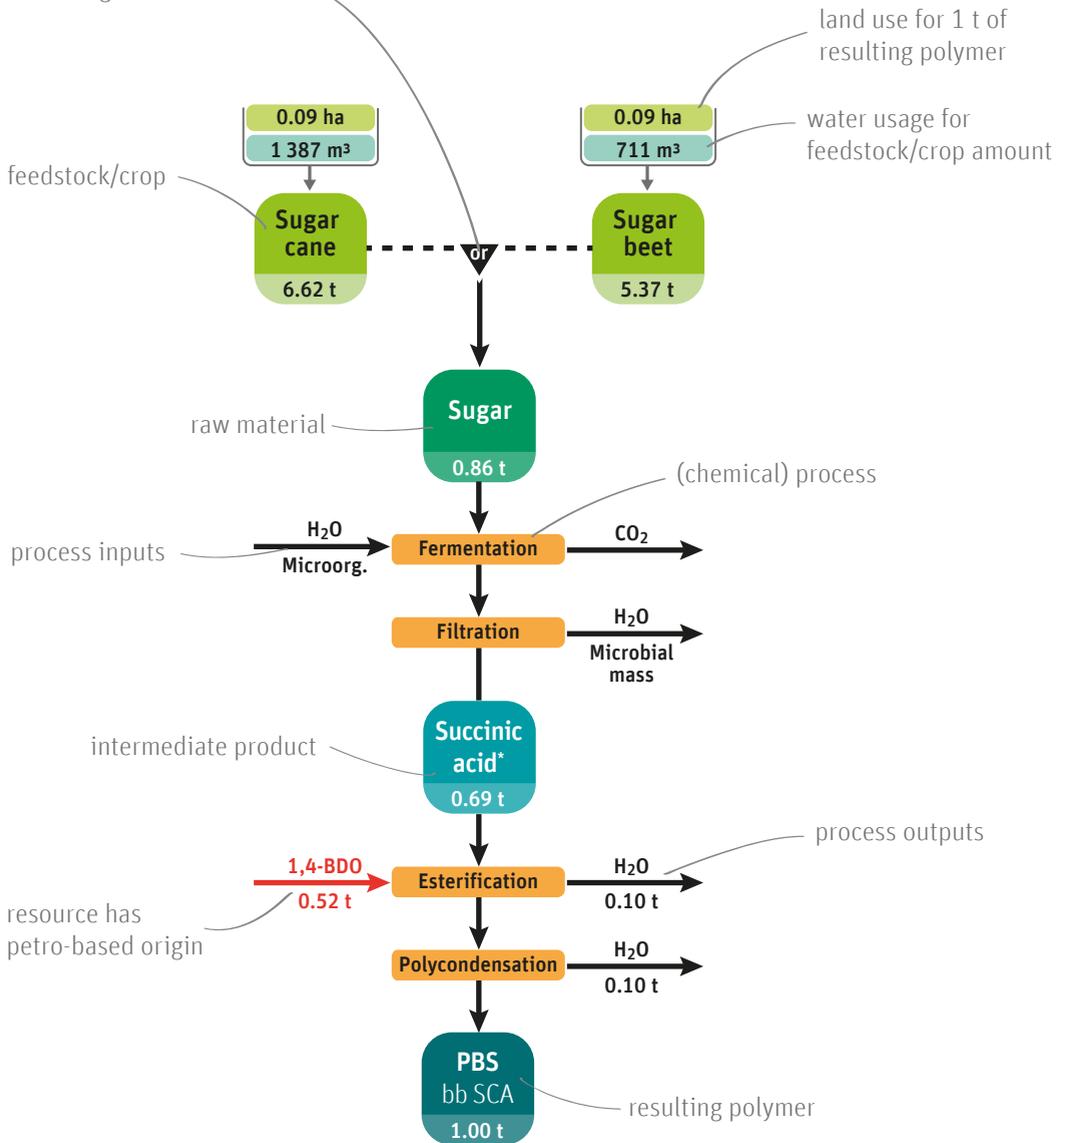


2.1 Bio-based polyesters

2.1.1 Polylactic acid (PLA)


Bio-based content: 100 %

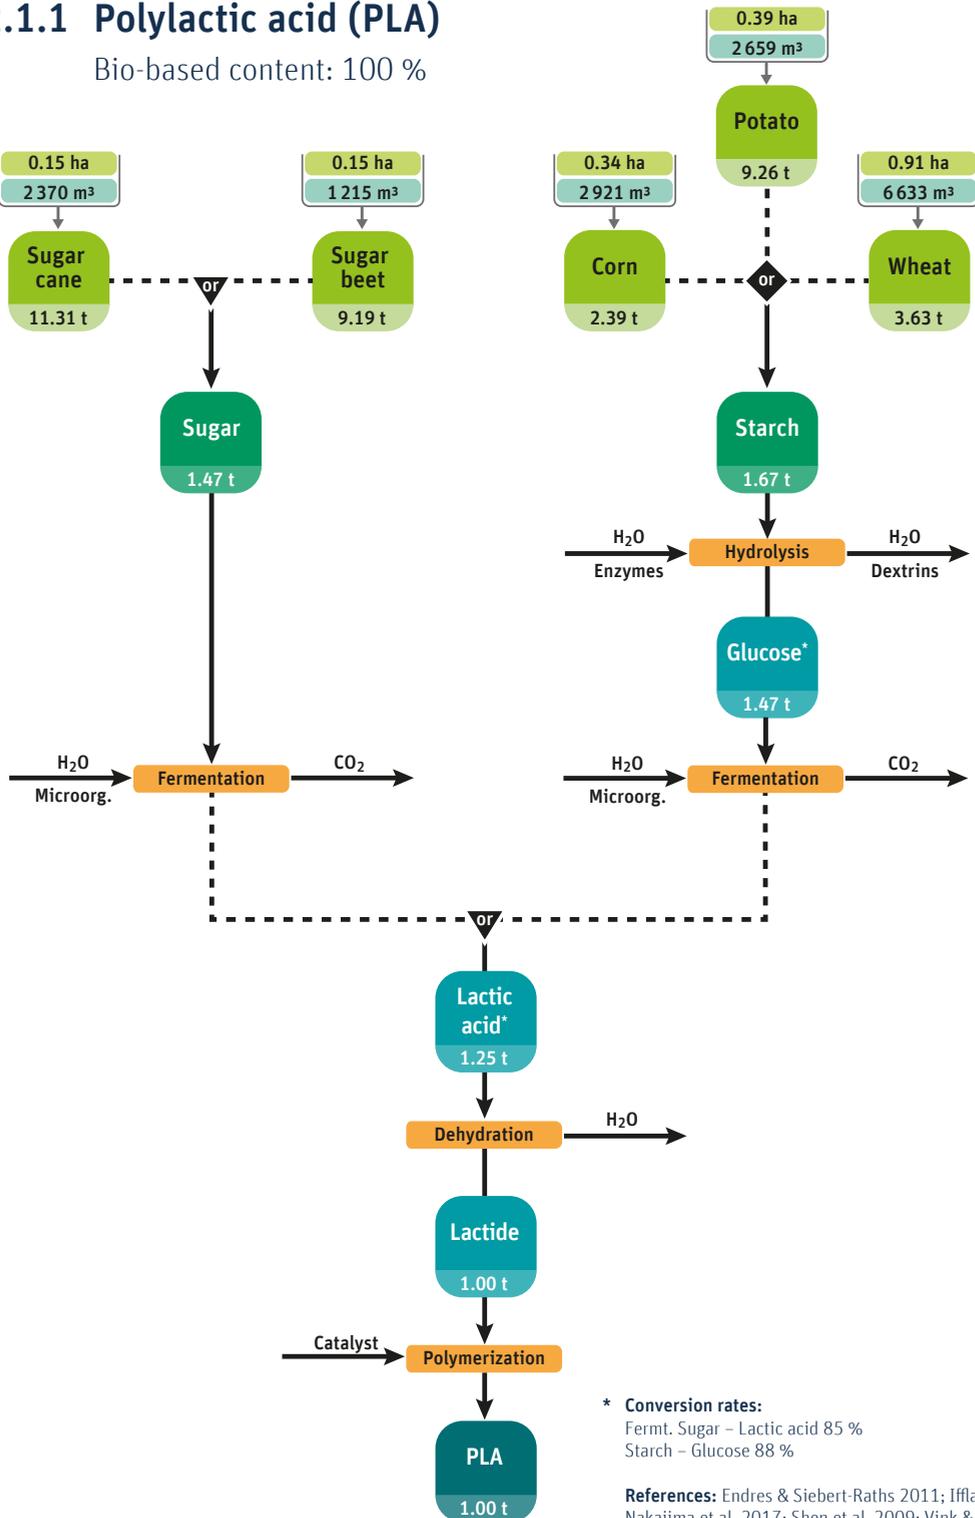


PLA – Feedstock requirements in t (different feedstocks)

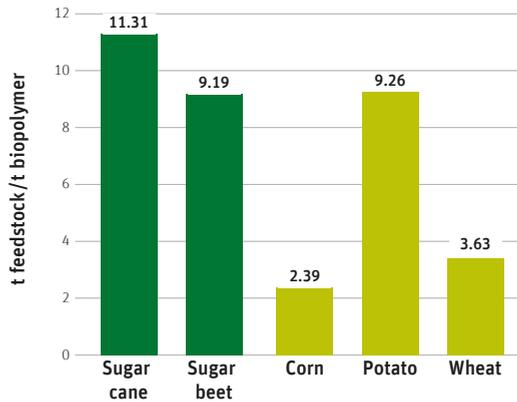

PLA – Land use in ha (different feedstocks)

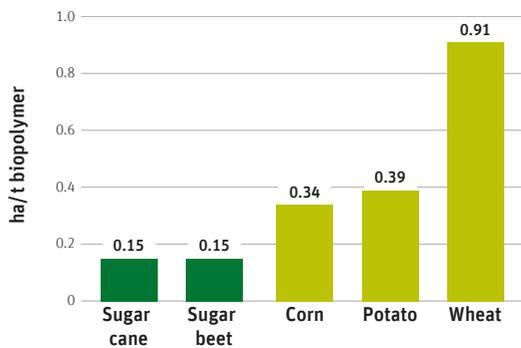


PLA – Water use in m³ (different feedstocks)

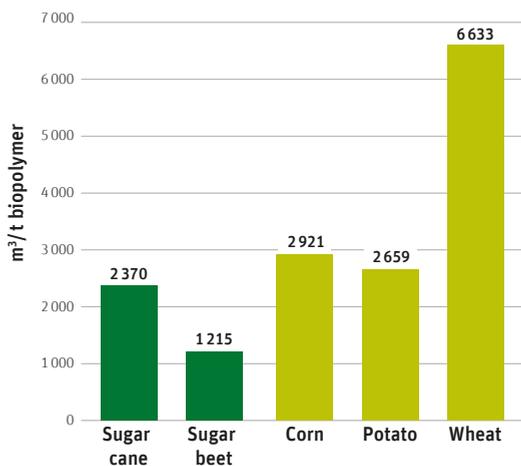


2.1.2 Polyhydroxybutyrate (PHB)

Bio-based content: 100 %

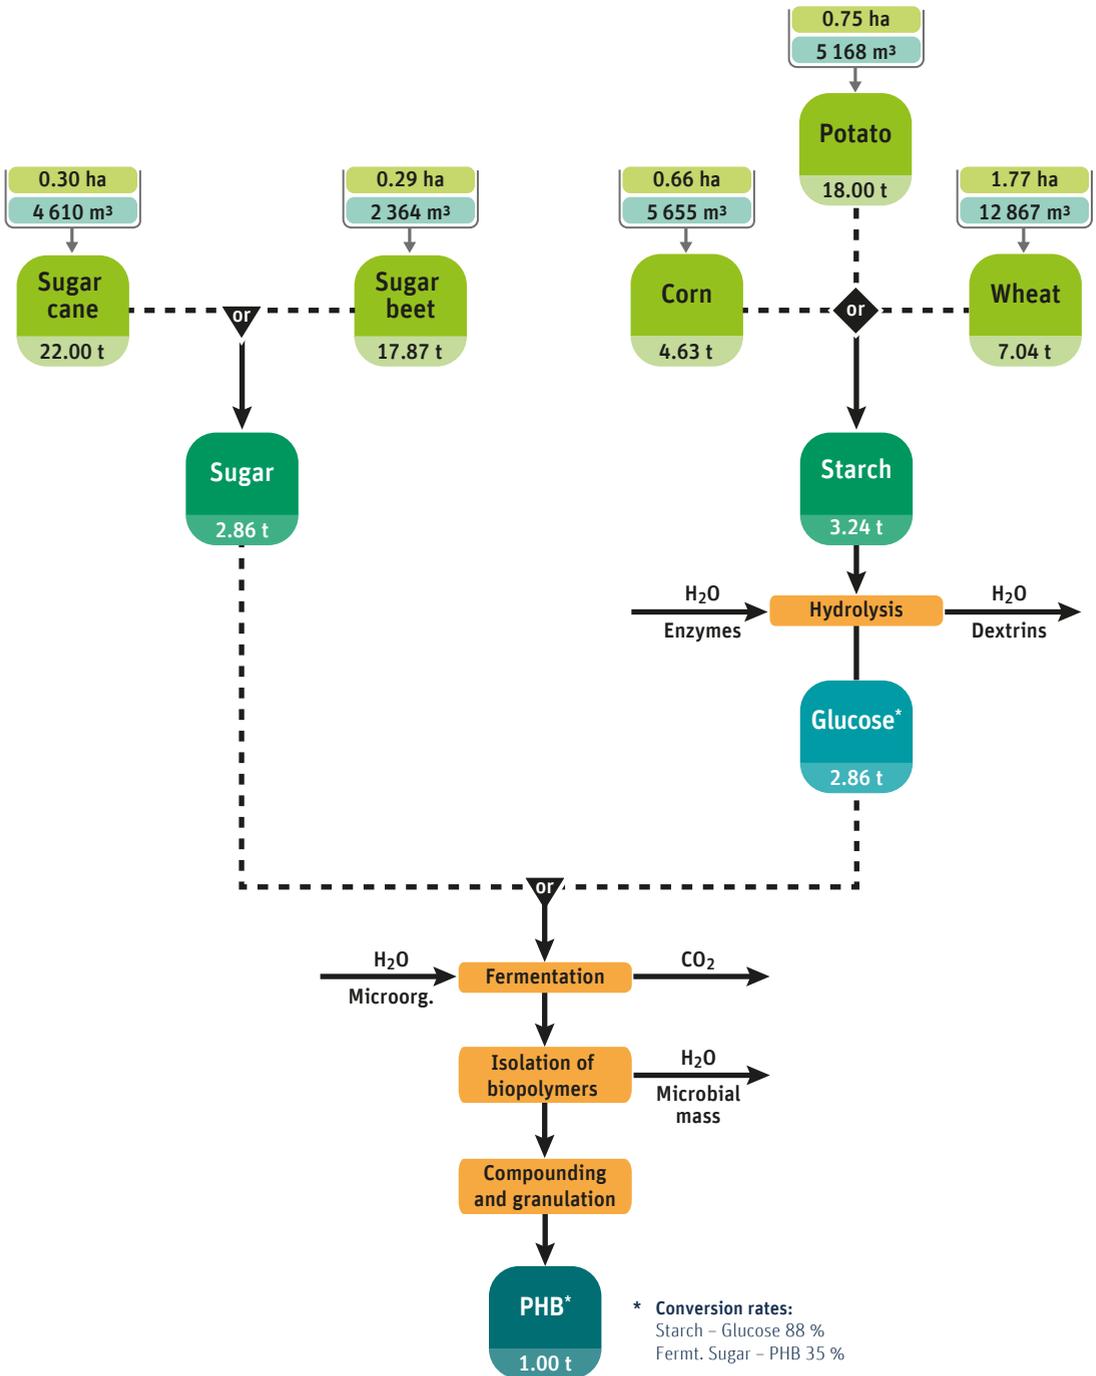


References: Chen 2010; Endres & Siebert-Raths 2011; Iffland et al. 2015; Kootstra et al. 2017; Nakajima et al. 2017; Shen et al. 2009


PHB – Feedstock requirements in t (different feedstocks)

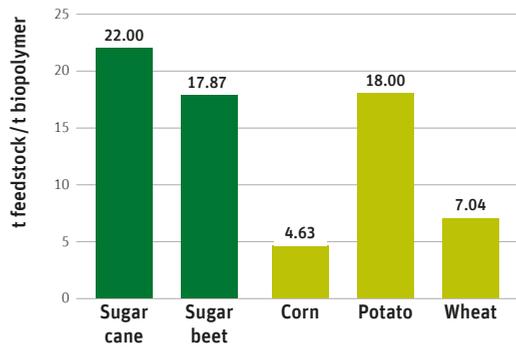

PHB – Land use in ha (different feedstocks)

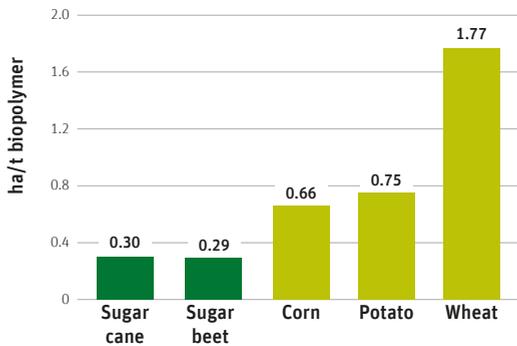


PHB – Water use in m³ (different feedstocks)

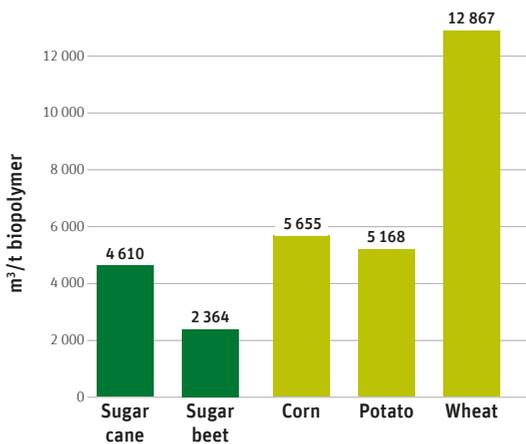

2.1.3 Polybutylene succinate (PBS)

with bio-based succinic acid (PBS bb SCA)

Bio-based content: 57 %

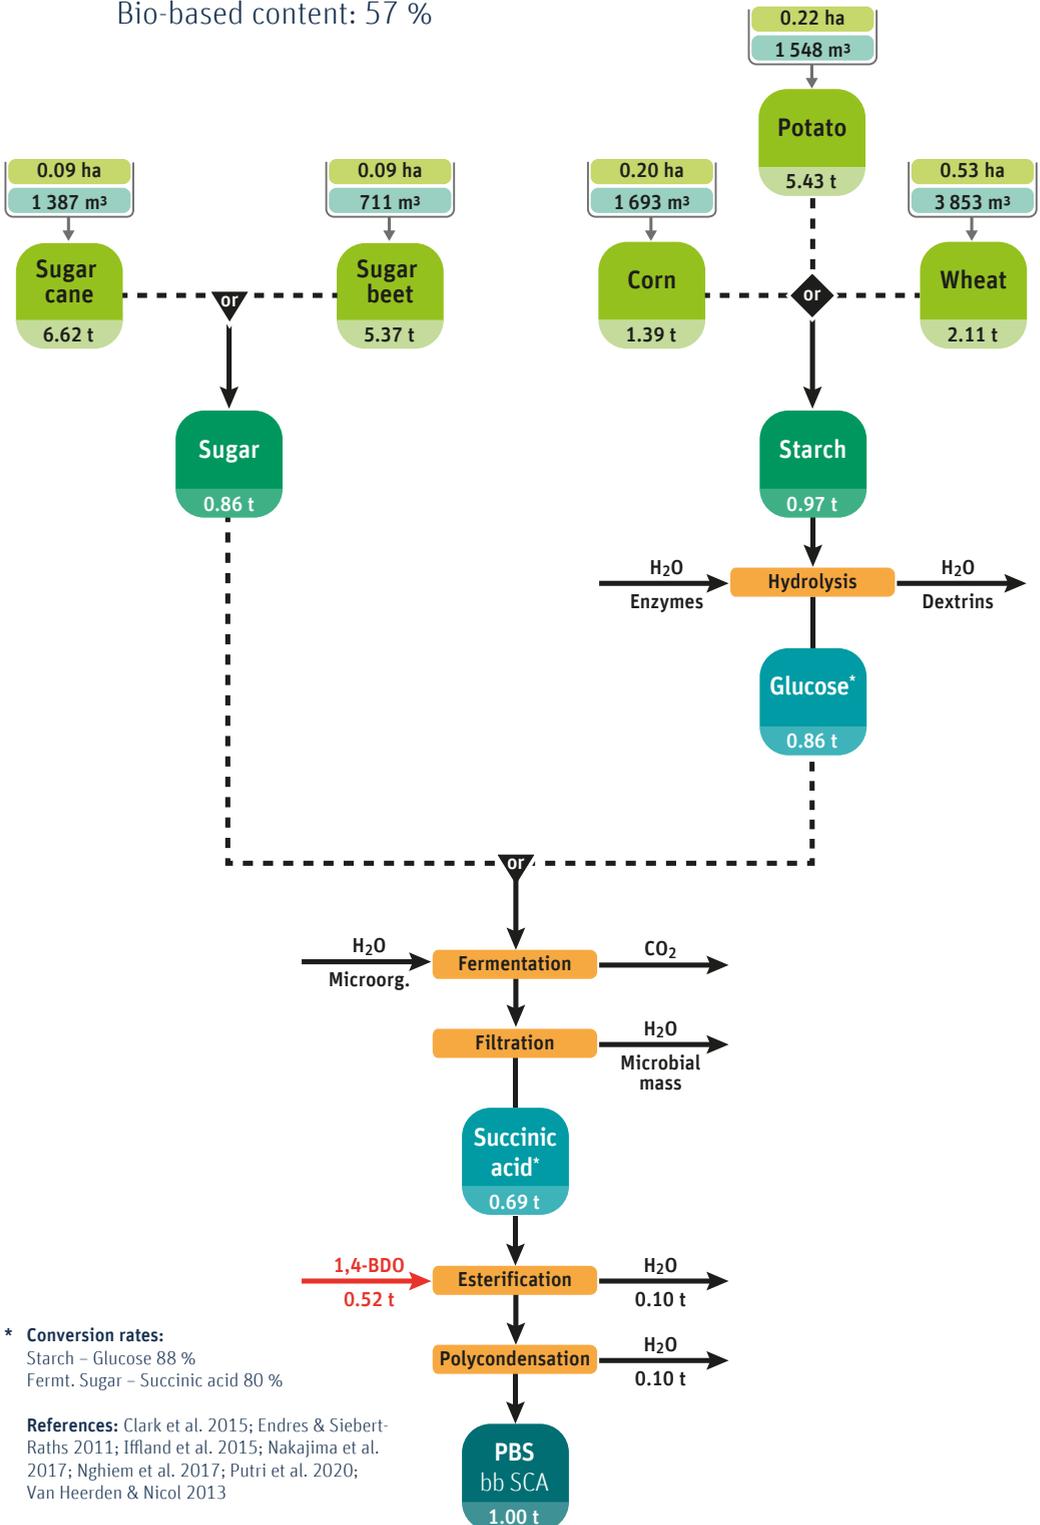


* Conversion rates:
 Starch – Glucose 88 %
 Fermt. Sugar – Succinic acid 80 %

References: Clark et al. 2015; Endres & Siebert-Raths 2011; Iffland et al. 2015; Nakajima et al. 2017; Nghiem et al. 2017; Putri et al. 2020; Van Heerden & Nicol 2013

2.1.3 Polybutylene succinate (PBS)


Bio-based content: 100 %

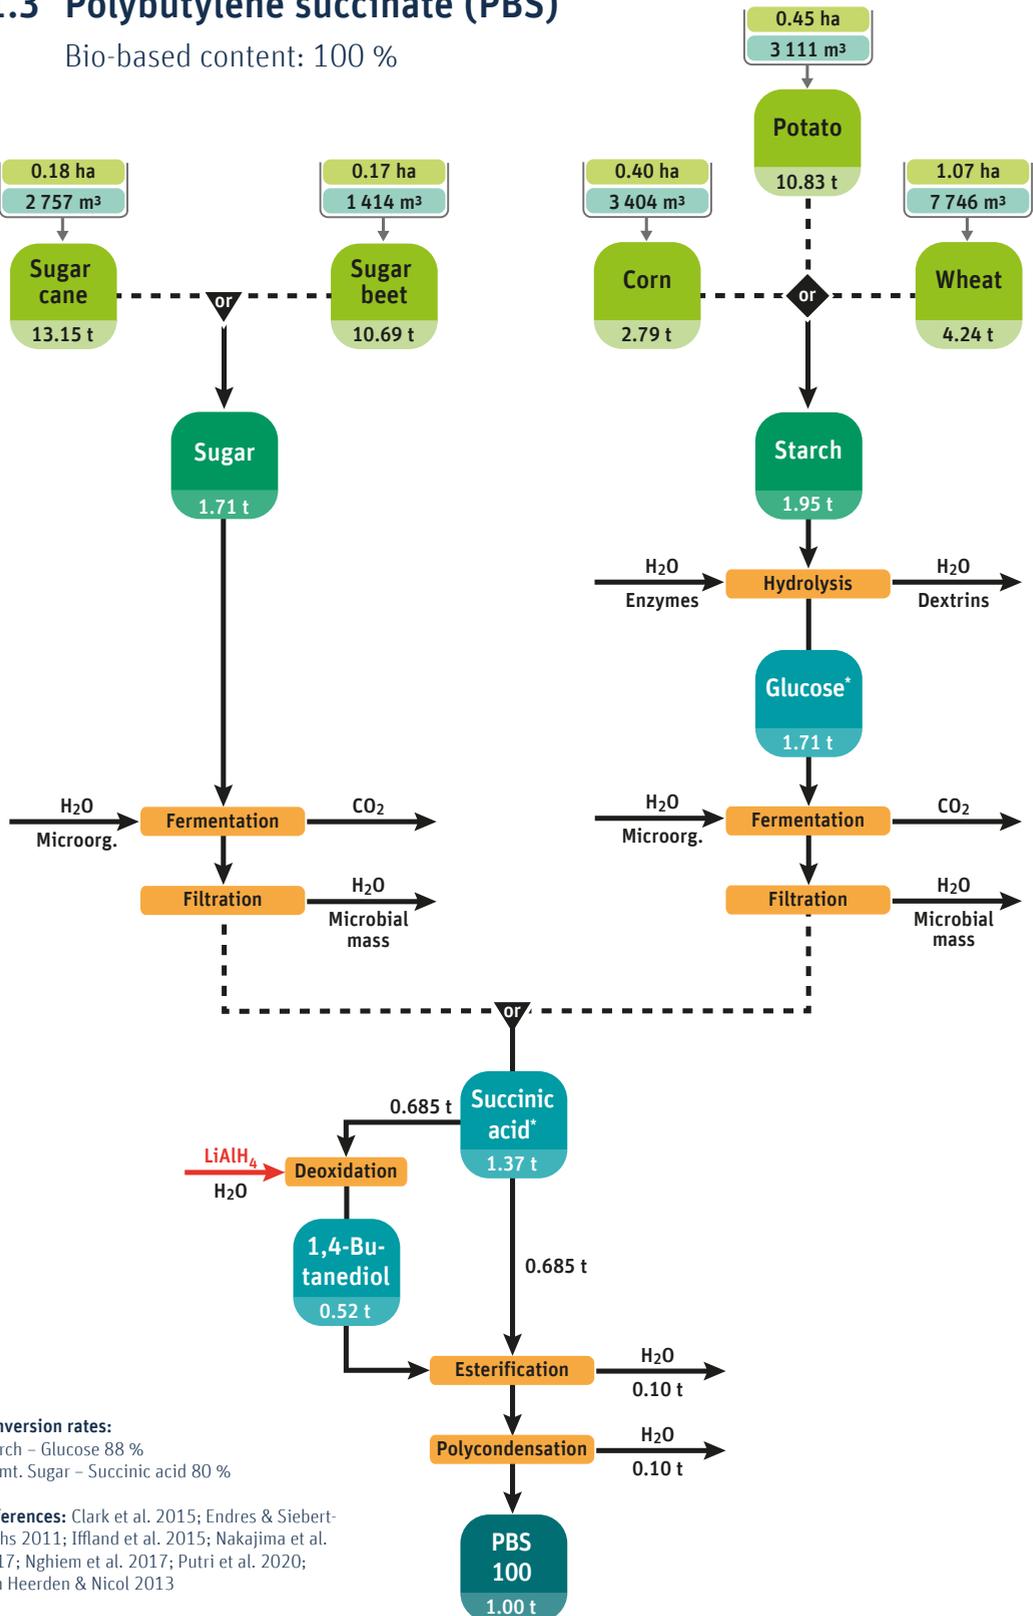


* Conversion rates:
 Starch – Glucose 88 %
 Fermt. Sugar – Succinic acid 80 %

References: Clark et al. 2015; Endres & Siebert-Raths 2011; Iffland et al. 2015; Nakajima et al. 2017; Nghiem et al. 2017; Putri et al. 2020; Van Heerden & Nicol 2013


PBS variations – Feedstock requirements in t (different feedstocks)

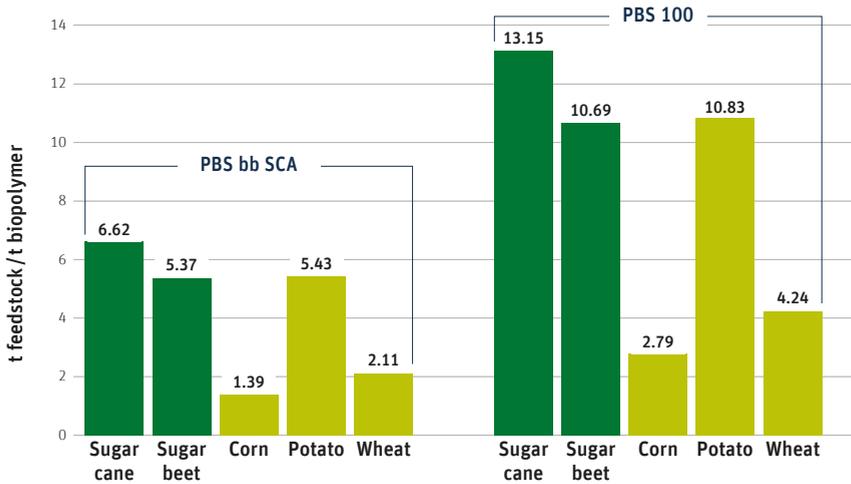

PBS variations – Land use in ha (different feedstocks)

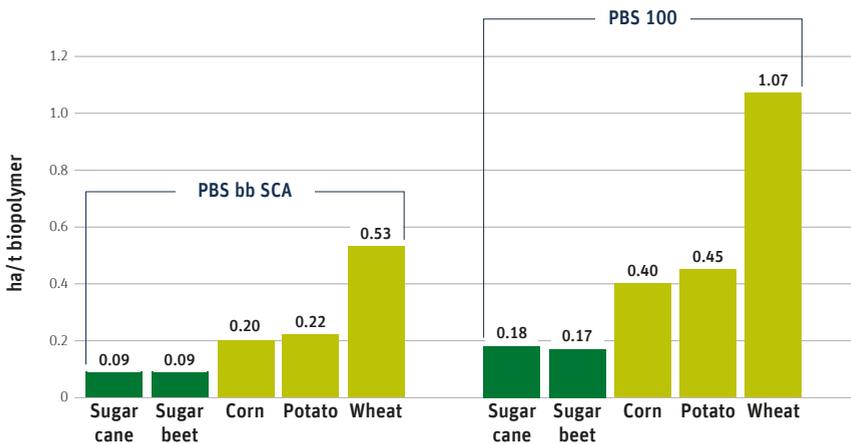


PBS variations – Water use in m³ (different feedstocks)

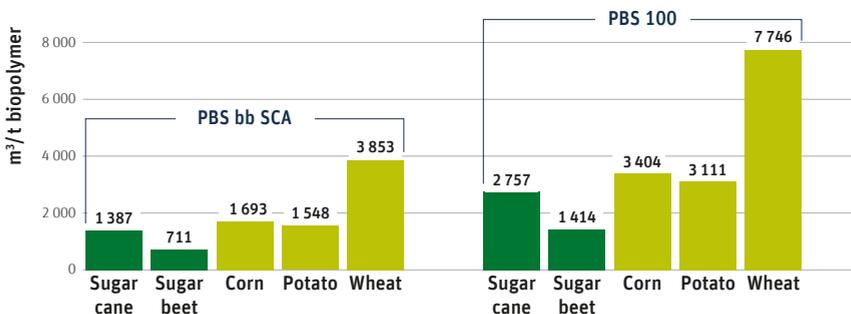

2.1.4 Polybutylene succinate adipate (PBSA)

with bio-based succinic acid (PBSA bb SCA)

Bio-based content: 33 %

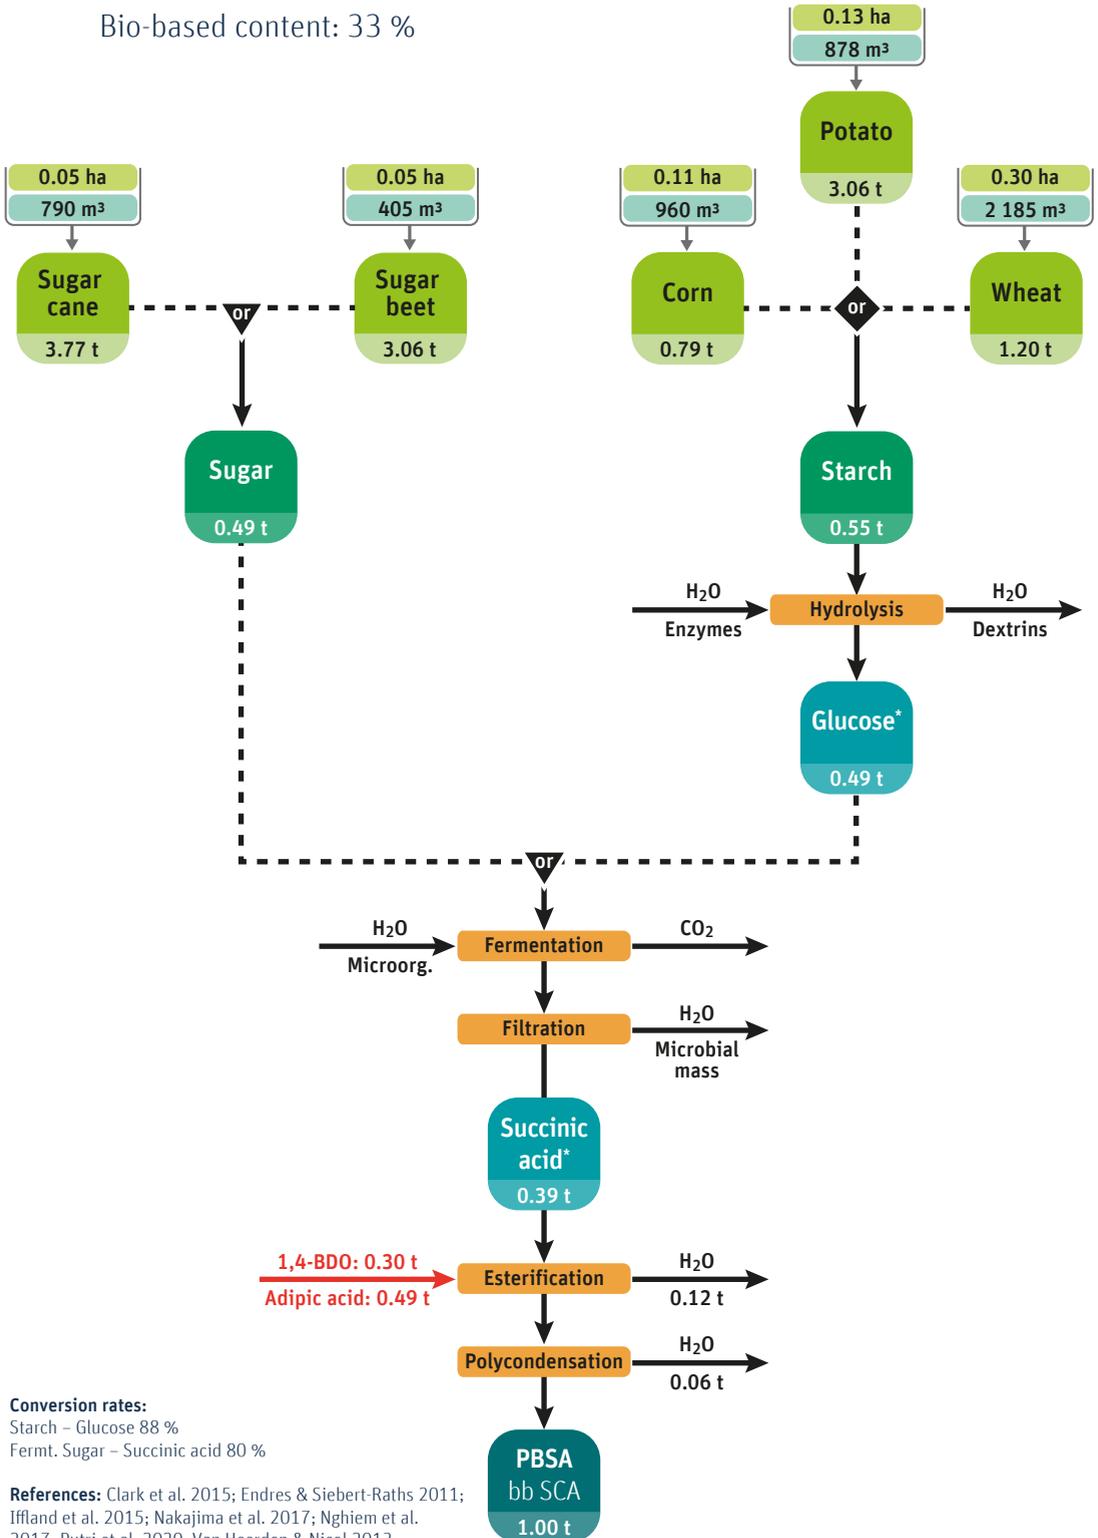


* Conversion rates:
Starch – Glucose 88 %
Fermt. Sugar – Succinic acid 80 %

References: Clark et al. 2015; Endres & Siebert-Raths 2011; Iffland et al. 2015; Nakajima et al. 2017; Nghiem et al. 2017; Putri et al. 2020; Van Heerden & Nicol 2013

2.1.4 Polybutylene succinate adipate (PBSA)

with bio-based succinic acid and 1,4-butanediol (PBSA bb SCA/BDO)

Bio-based content: 58 %

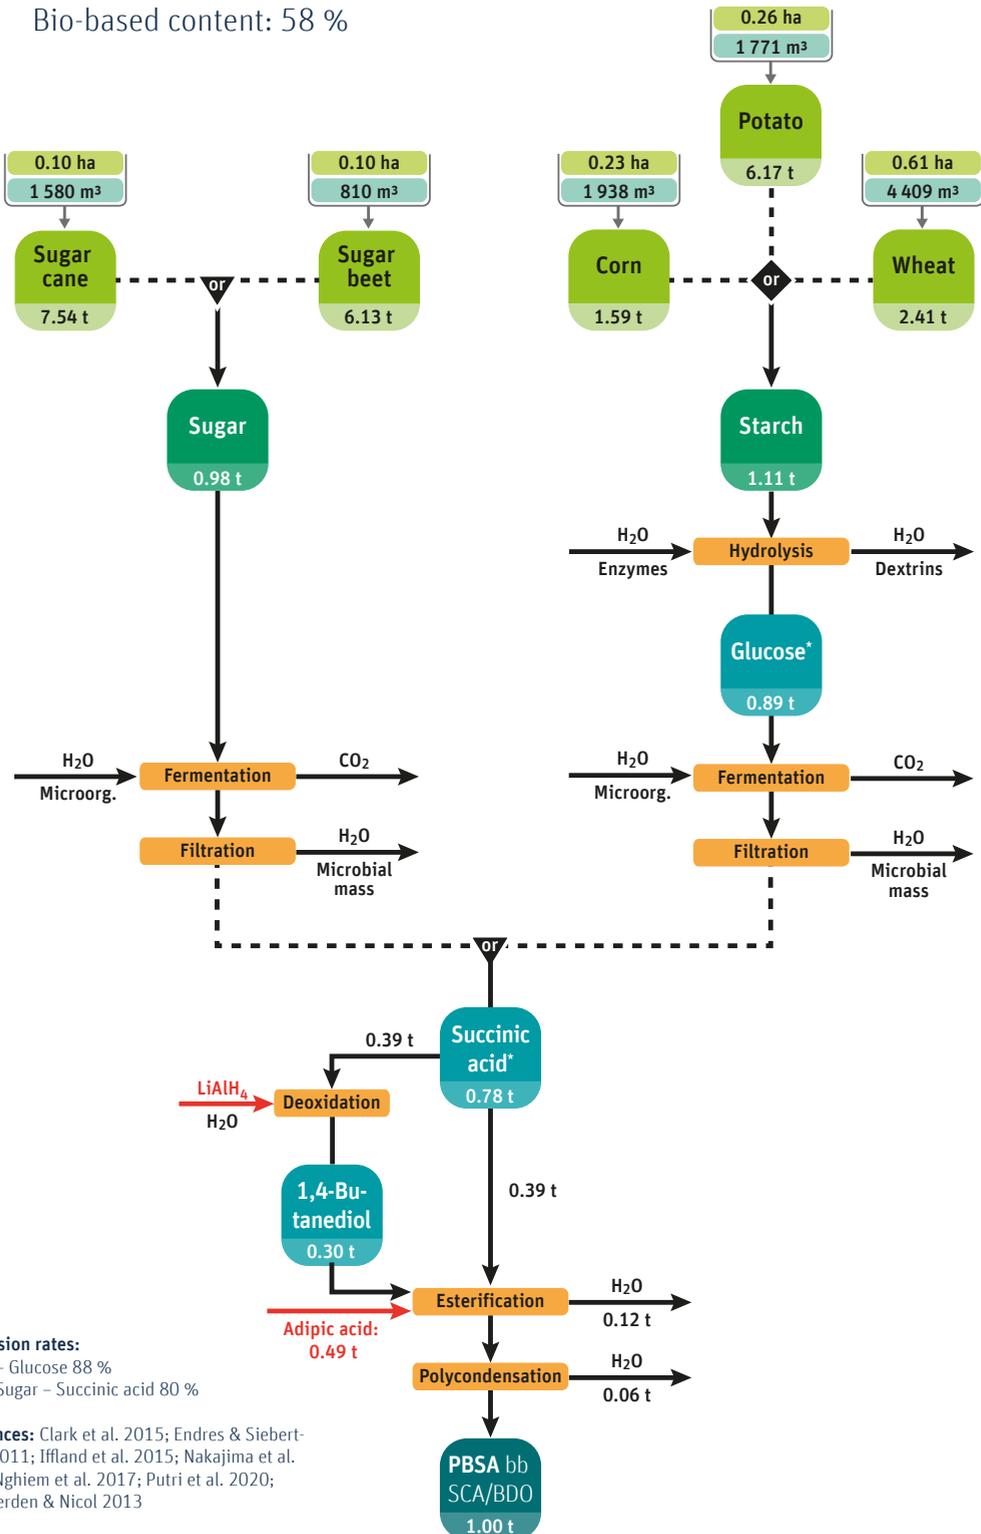


* Conversion rates:
 Starch – Glucose 88 %
 Fermt. Sugar – Succinic acid 80 %

References: Clark et al. 2015; Endres & Siebert-Raths 2011; Iffland et al. 2015; Nakajima et al. 2017; Nghiem et al. 2017; Putri et al. 2020; Van Heerden & Nicol 2013


PBSA variations – Feedstock requirements in t

(different feedstocks)

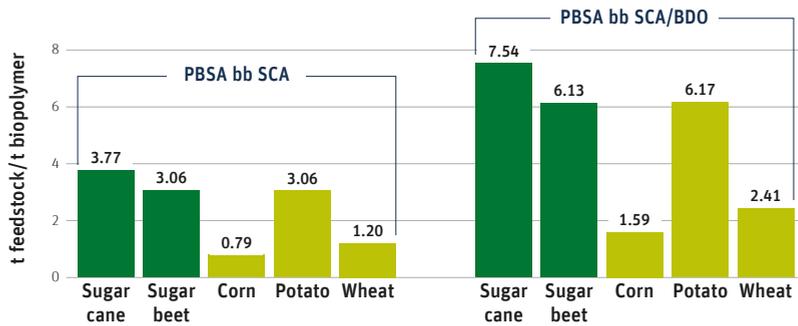


PBSA variations – Land use in ha

(different feedstocks)

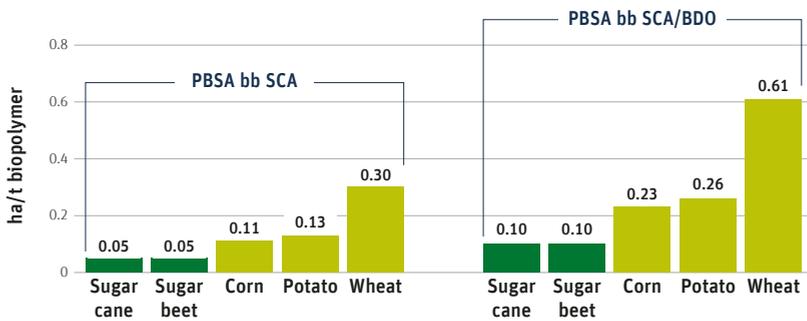

PBSA variations – Water use in m³


(different feedstocks)

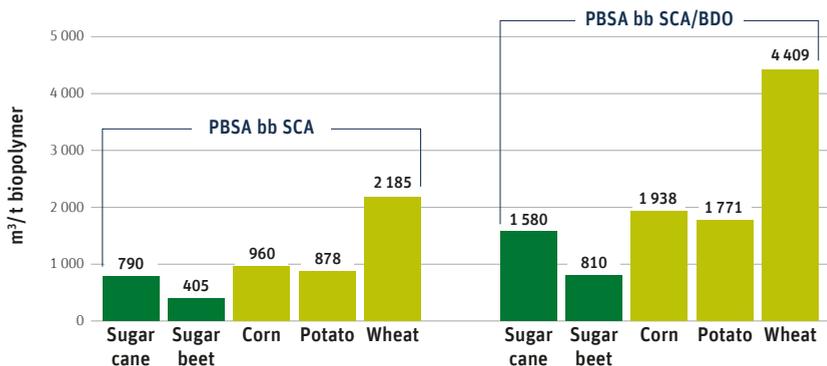

2.1.5 Polytrimethylene terephthalate (PTT)


with bio-based 1,3-propanediol (PTT bb PDO)

Bio-based content: 31 %

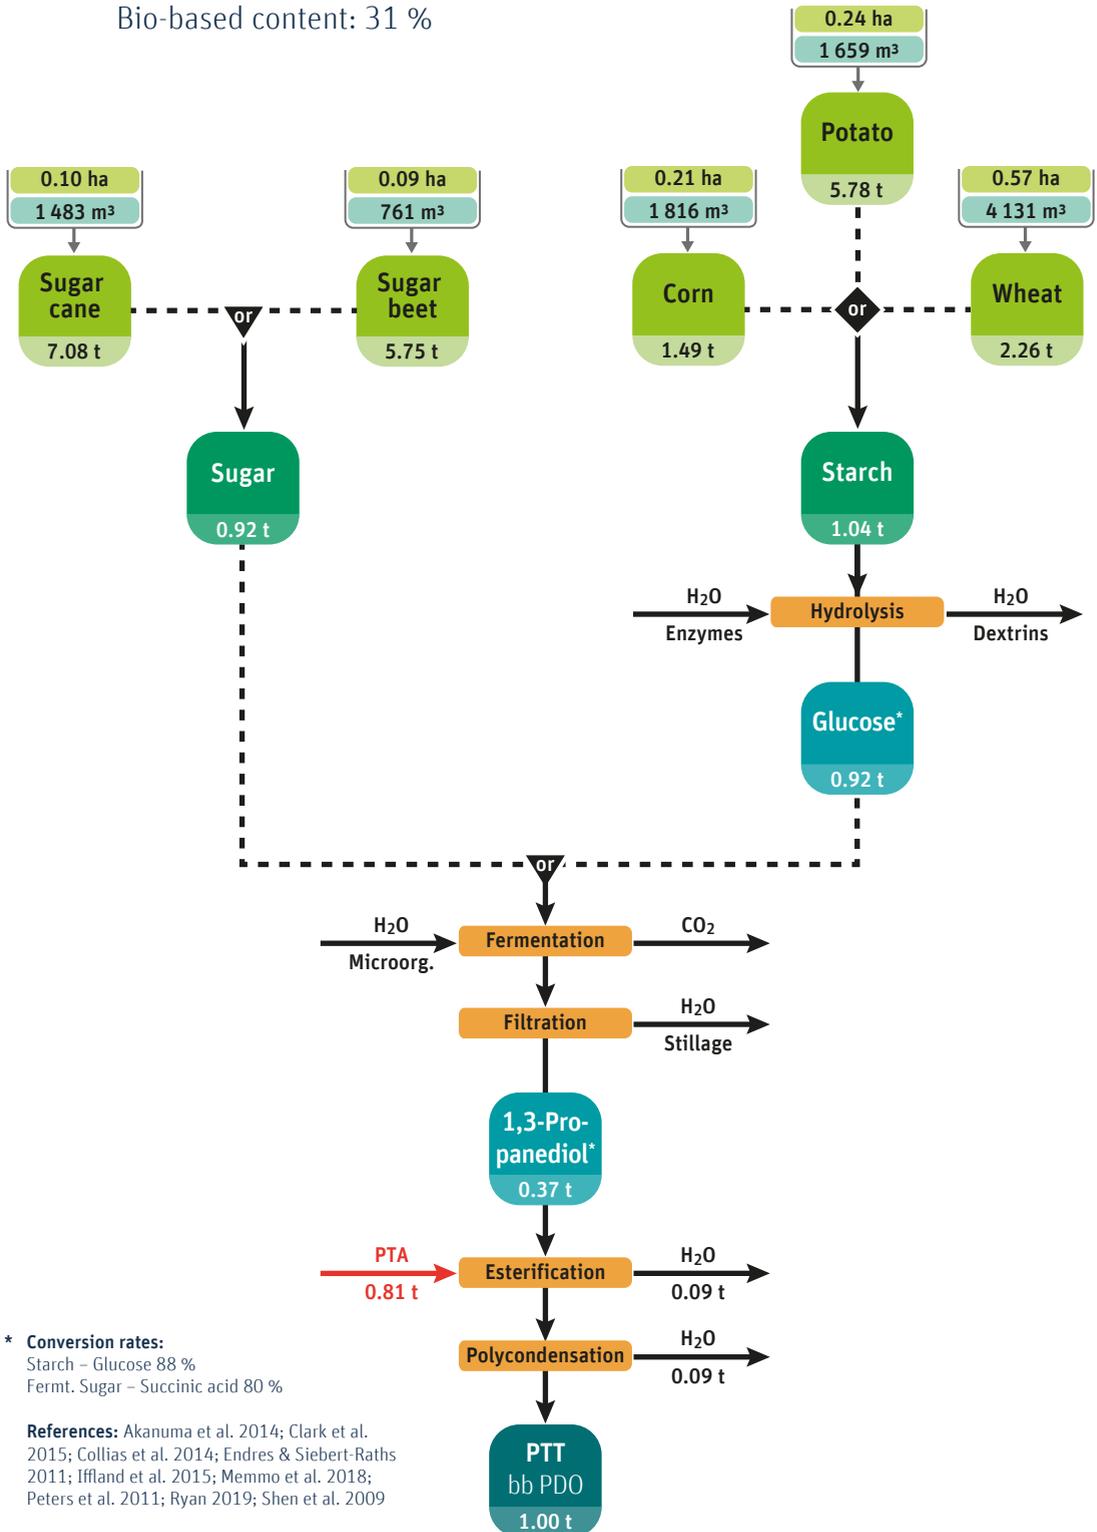

2.1.5 Polytrimethylene terephthalate (PTT)

Bio-based content: 100 %

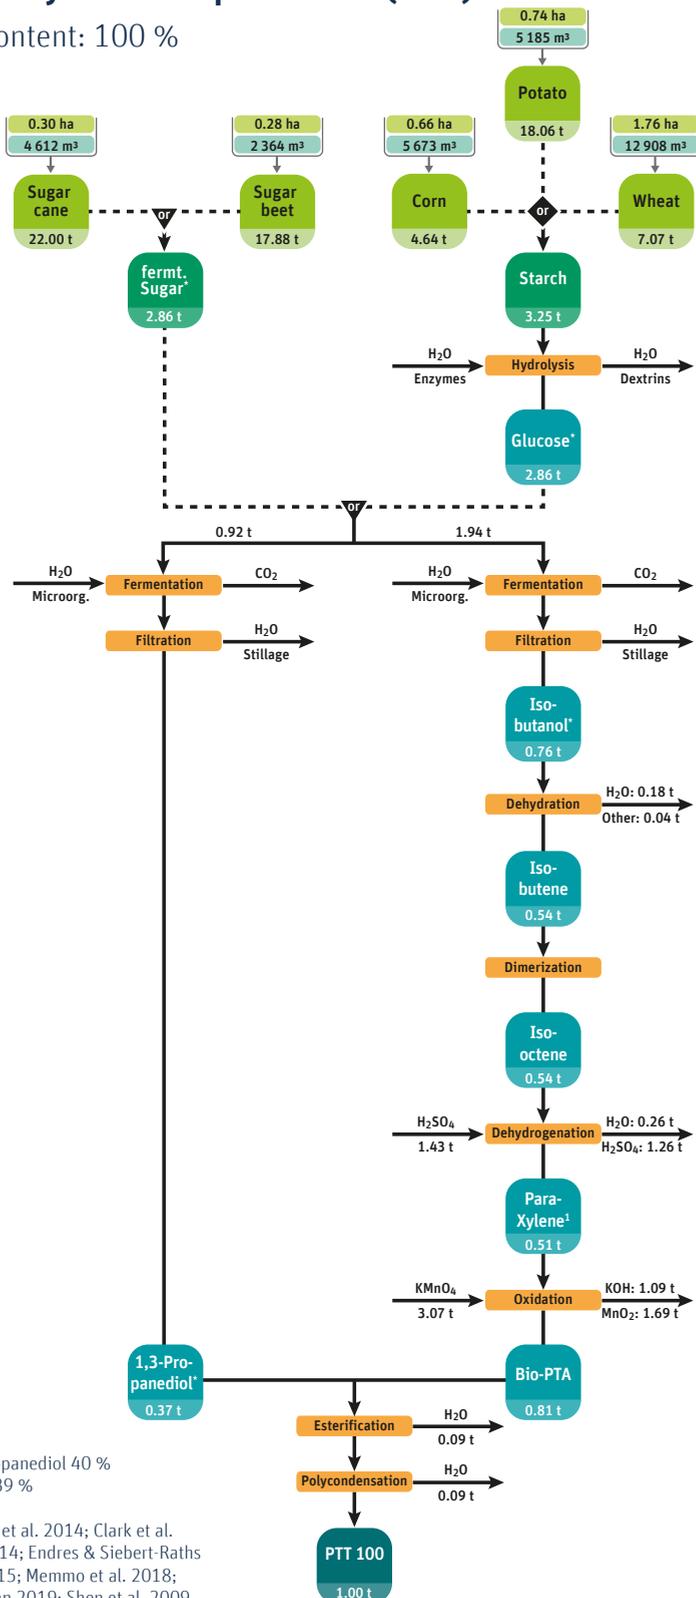


¹ GEVO-Process


- * **Conversion rates:**
 Starch – Glucose 88 %
 Fermt. Sugar – 1,3-Propanediol 40 %
 Glucose – Isobutanol 39 %

References: Akanuma et al. 2014; Clark et al. 2015; Collias et al. 2014; Endres & Siebert-Raths 2011; Iffland et al. 2015; Memmo et al. 2018; Peters et al. 2011; Ryan 2019; Shen et al. 2009


PTT variations – Feedstock requirements in t (different feedstocks)

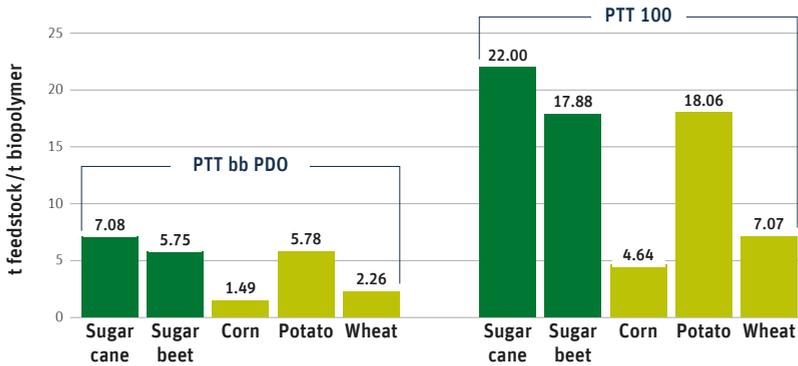

PTT variations – Land use in ha (different feedstocks)

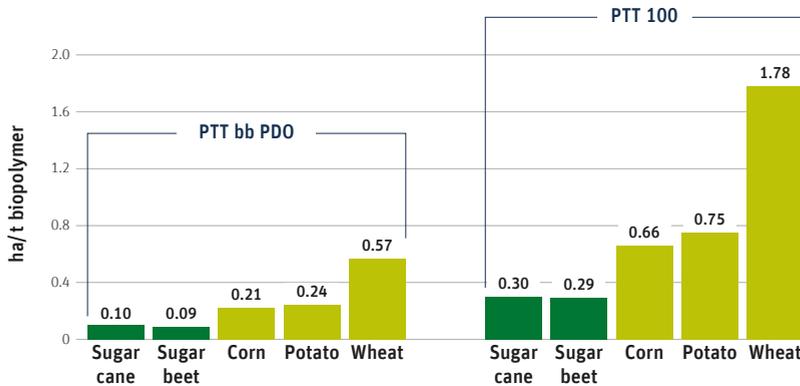


PTT variations – Water use in m³ (different feedstocks)

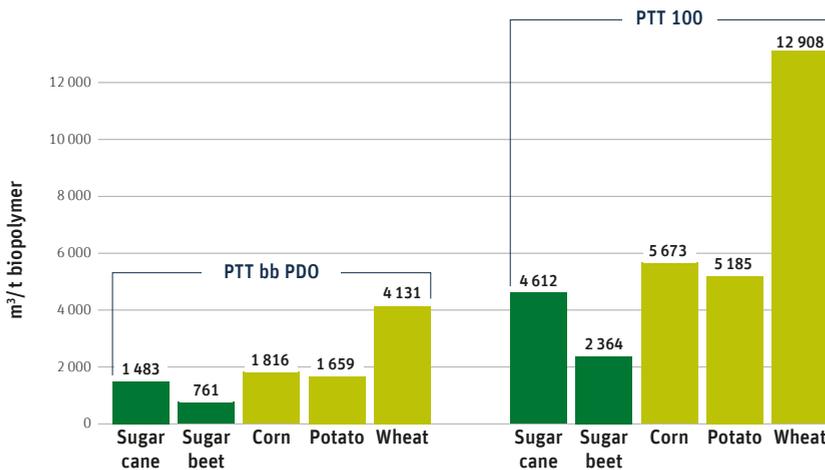

2.1.6 Polyethylene terephthalate (Bio-PET)

with bio-based ethanol

Bio-based content: 30 %

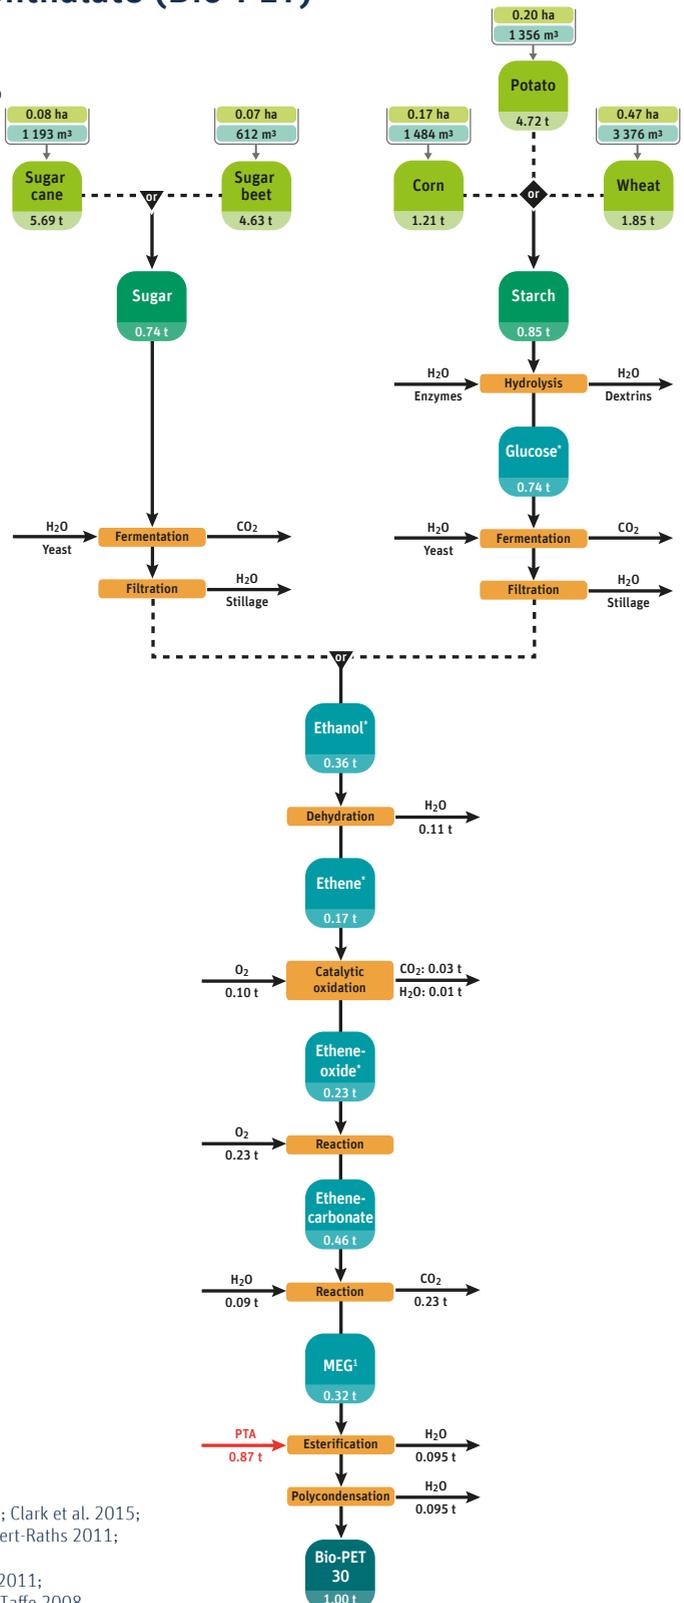


¹ Omega-Process (Shell)

- * **Conversion rates:**
 - Starch – Glucose 88 %
 - Glucose – Ethanol 48 %
 - Ethanol – Ethene 48 %
 - Ethene – Etheneoxide 85 %

References: Akanuma et al. 2014; Clark et al. 2015; Collias et al. 2014; Endres & Siebert-Raths 2011; Iffland et al. 2015; Kawabe 2010; Memmo et al. 2018; Peters et al. 2011; Ryan 2019; Siracusa et al. 2020; Taffe 2008

2.1.6 Polyethylene terephthalate (Bio-PET)

Bio-based content: 100 %

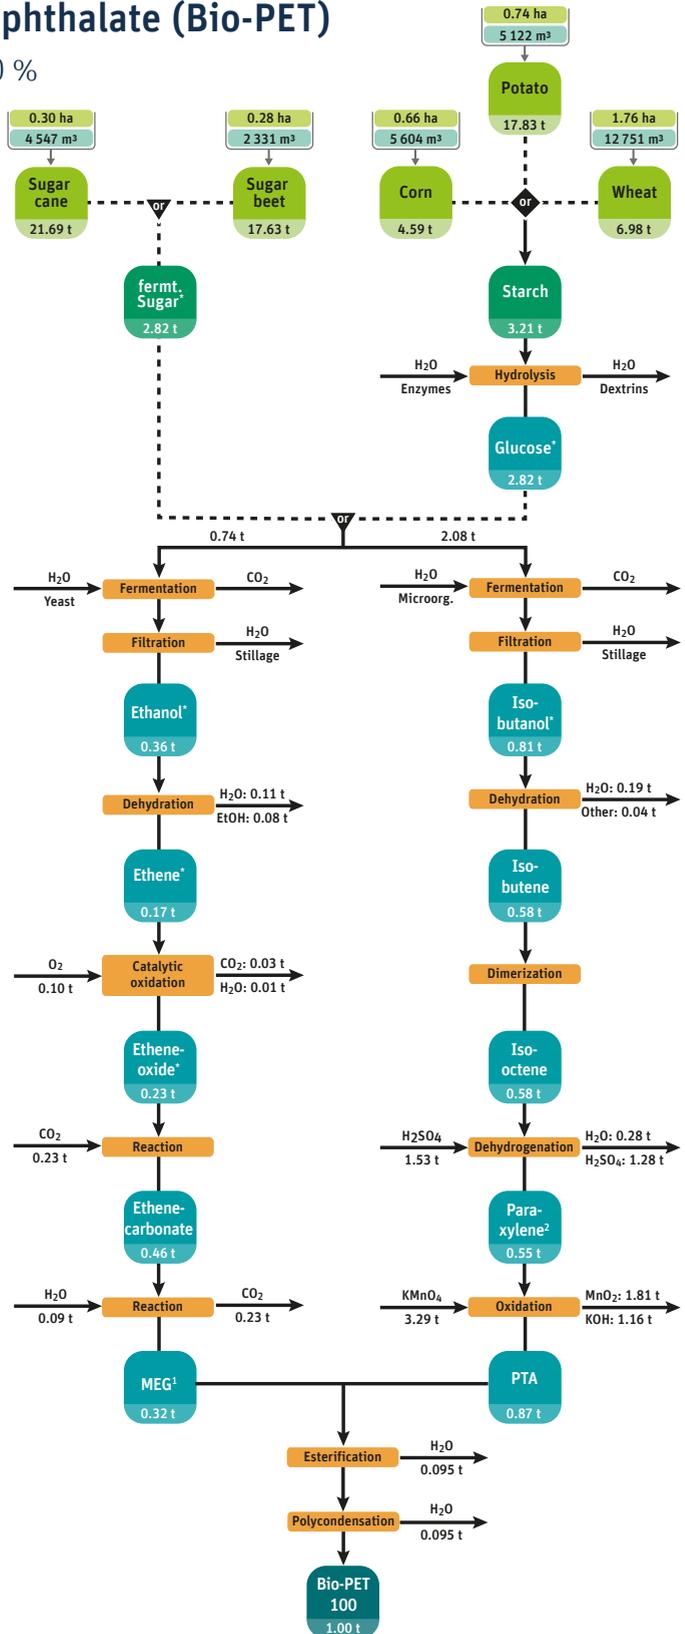

1 Omega-Process (Shell)


2 GEVO-Process

*** Conversion rates:**


- Starch – Glucose 88 %
- Glucose – Ethanol 48 %
- Glucose – Isobutanol 39 %
- Ethanol – Ethene 48 %
- Ethene – Etheneoxide 85 %

References: Akanuma et al. 2014; Clark et al. 2015; Collias et al. 2014; Endres & Siebert-Raths 2011; Iffland et al. 2015; Kawabe 2010; Memmo et al. 2018; Peters et al. 2011; Ryan 2019; Siracusa et al. 2020; Taffe 2008


Bio-PET variations – Feedstock requirements in t (different feedstocks)

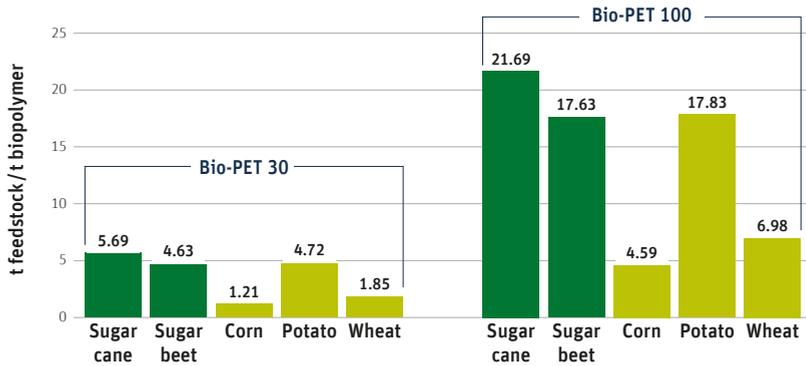

Bio-PET variations – Land use in ha (different feedstocks)

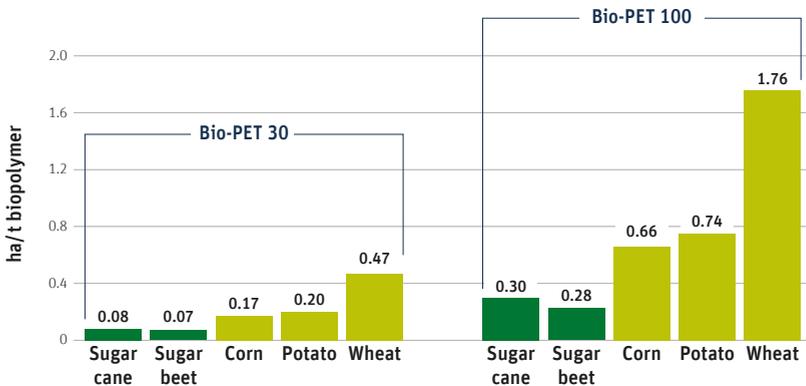


Bio-PET variations – Water use in m³ (different feedstocks)

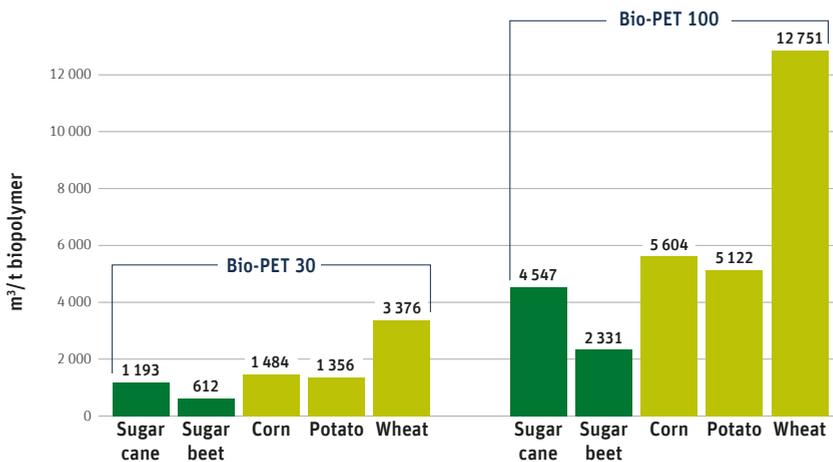

2.1.7 Polyethylene furanoate (PEF)

Bio-based content: 100 %

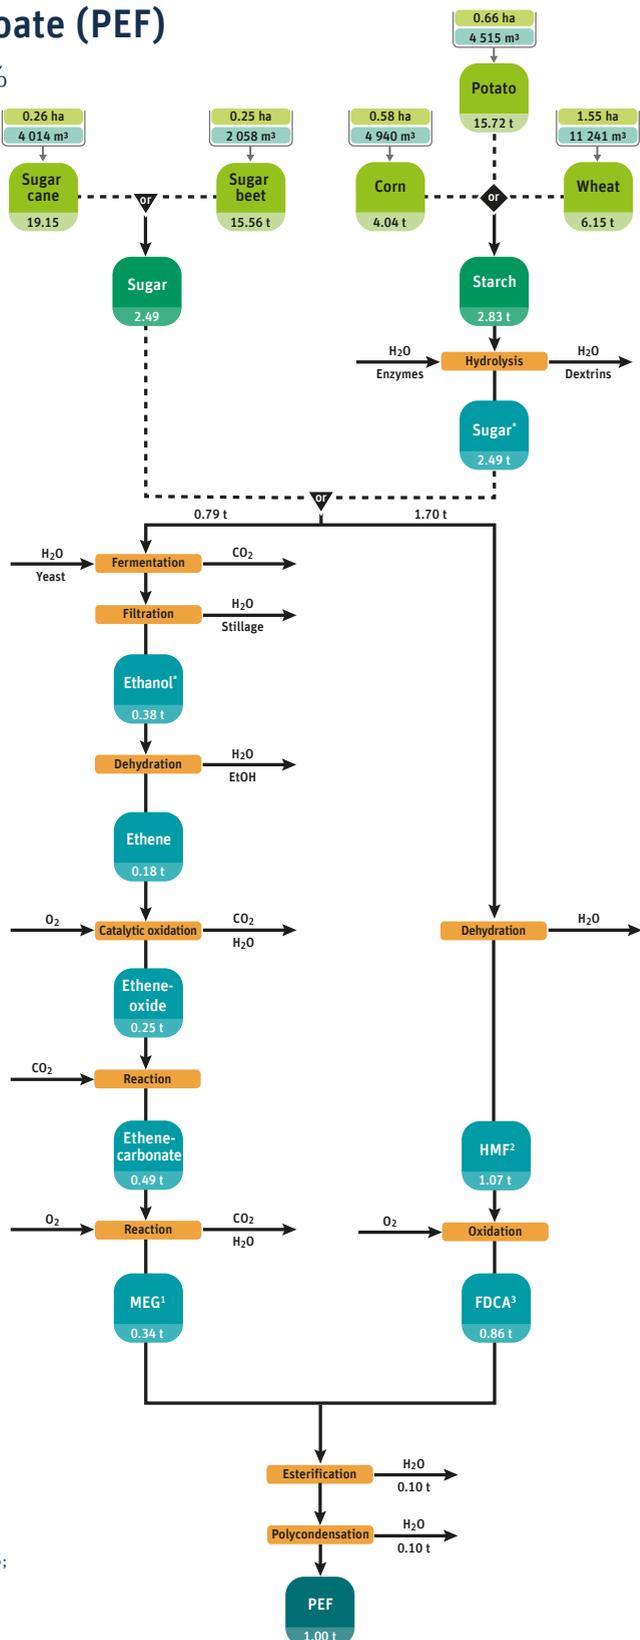


- ¹ MEG = Ethylene glycol
- ² Hydroxymethylfurfural
- ³ FDCA= 2,5-Furandicarboxylic acid


- * **Conversion rates:**
 - Starch – Sugar 88 %
 - Glucose – Ethanol 48 %
 - Ethanol – Ethene 48 %
 - Ethene – Etheneoxide 85 %
 - HMF – FDCA 80 %
 - Sugar (Fructose) – HMF 63 %

References: Andreeßen 2019; Eerhart et al. 2012; Hajid et al. 2018; Hwang et al. 2020; Iffland et al. 2015; Kawabe 2010; Nakajima et al. 2017; Taffe 2008; Van Putten 2011


PEF – Feedstock requirements in t (different feedstocks)

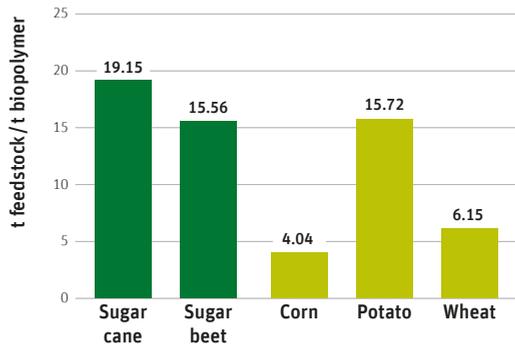

PEF – Land use in ha (different feedstocks)

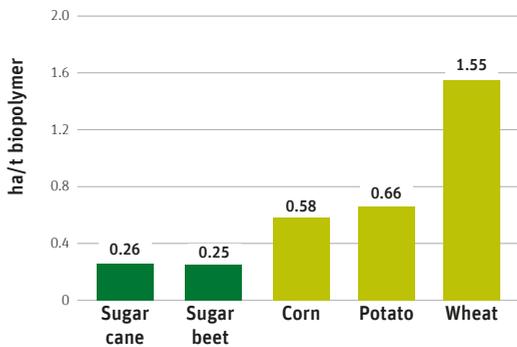


PEF – Water use in m³ (different feedstocks)

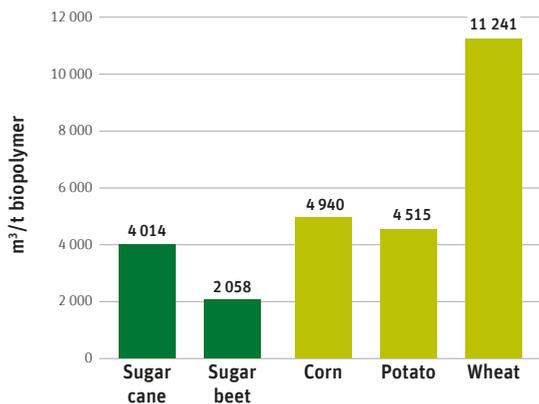

2.1.8 Polybutylene terephthalate (Bio-PBT)

with bio-based 1,4-butanediol (Bio-PBT bb BDO)

Bio-based content: 35 %

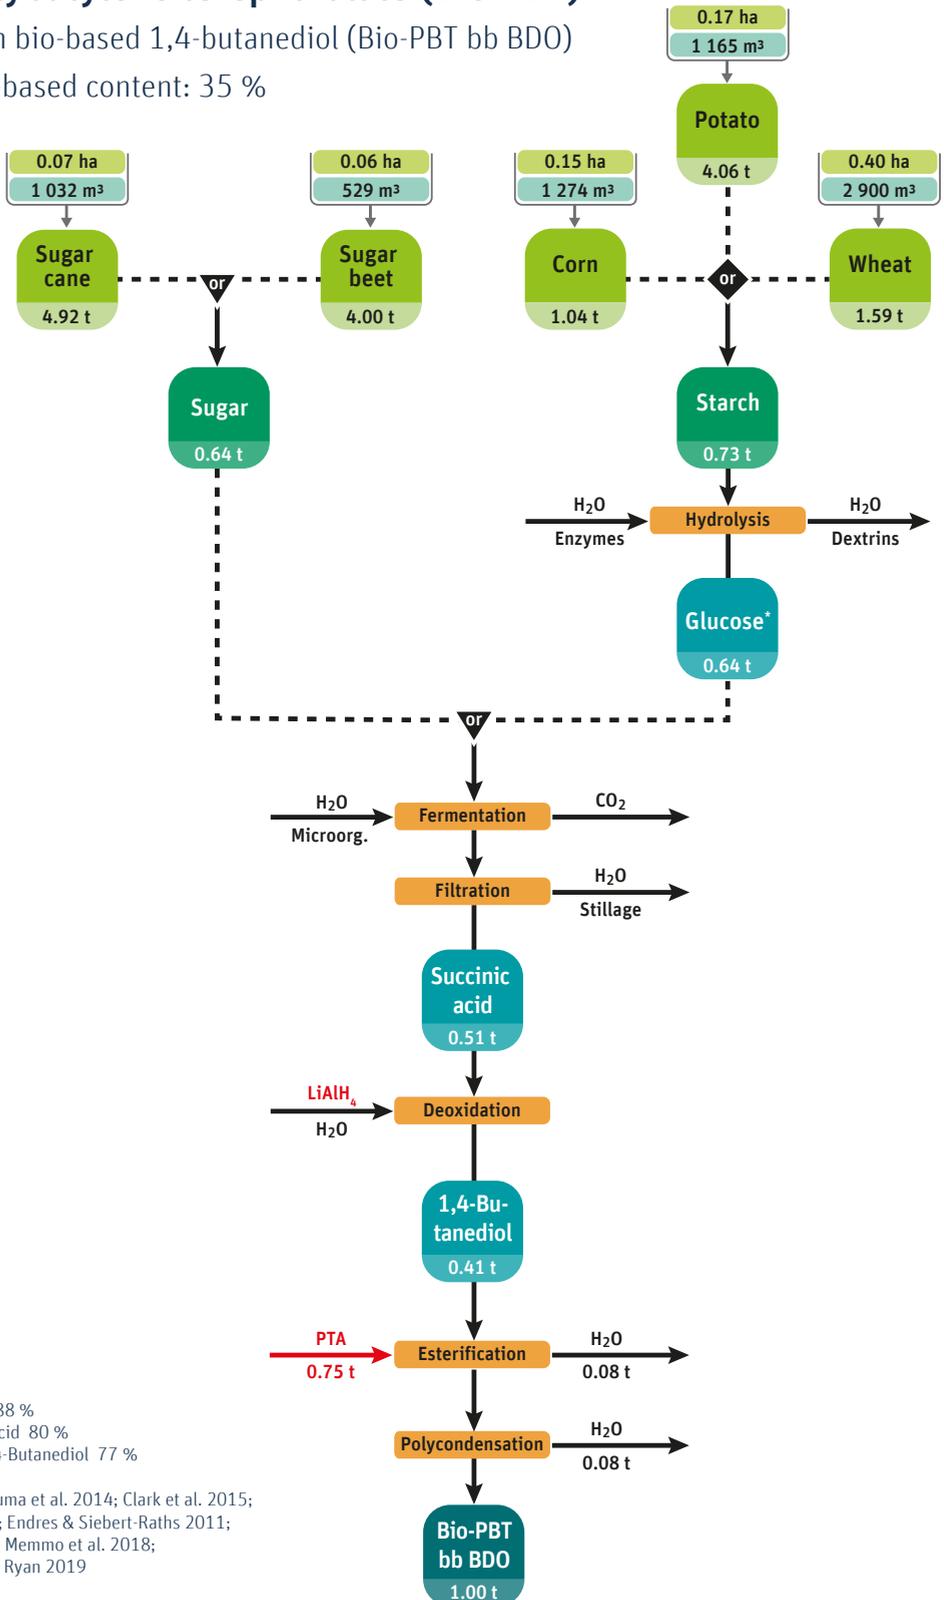

* Conversion rates:

Starch – Glucose 88 %


Sugar – Succinic acid 80 %

Succinic acid – 1,4-Butanediol 77 %

References: Akanuma et al. 2014; Clark et al. 2015; Collias et al. 2014; Endres & Siebert-Raths 2011; Iffland et al. 2015; Memmo et al. 2018; Peters et al. 2011; Ryan 2019

2.1.8 Polybutylene terephthalate (Bio-PBT)

Bio-based content: 100 %

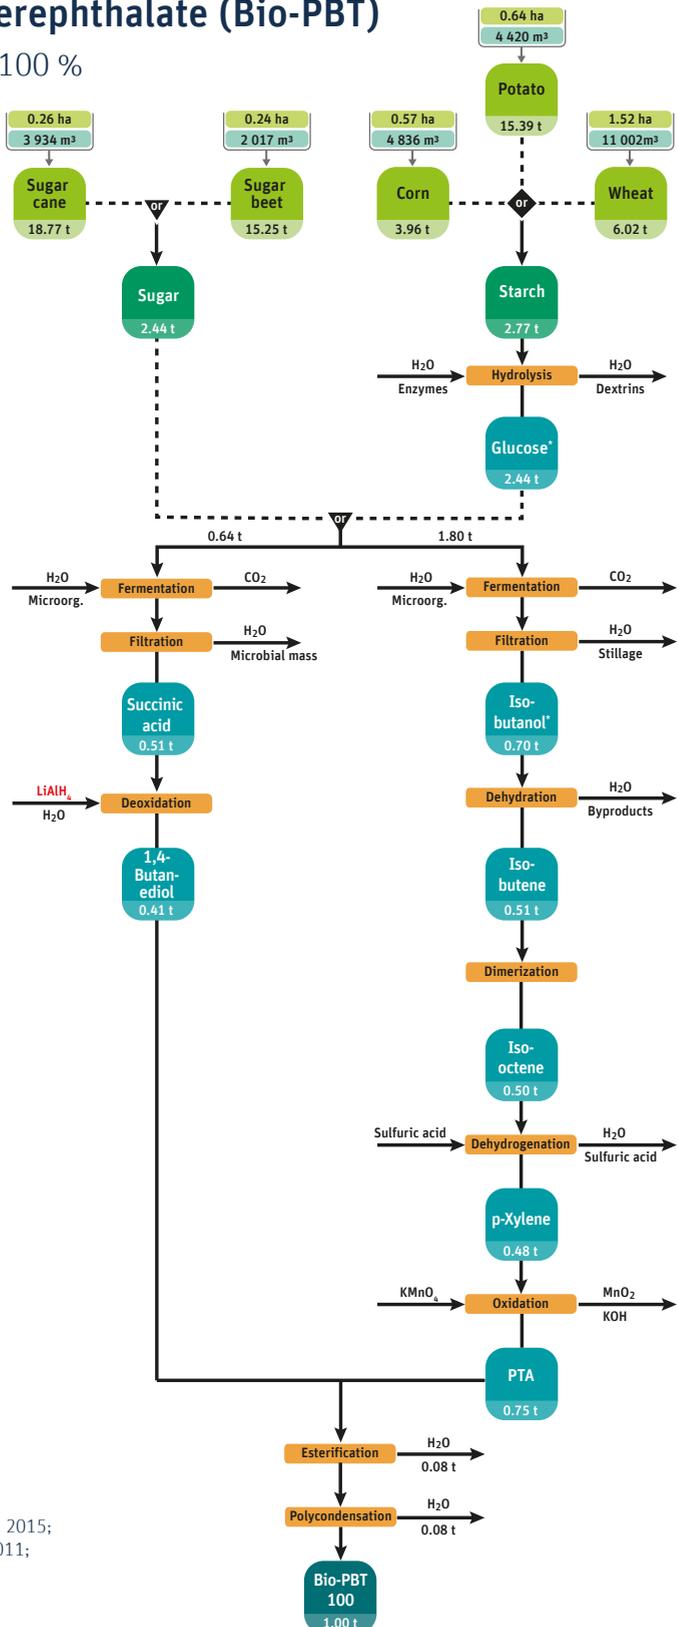


* Conversion rates:

- Starch – Glucose 88 %
- Glucose – Isobutanol 39 %
- Isobutanol – p-Xylene 68 %
- Sugar – Succinic acid 80 %
- Succinic acid – 1,4 Butanediol 77 %


References: Akanuma et al. 2014; Clark et al. 2015; Collias et al. 2014; Endres & Siebert-Raths 2011; Iffland et al. 2015; Memmo et al. 2018; Peters et al. 2011; Ryan 2019

Bio-PBT variations – Feedstock requirements in t


(different feedstocks)

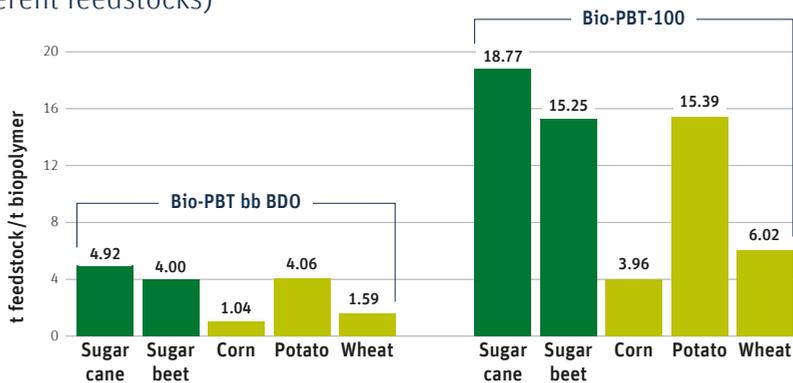

Bio-PBT variations – Land use in ha (different feedstocks)

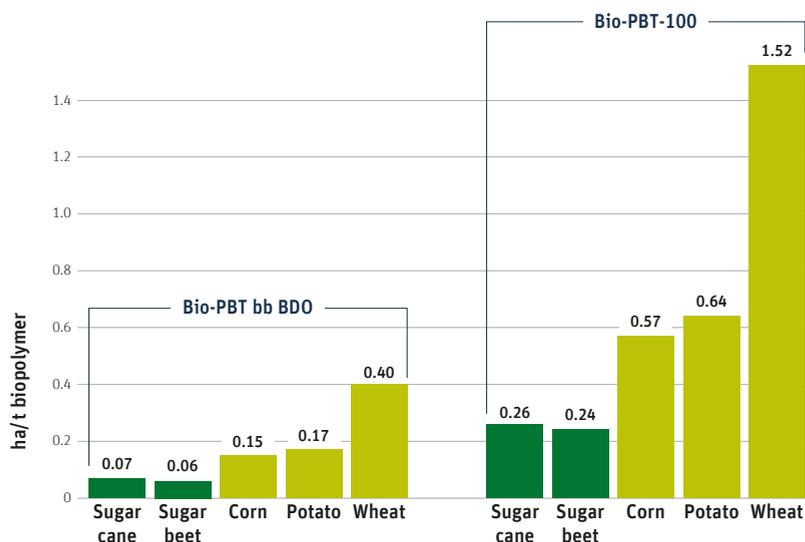


Bio-PBT variations – Water use in m³ (different feedstocks)

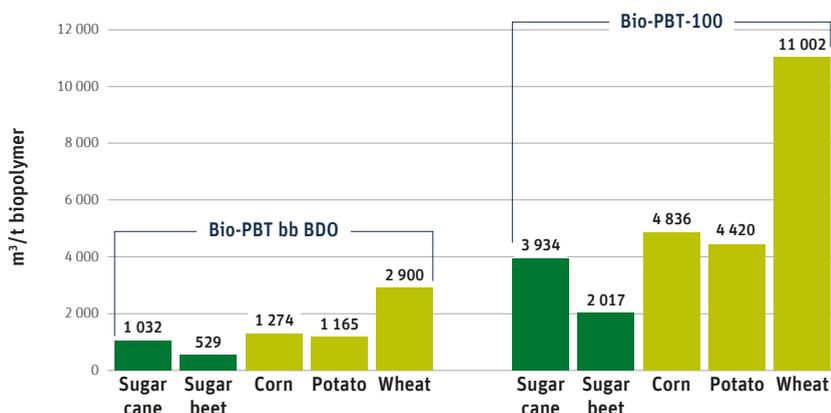

2.1.9 Polybutylene adipate terephthalate (Bio-PBAT)

with bio-based 1,4-butanediol (Bio-PBAT bb BDO)

Bio-based content: 37 %

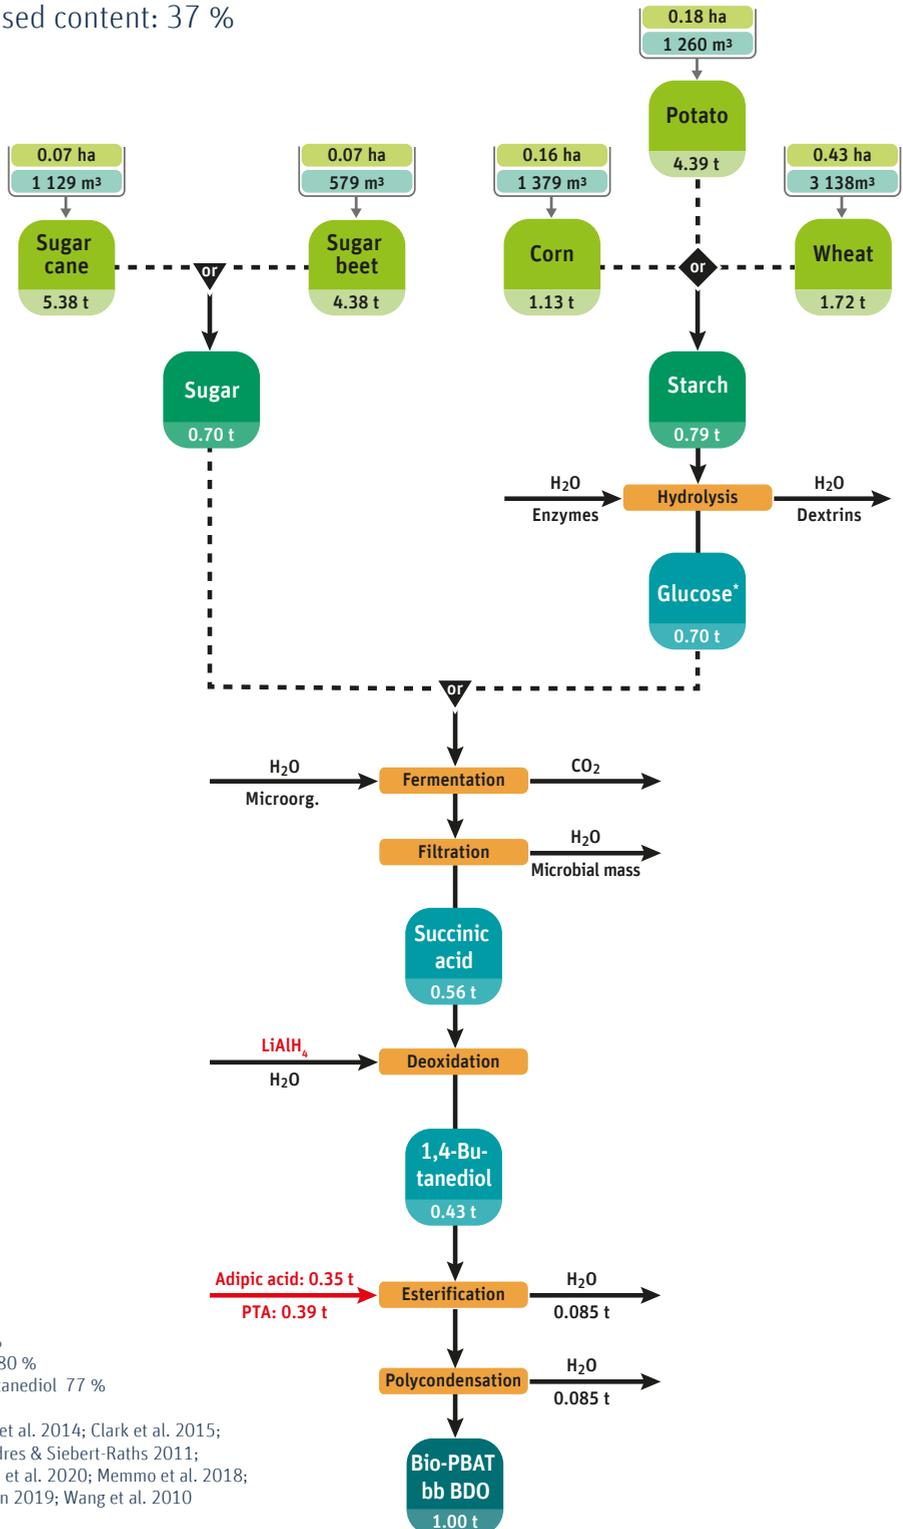

* Conversion rates:

Starch – Glucose 88 %

Sugar – Succinic acid 80 %

Succinic acid – 1,4-Butanediol 77 %


References: Akanuma et al. 2014; Clark et al. 2015; Collias et al. 2014; Endres & Siebert-Raths 2011; Iffland et al. 2015; Jian et al. 2020; Memmo et al. 2018; Peters et al. 2011; Ryan 2019; Wang et al. 2010

2.1.9 Polybutylene adipate terephthalate (Bio-PBAT)

with bio-based 1,4-butanediol and terephthalic acid

(Bio-PBAT bb BDO/PTA)

Bio-based content: 70 %

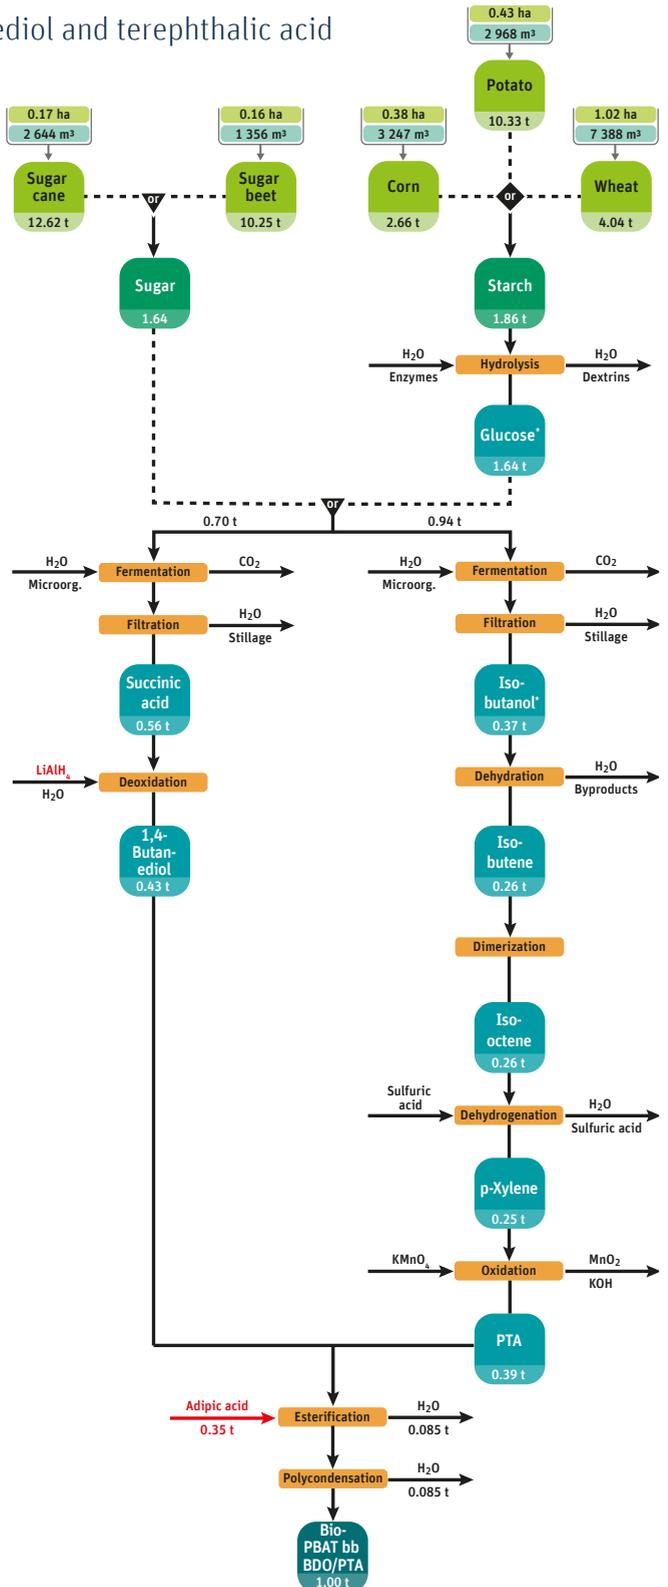


*** Conversion rates:**

- Starch – Glucose 88 %
- Glucose – Isobutanol 39 %
- Isobutanol – p-Xylene 68 %
- Sugar – Succinic acid 80 %
- Succinic acid – 1,4-Butanediol 77 %

References: Akanuma et al. 2014; Clark et al. 2015; Collias et al. 2014; Endres & Siebert-Raths 2011; Iffland et al. 2015; Jian et al. 2020; Memmo et al. 2018; Peters et al. 2011; Ryan 2019; Wang et al. 2010


Bio-PBAT variations – Feedstock requirements in t

(different feedstocks)

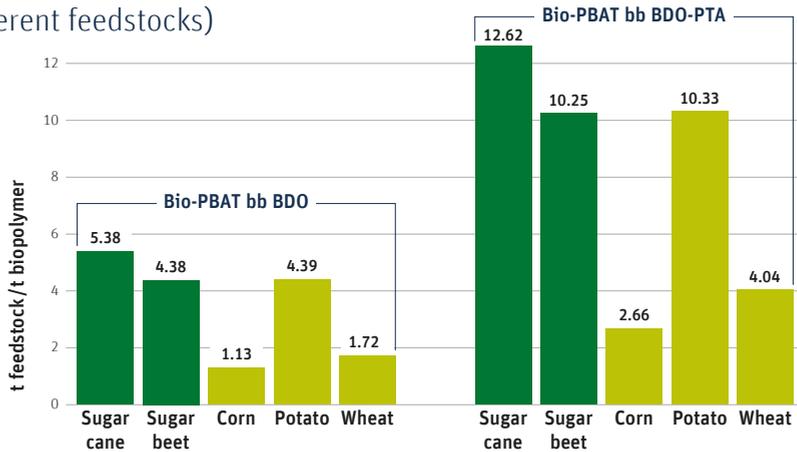


Bio-PBAT variations – Land use in ha

(different feedstocks)

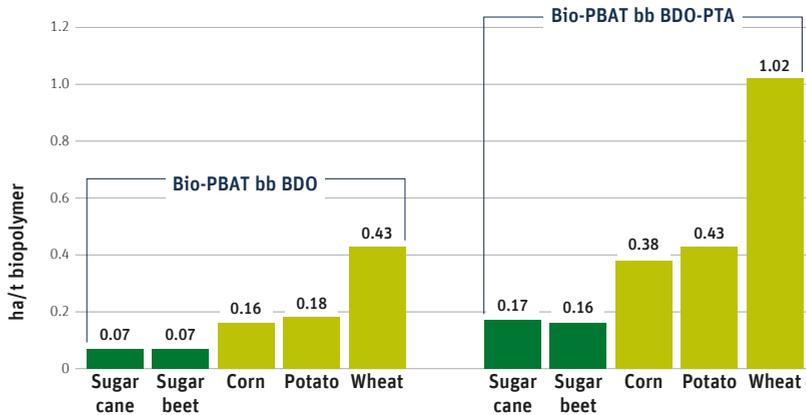

Bio-PBAT variations – Water use in m³


(different feedstocks)

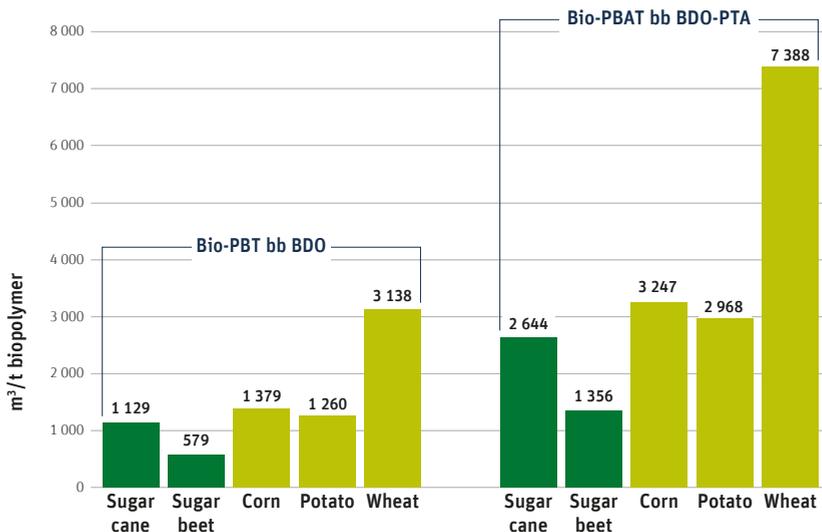

2.2 Bio-based polyolefins

2.2.1 Polyethylene (Bio-PE)


Bio-based content: 100 %

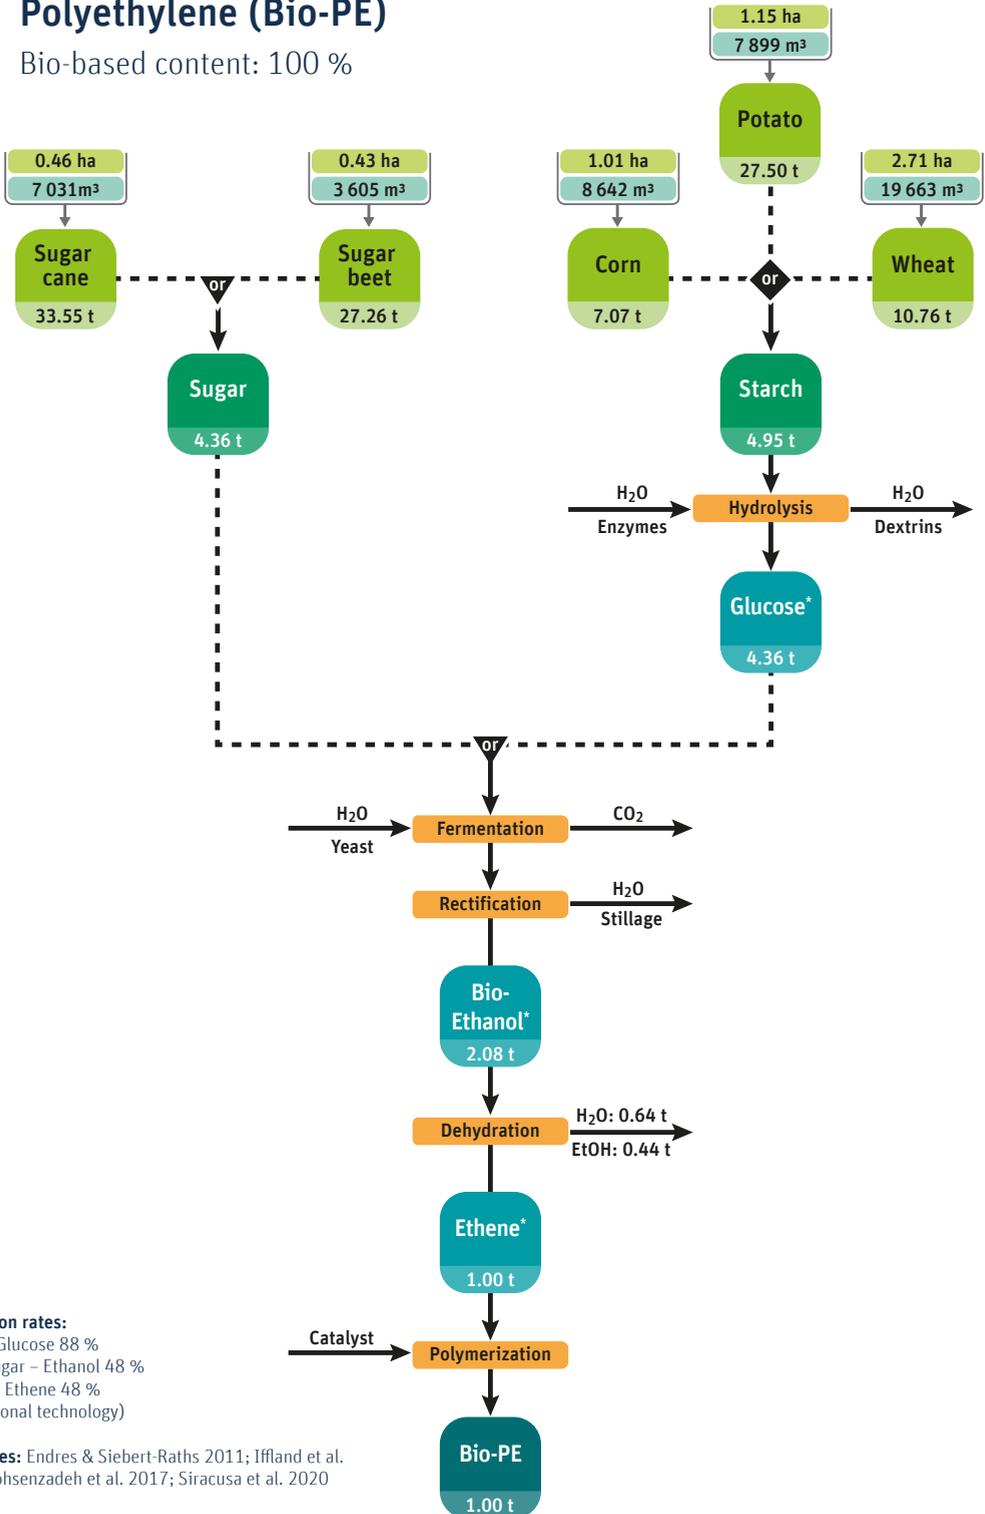


* Conversion rates:
 Starch – Glucose 88 %
 Fermt. Sugar – Ethanol 48 %
 Ethanol – Ethene 48 %
 (conventional technology)

References: Endres & Siebert-Raths 2011; Iffland et al. 2015; Mohsenzadeh et al. 2017; Siracusa et al. 2020

Bio-PE – Feedstock requirements in t (different feedstocks)

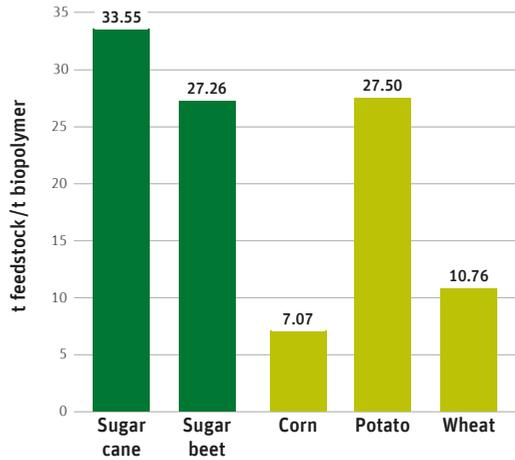


Bio-PE – Land use in ha (different feedstocks)

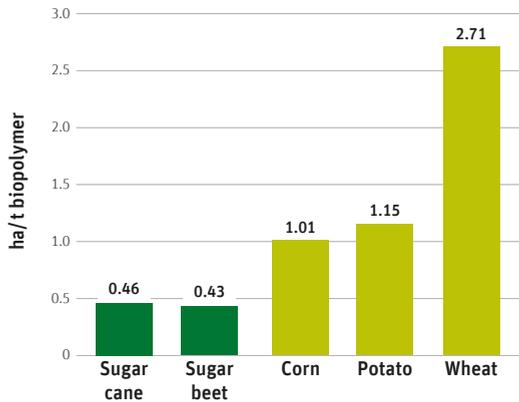


Bio-PE – Water use in m³

(different feedstocks)

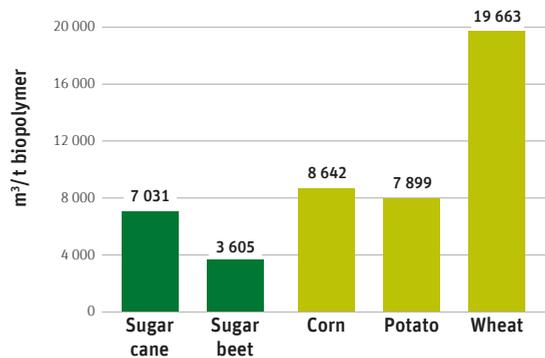

2.2.2 Polypropylene (Bio-PP)


Bio-based content: 100 %

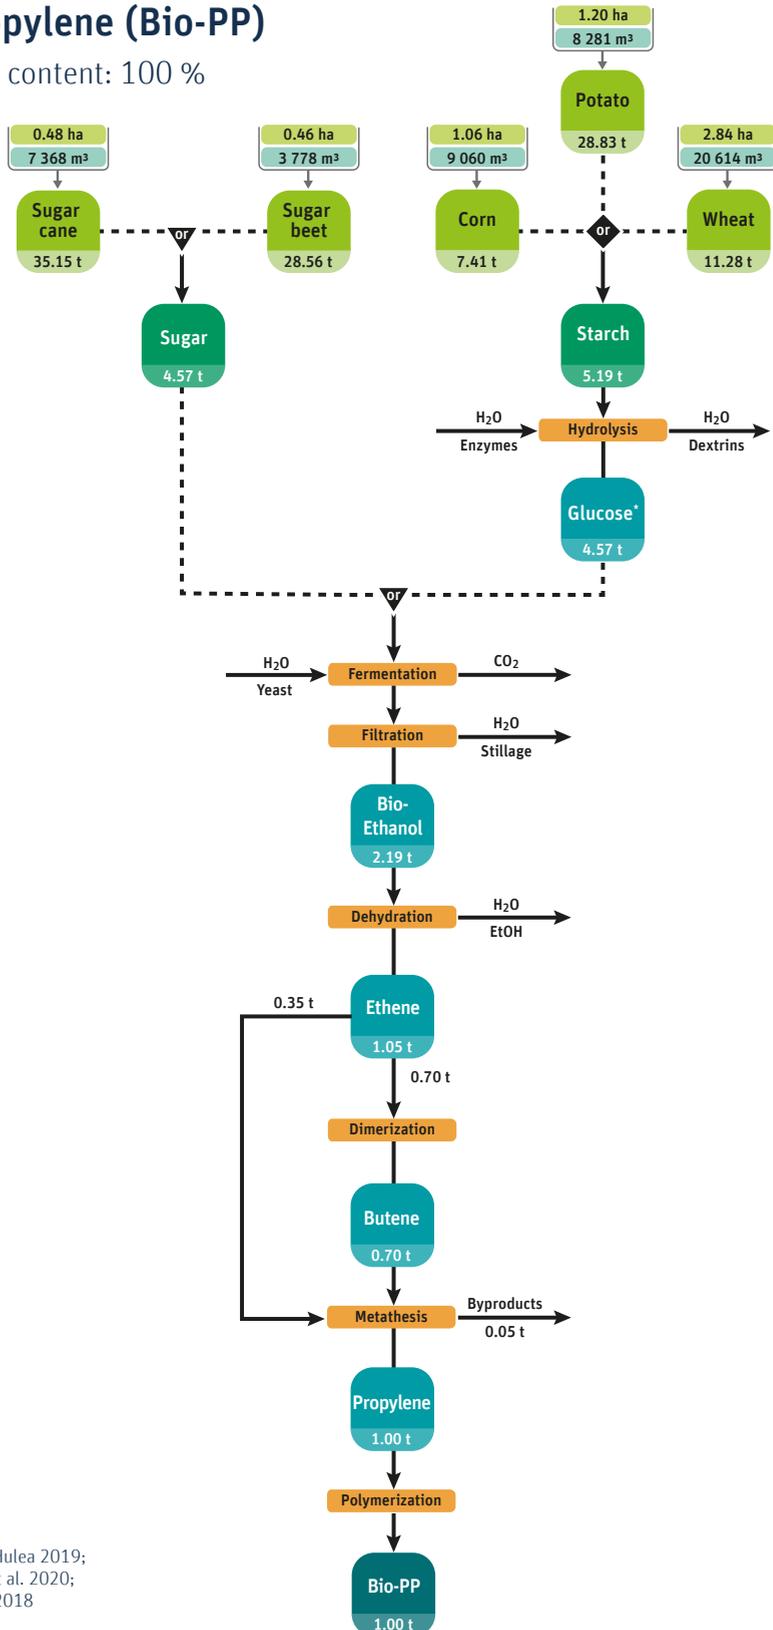


- * Conversion rates:
 Starch – Glucose 88 %
 Glucose – Ethanol 48 %
 Ethanol – Ethene 48 %
 Butene – Propylene 68 %

References: Andreeßen 2019; Hulea 2019; Mahdaviyani et al. 2010; Nessi et al. 2020; Siracusa et al. 2020; Zou et al. 2018


Bio-PP – Feedstock requirements in t (different feedstocks)

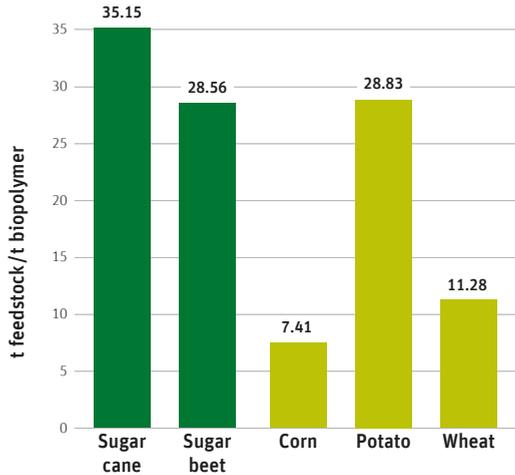

Bio-PP – Land use in ha (different feedstocks)

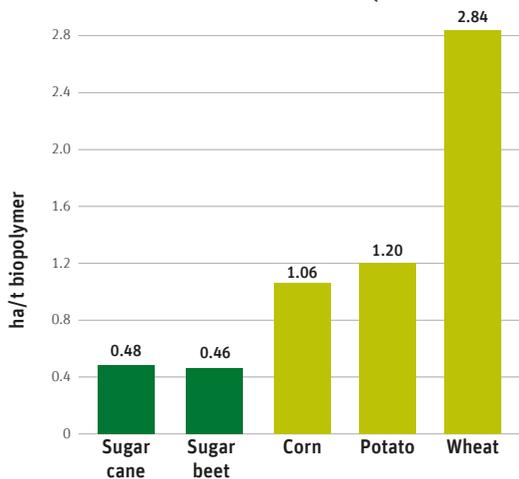

Bio-PP – Water use in m³ (different feedstocks)

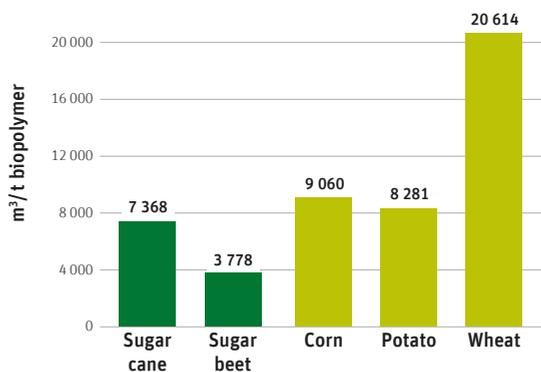


2.3 Bio-based polyamides (Bio-PA)

2.3.1 Homopolyamides

2.3.1.1 Bio-PA 6


Bio-based content: 100 %

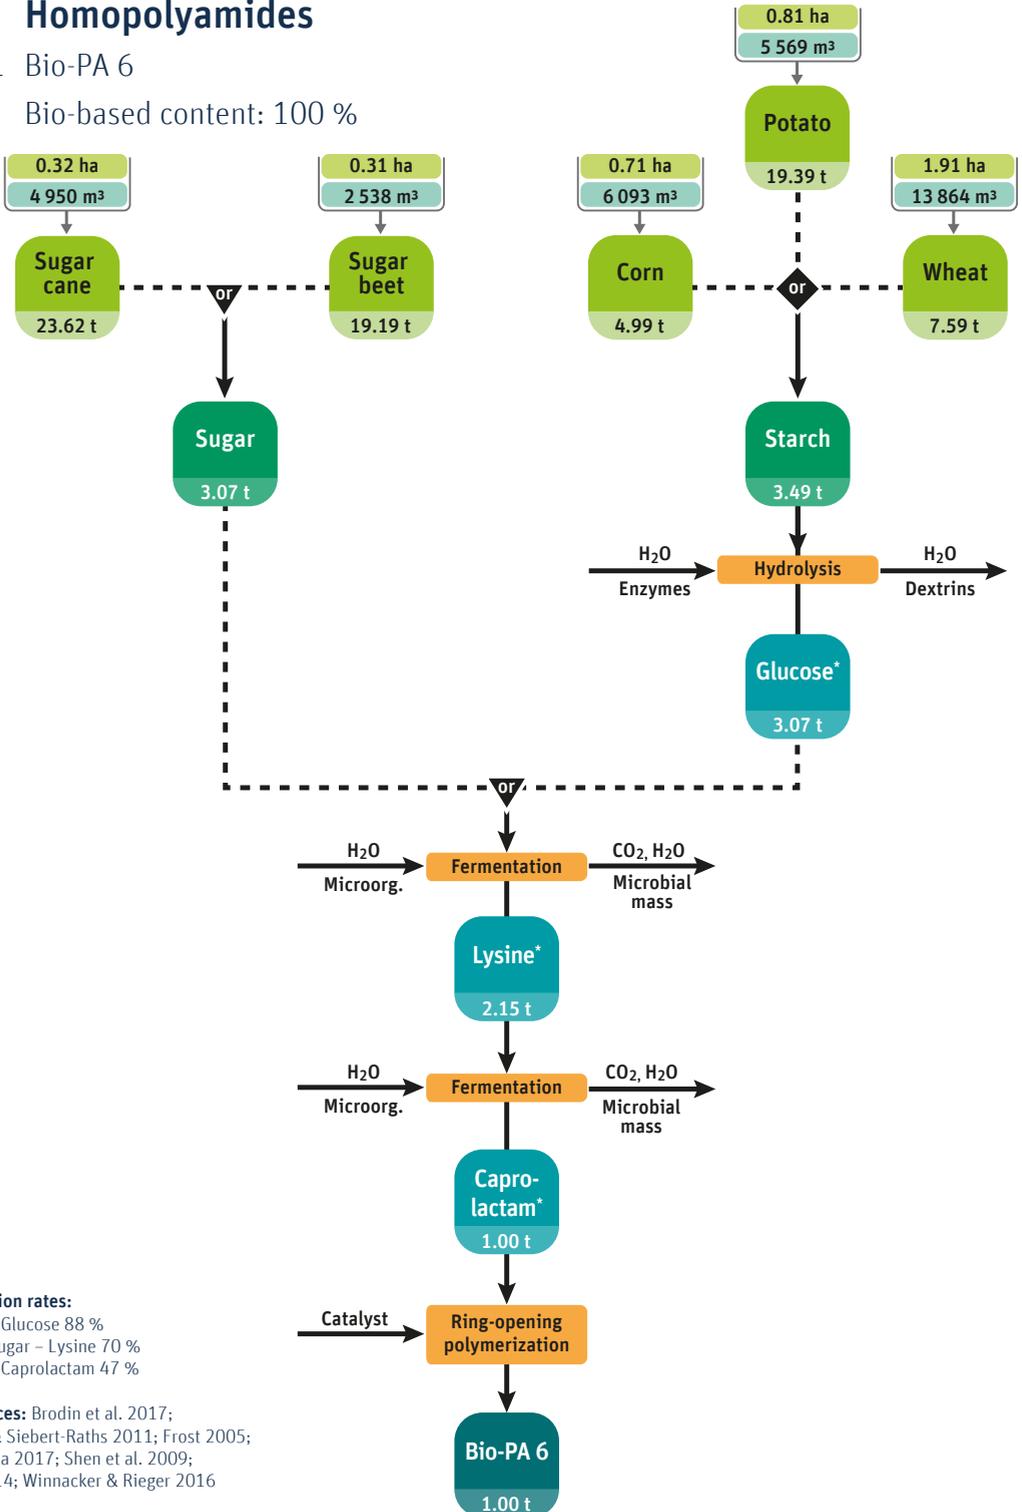


* Conversion rates:
 Starch – Glucose 88 %
 Fermt. Sugar – Lysine 70 %
 Lysine – Caprolactam 47 %

References: Brodin et al. 2017;
 Endres & Siebert-Raths 2011; Frost 2005;
 Kyulavska 2017; Shen et al. 2009;
 Türk 2014; Winnacker & Rieger 2016


Bio-PA 6 – Feedstock requirements in t (different feedstocks)

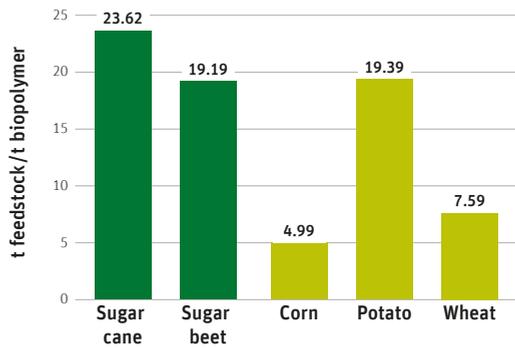

Bio-PA 6 – Land use in ha (different feedstocks)

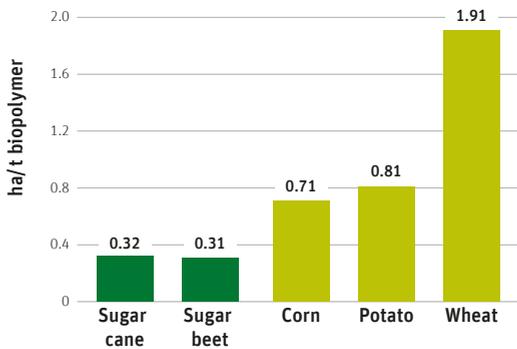


Bio-PA 6 – Water use in m³ (different feedstocks)

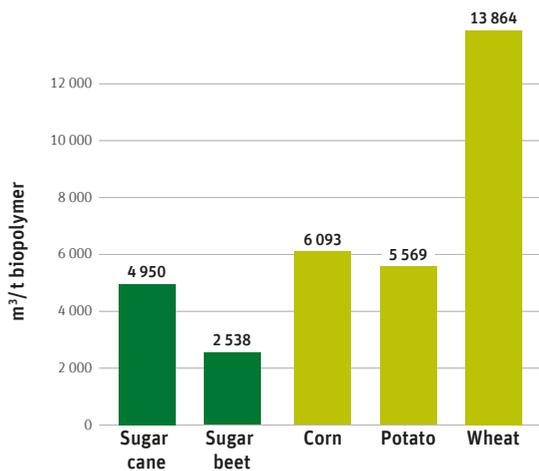

2.3.1 Homopolyamides

2.3.1.2 Bio-PA 11

Bio-based content: 100 %

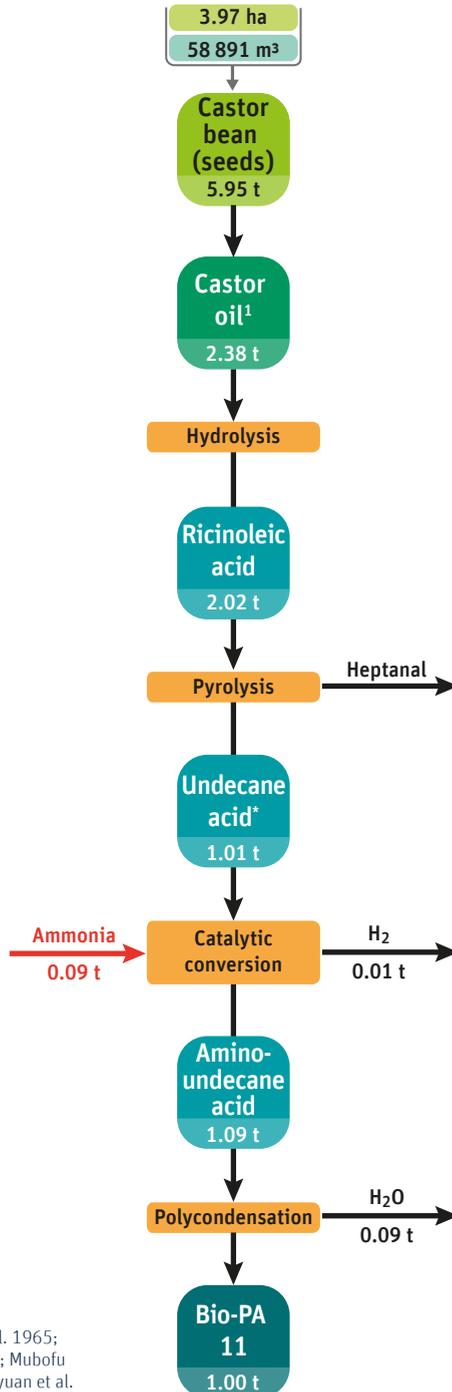

¹ One harvest per year


* Conversion rates:
Ricinoleic acid – Undecane acid 50 %

References: Devaux et al. 2011; Diamond et al. 1965; Endres & Siebert-Raths 2011; Kyulavska 2017; Mubofu 2016; Radzik et al. 2020; Shen et al. 2009; Siyuan et al. 2019; Türk 2014; Winnacker & Rieger 2016

2.3.2 Copolyamides

2.3.2.1 Bio-PA 4.10 – Bio-PA 5.10 – Bio-PA 6.10

Bio-based contents: Bio-PA 4.10: 70 %, Bio-PA 5.10: 66 %, Bio-PA 6.10: 64 %

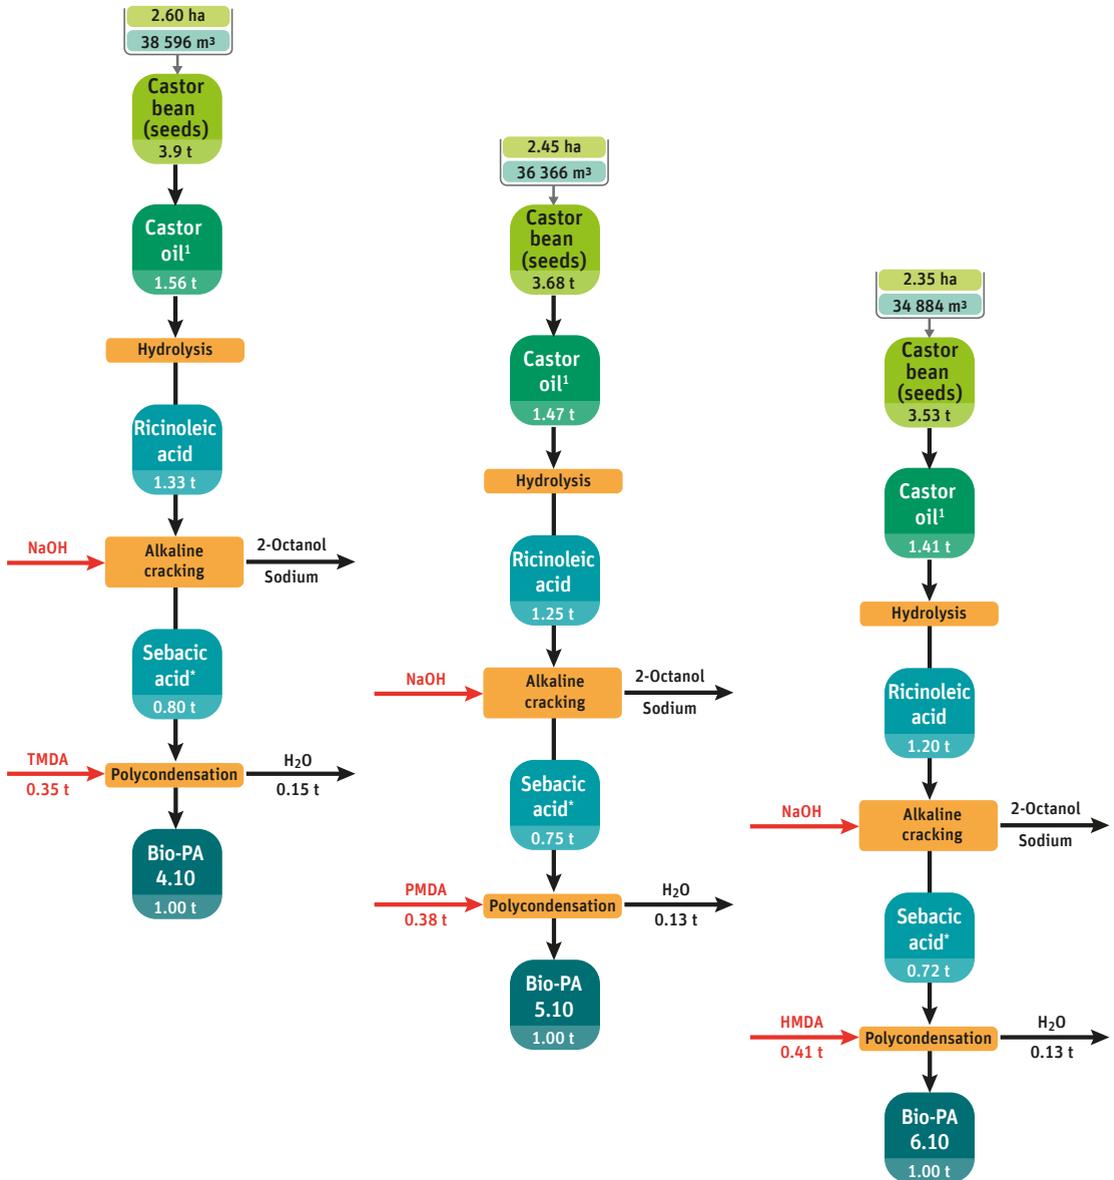

¹ One harvest per year


* Conversion rates:
Ricinoleic acid – Sebacic acid 60 %

References: Devaux et al. 2011; Diamond et al. 1965; Endres & Siebert-Raths 2011; Kyulavska 2017; Mubofu 2016; Radzik et al. 2020; Shen et al. 2009; Siyuan et al. 2019; Türk 2014; Winnacker & Rieger 2016

2.3.2 Copolyamides

2.3.2.2 Bio-PA 10.10

Bio-based content: 100 %

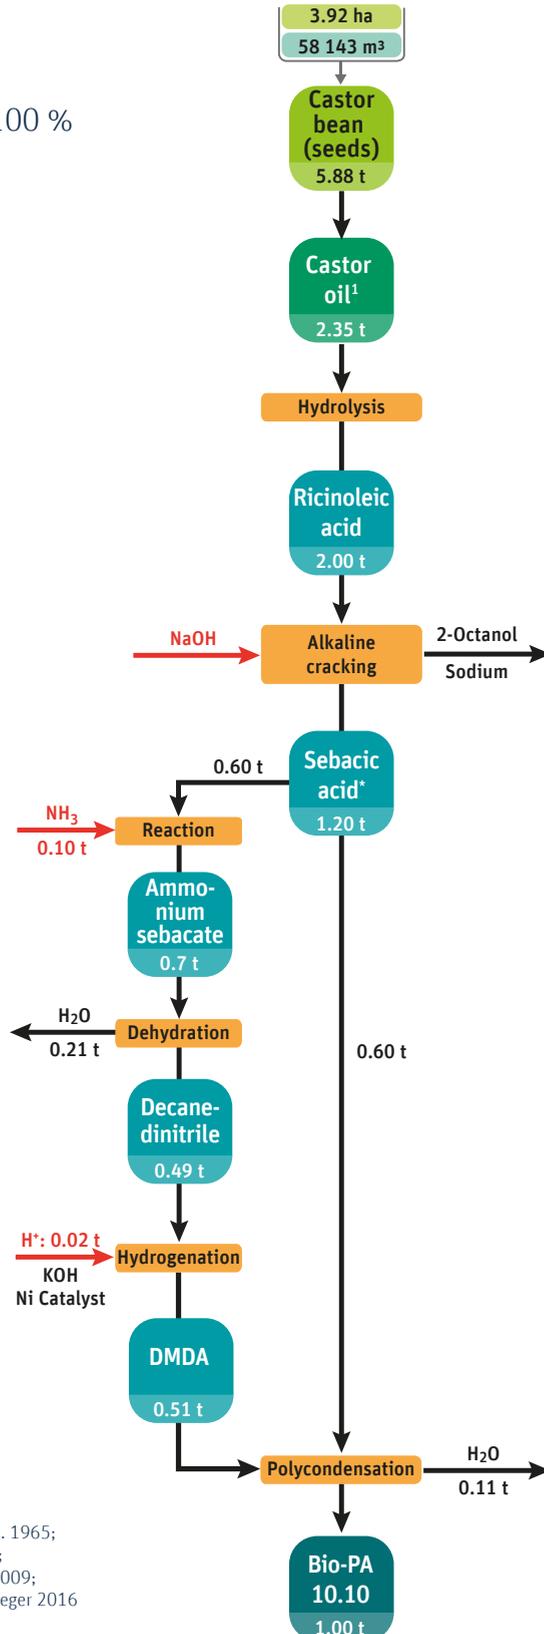


¹ One harvest per year

* **Conversion rates:**
Ricinoleic acid – Sebacic acid 60 %


References: Devaux et al. 2011; Diamond et al. 1965; Endres & Siebert-Raths 2011; Kyulavska 2017; Mubofu 2016; Radzik et al. 2020; Shen et al. 2009; Siyuan et al. 2019; Türk 2014; Winnacker & Rieger 2016

Bio-PA variations – Feedstock requirements in t


(feedstock castor bean)

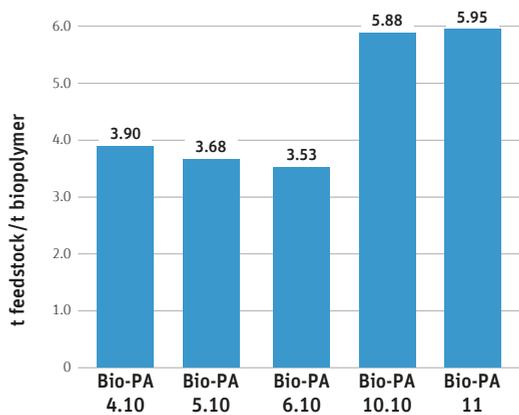

Bio-PA variations – Land use in ha (feedstock castor bean)

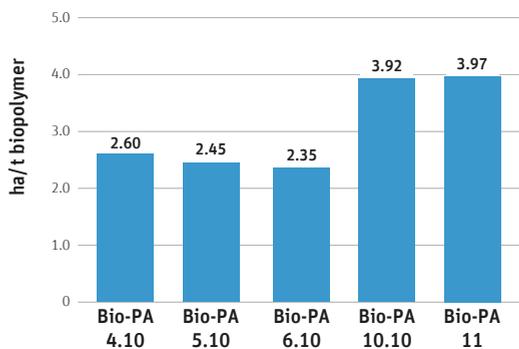


Bio-PA variations – Water use in m³ (feedstock castor bean)

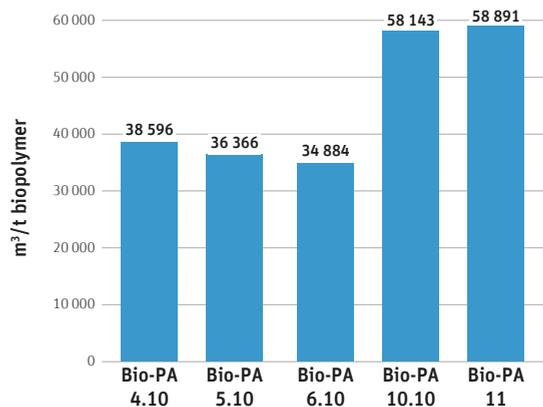

2.4 Polyurethanes


Bio-based contents: Bio-PU, Rigid foam: 50 %, Bio-PU, Flexible foam: 60 %

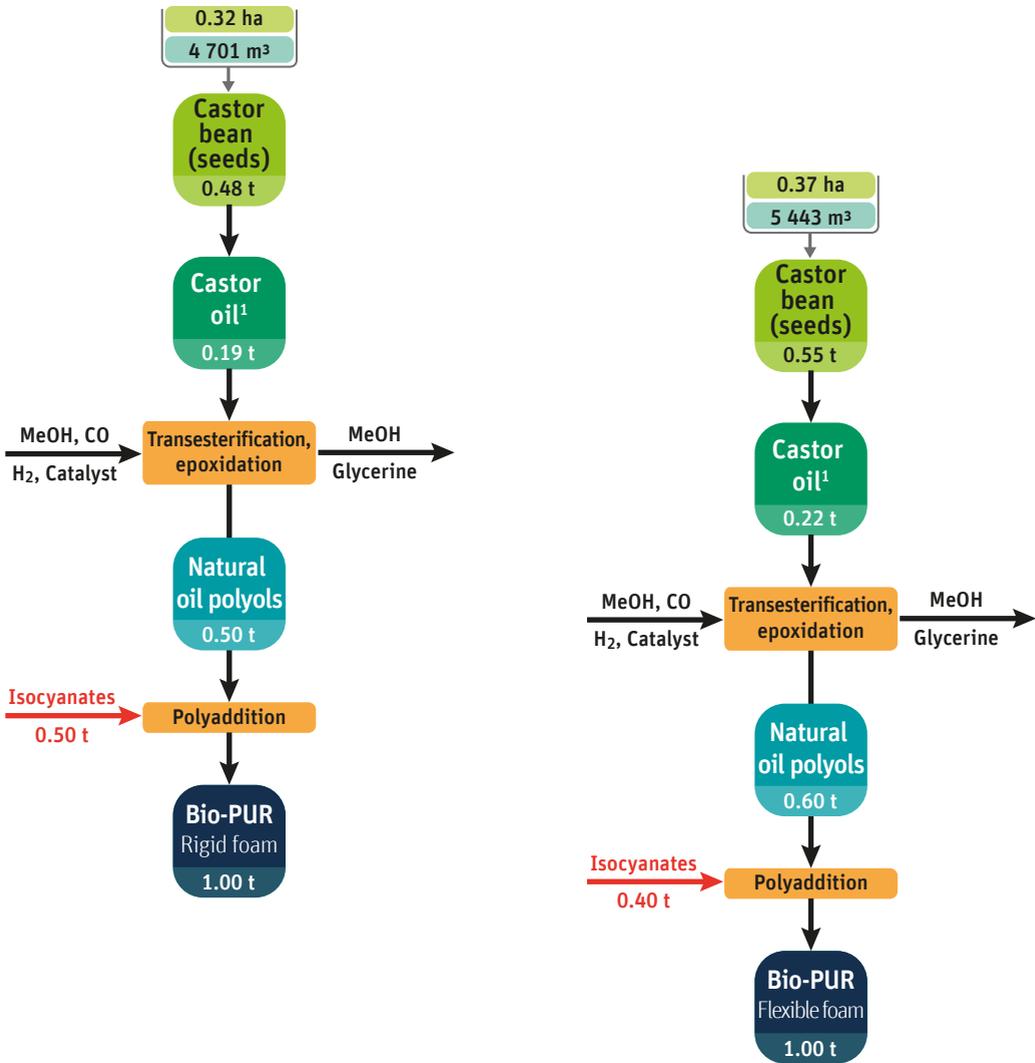


¹ One harvest per year

References: Andreeßen 2019; Endres & Siebert-Raths 2011; Shen et al. 2009


Bio-PUR variations – Feedstock requirements in t (feedstock castor bean)

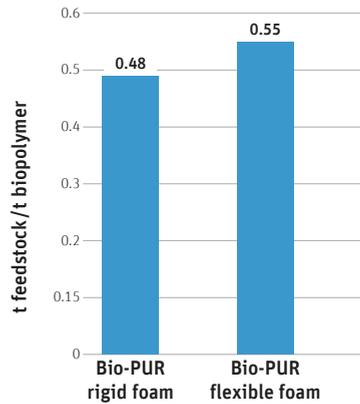

Bio-PUR variations – Land use in ha (feedstock castor bean)

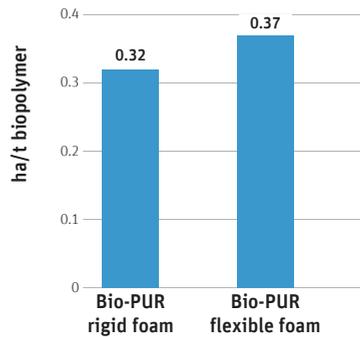

Bio-PUR variations – Water use in m³ (feedstock castor bean)

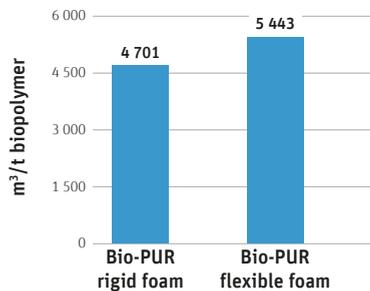


2.5 Polysaccharide polymers

2.5.1 Cellulose-based polymers (Cellulosics)

2.5.1.1 Regenerated cellulose

Bio-based content: 90 %


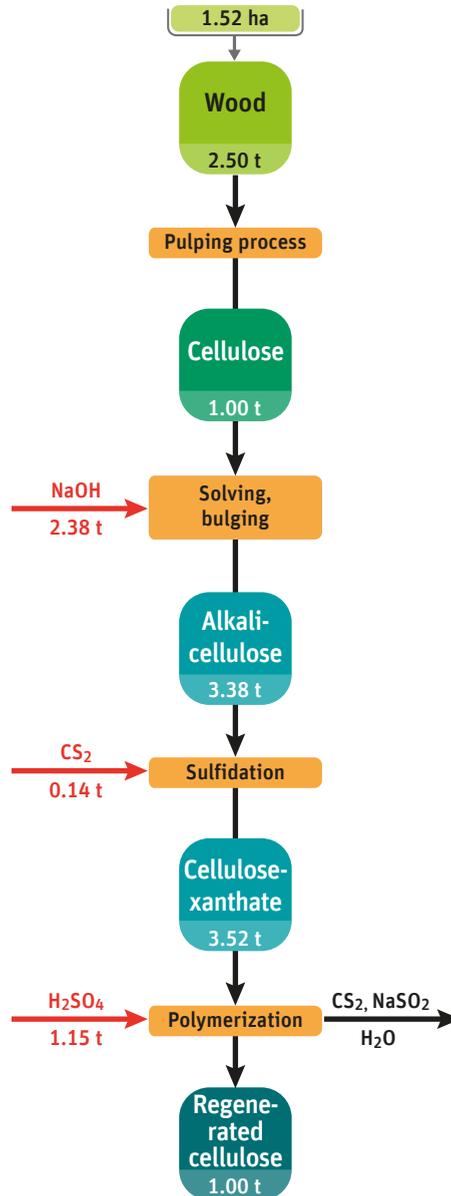


References: Endres & Siebert-Raths 2011; Sayyed et al. 2019; Xiaoya et al. 2020

2.5.1 Cellulose-based polymers (Cellulosics)


2.5.1.2 Cellulose diacetate

Bio-based content: 50 %

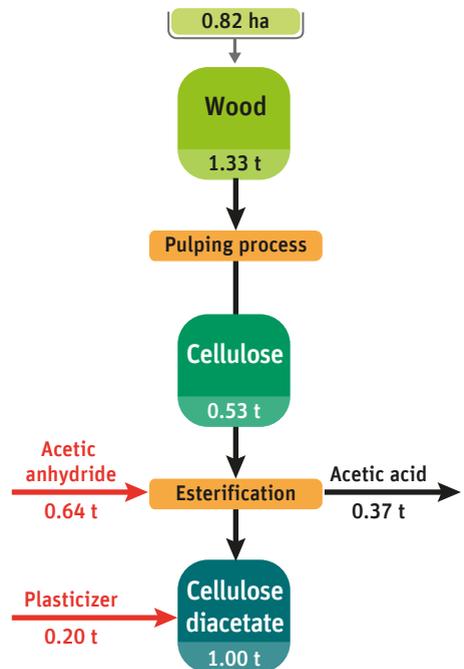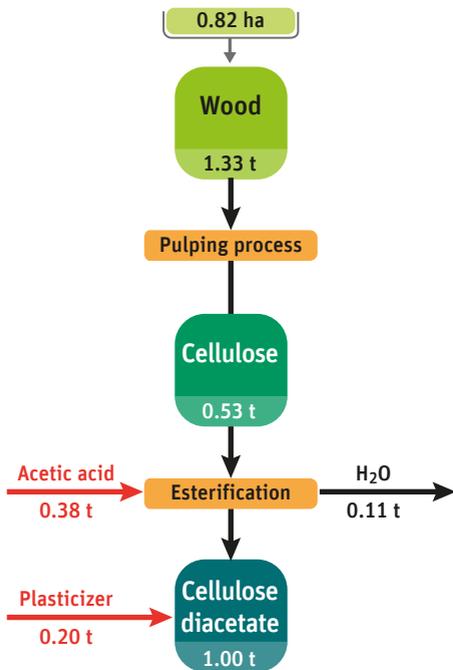


References: Endres & Siebert-Raths 2011; Sayyed et al. 2019

Cellulosics – Feedstock requirements in t (feedstock wood)

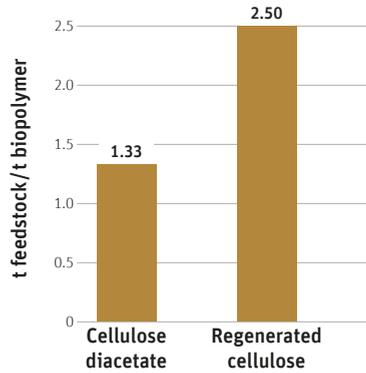


Cellulosics – Land use in ha (feedstock wood)

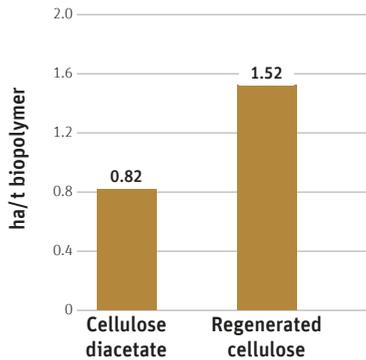

2.5.2 Starch-based polymers

2.5.2.1 Thermoplastic starch (TPS)

Bio-based content: 75 %

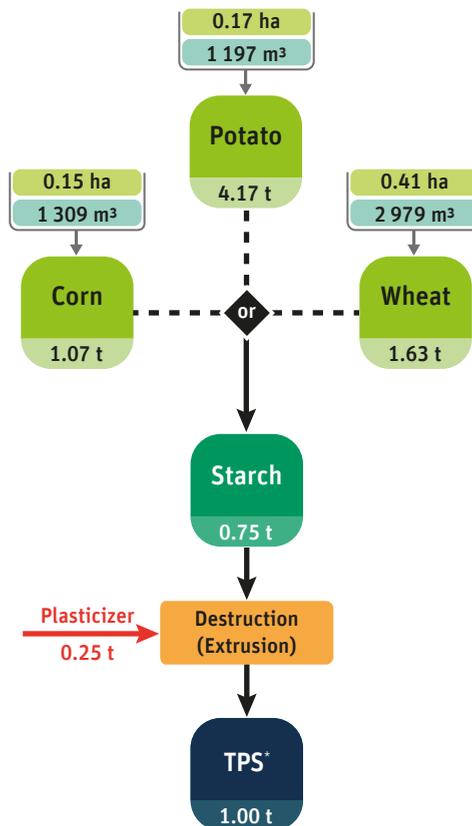


* Starch content 75 %

References: Endres & Siebert-Raths 2011; Iffland et al. 2015

2.5.2 Starch-based polymers

2.5.2.2 Starch blends


Bio-based contents: Starch blend 30/70: 23 %, Starch blend 50/50: 38 %,
Starch blend 70/30: 53 %

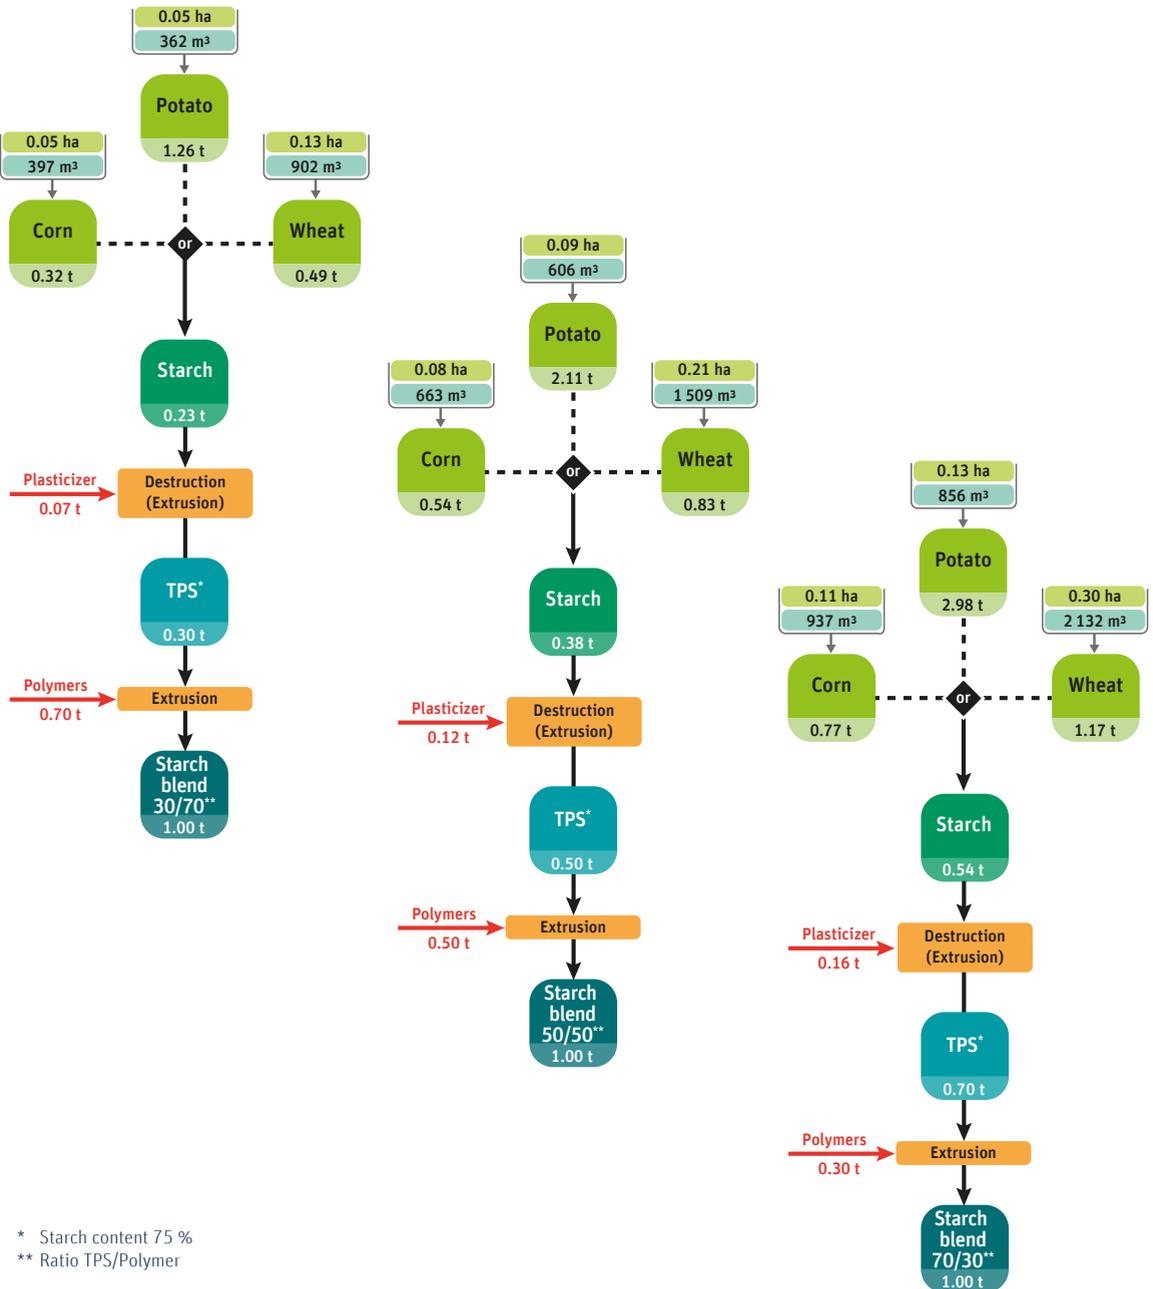


* Starch content 75 %
** Ratio TPS/Polymer

References: Endres & Siebert-Raths 2011; Iffland et al. 2015


Starch-based polymers – Feedstock requirements in t (different feedstocks)

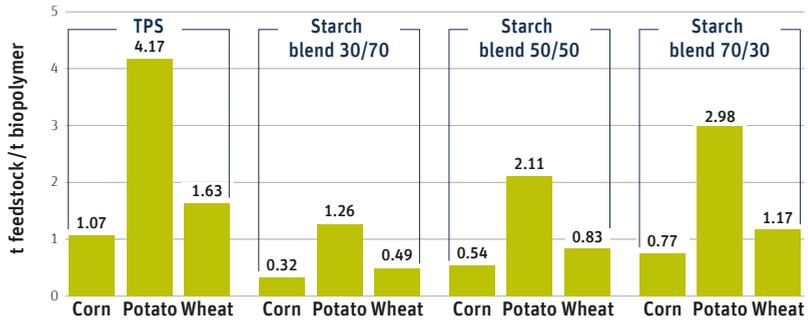

Starch-based polymers – Land use in ha (different feedstocks)

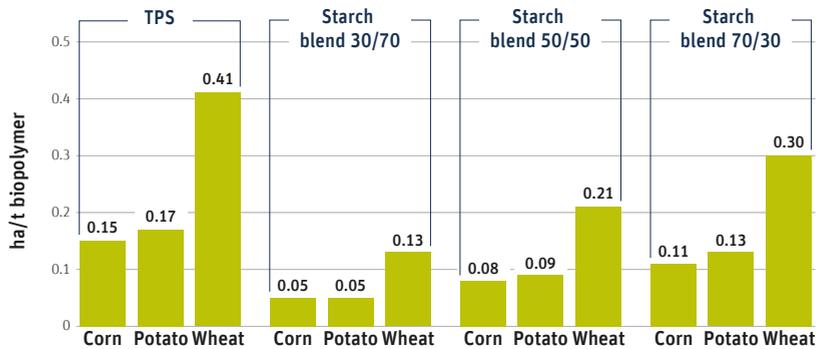


Starch-based polymers – Water use in m³ (different feedstocks)

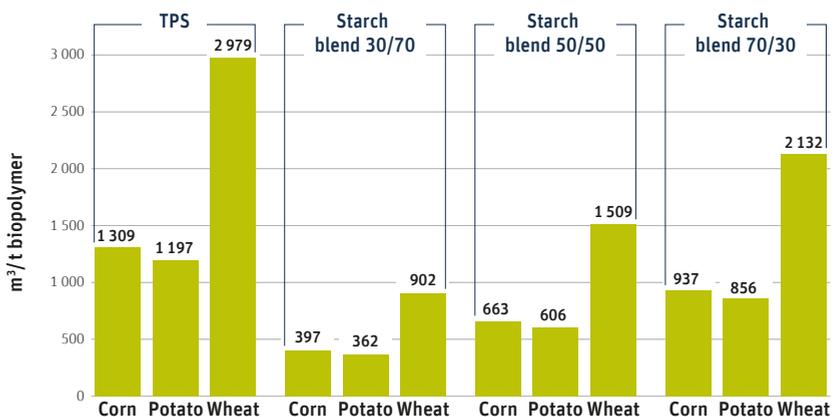

2.6 Polyvinyl chloride (Bio-PVC)

2.6.1 Bio-PVC-U (unplasticized)

Bio-based content: 40 %

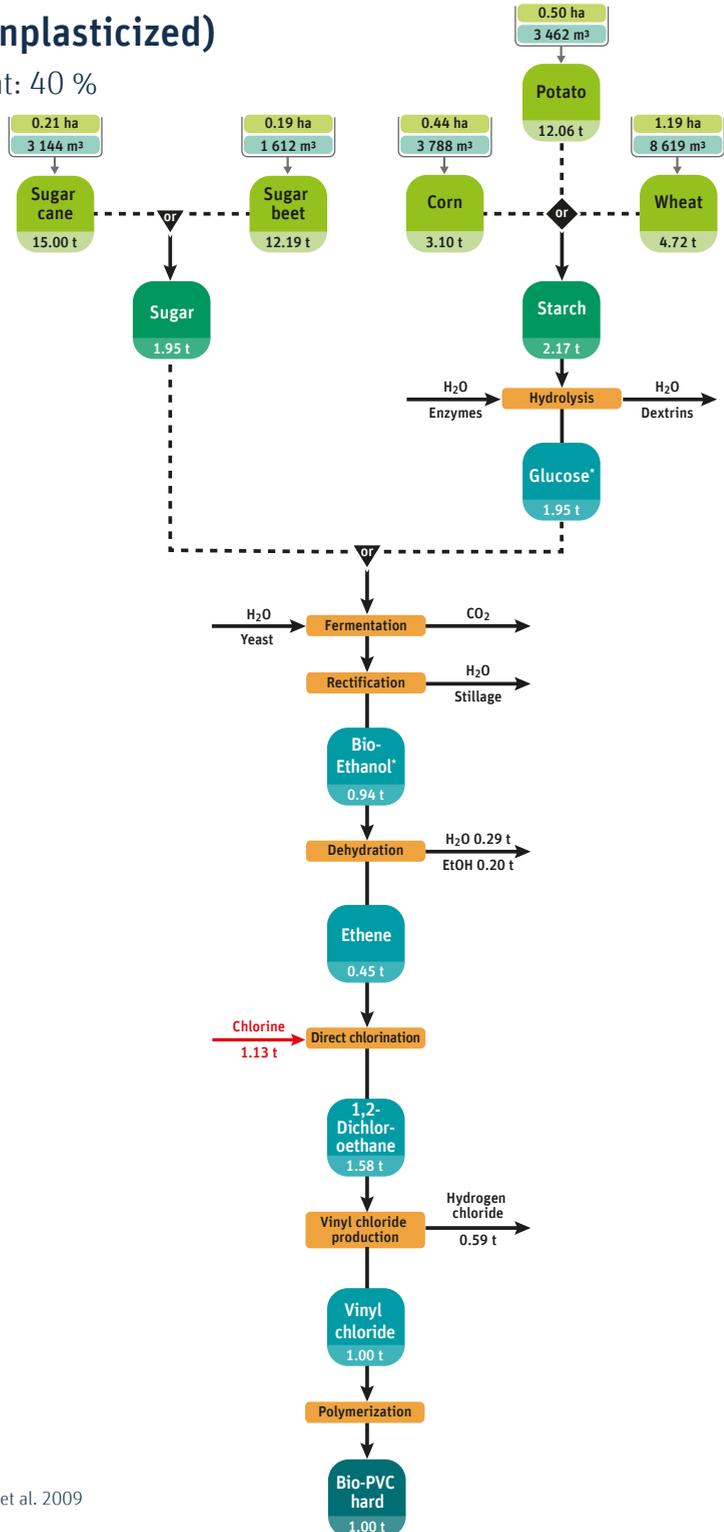


* Conversion rates:
 Starch – Glucose 88 %
 Glucose – Ethanol 48 %
 Ethanol – Ethene 48 %

References: Alvarenga et al. 2013; Shen et al. 2009

2.6.2 Bio-PVC-P (plasticized)

Bio-based content: 30 %

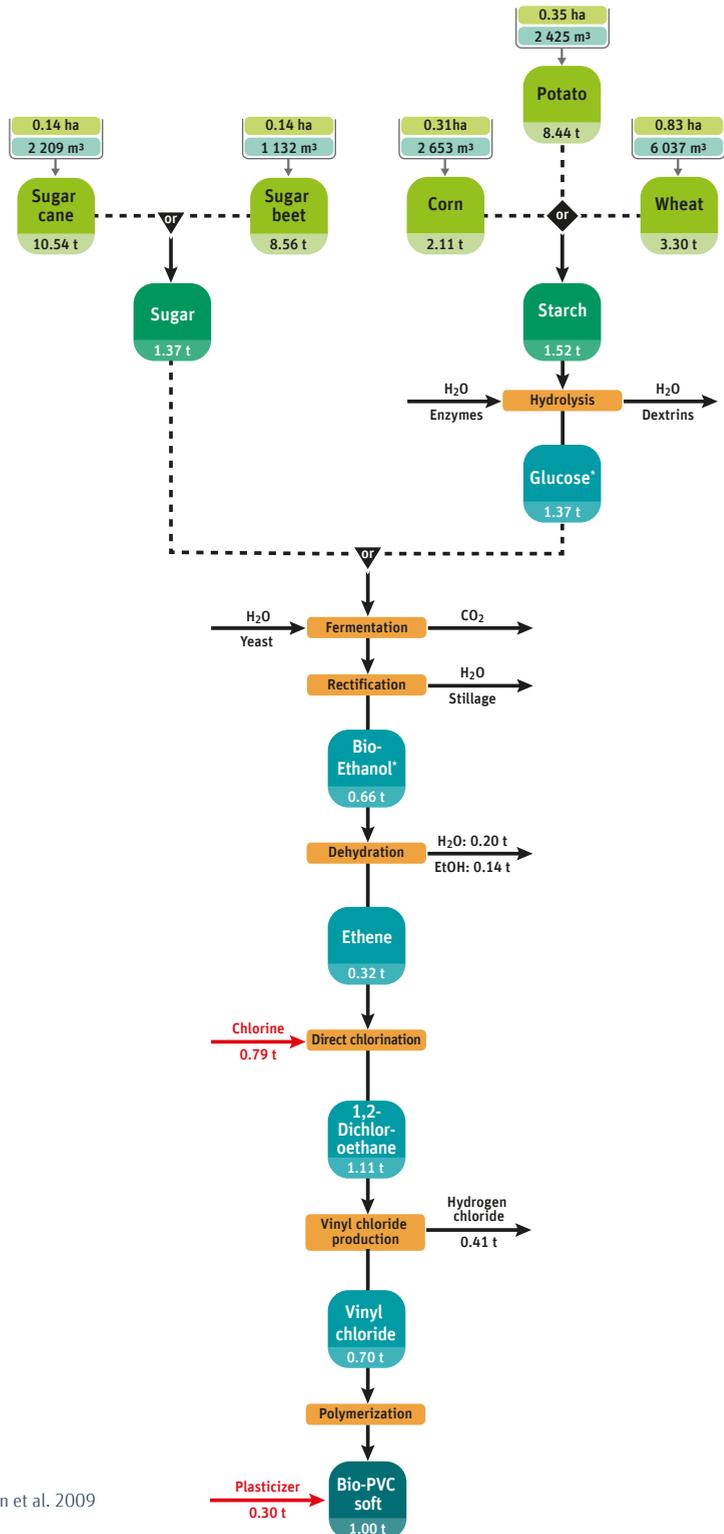


* Conversion rates:
 Starch – Glucose 88 %
 Glucose – Ethanol 48 %
 Ethanol – Ethene 48 %

References: Alvarenga et al. 2013; Shen et al. 2009


Bio-PVC-hard – Feedstock requirements in t

(different feedstocks)

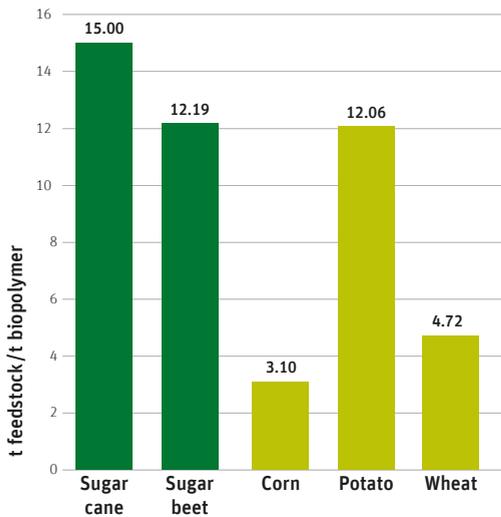


Bio-PVC-hard variations – Land use in ha

(different feedstocks)

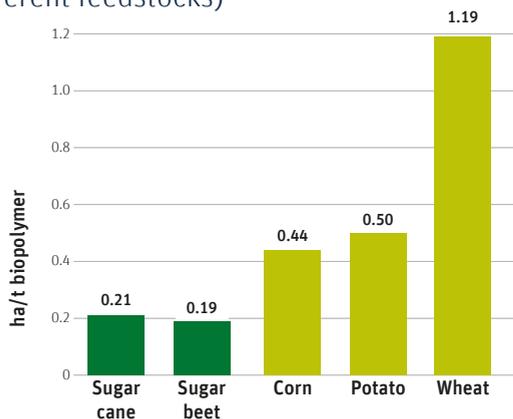


Bio-PVC-hard variations – Water use in m³

(different feedstocks)

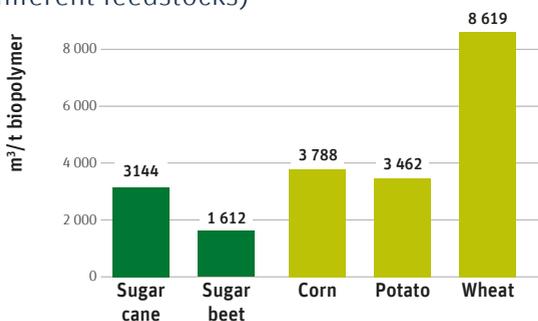


Bio-PVC-soft – Feedstock requirements in t

(different feedstocks)

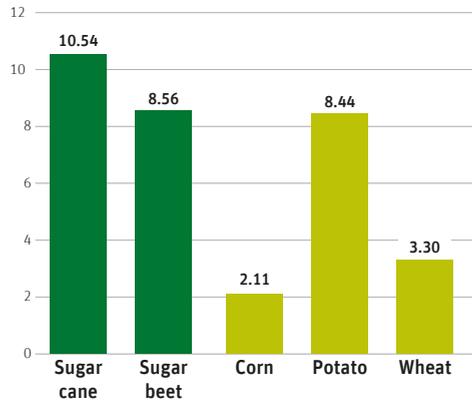


Bio-PVC-soft variations – Land use in ha

(different feedstocks)

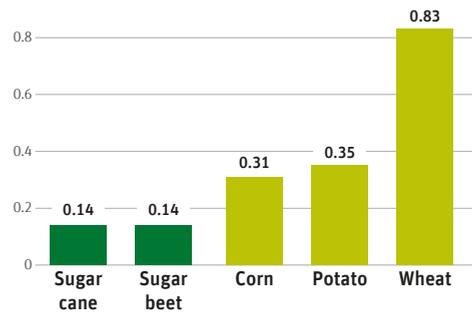

Bio-PVC-soft variations – Water use in m³


(different feedstocks)

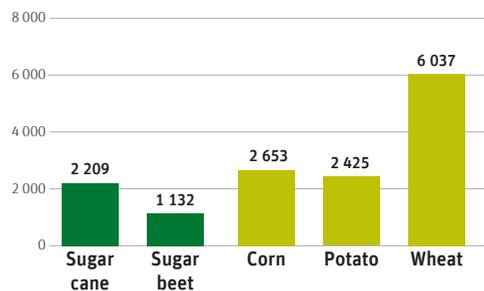

2.7 Bio-based polyacrylates

2.7.1 Poly(methyl methacrylate) (Bio-PMMA)

with bio-based ethylene
 Bio-based content: 30 %

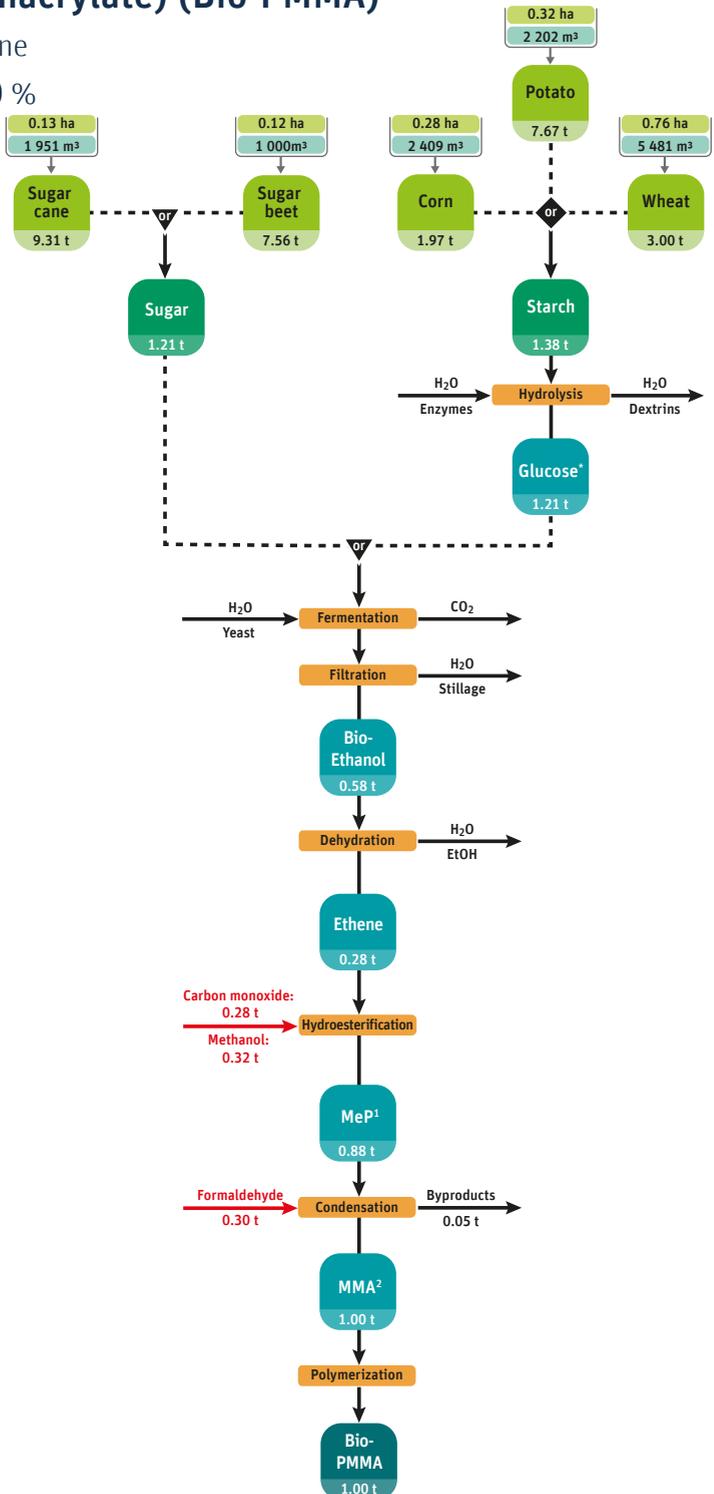


¹ MeP = Methylpropionate
² MMA = Methylmethacrylate


* Conversion rates:
 Starch – Glucose 88 %
 Glucose – Ethanol 48 %
 Ethanol – Ethene 48 %

References: Barnicki 2012;
 Lebeau & Lynch 2020; Veith et al. 2020


Bio-PMMA – Feedstock requirements in t (different feedstocks)

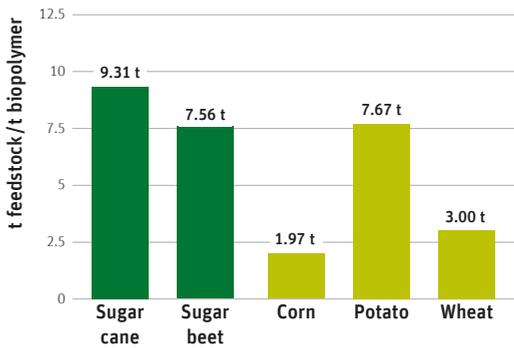

Bio-PMMA – Land use in ha (different feedstocks)

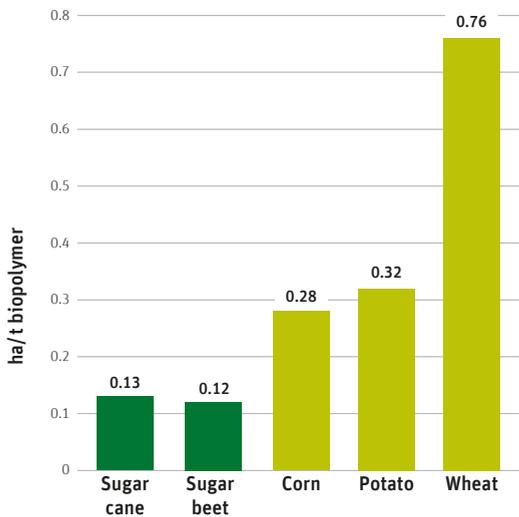

Bio-PMMA – Water use in m³ (different feedstocks)

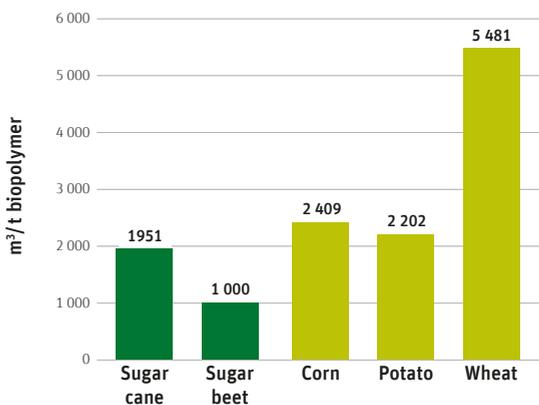

Market data and land use facts

As already mentioned in the introduction, the focus of attention is on “New Economy” bioplastics, including their position at the market. To give the reader an impression of the market share of these innovative and novel bioplastics the following pages contain a summary of IfBB's research.

When considering the most important Old Economy bioplastics with their global production capacity of about 21 million tonnes annually, it turns out that the share of New Economy bioplastics is almost 10 times lower, i.e. 11.9 % of the market volume of all bio-based plastics (Old and New Economy Bioplastics included).



While the combined production capacities for Old and New Economy bioplastics amount to around 23.8 million tonnes worldwide, the global plastics market for fossil and New Economy bioplastics will total around 431 million tonnes in 2024 (cf. Plastics Europe – Plastics the Facts 2025). The corresponding land use of Old and New Economy bioplastics is currently at approximately 18.6 million hectares, which is equivalent to only 0.39 % of the global agricultural area or approximately 1.2 % of the arable land. Comparing these figures reveals that New Economy bioplastics, which tend to be the only focus of interest in land use discussions, use up only 10.2 % of the area required for all bio-based plastics combined.

Even though global forecasts predict a rapidly growing market for these novel bioplastics in the next few years, the need for agricultural areas will be still kept at a very low level. While the market for new bioplastics has been growing during the last years and a sustained growth is anticipated in the future, it can be assumed that land use for New Economy bioplastics by 2030 (5.39 million tonnes), for example, will be around 0.066 % of the global agricultural area or about 0.21 % of the arable land (see figures on page 58 and pages 66/67). Regardless of the significant growth rates, it should be mentioned that the market share of these New Economy bioplastics is still hovering at less than 1 % of the global plastics market and is likely not to exceed 2-3 % in the near future.

To make things even more compelling, it is a fact that bio-based plastics, even after multiple material usage, can still serve as an energy carrier. This means that additional crop lands, which

are currently used for direct energy production, could be set aside for the production of bioplastics. Prior material usage of biomass, as in the case of bioplastics, still permits subsequent trouble-free energy recovery, whereas direct incineration of biomass (and also crude oil-based products!) precludes an immediate subsequent material usage. In this case, more arable land for plant cultivation is needed and consequently another photosynthesis process, in order to gain new resources once again as feedstock for material usage.

Production capacities and land use Old and New Economy bioplastics¹ 2025

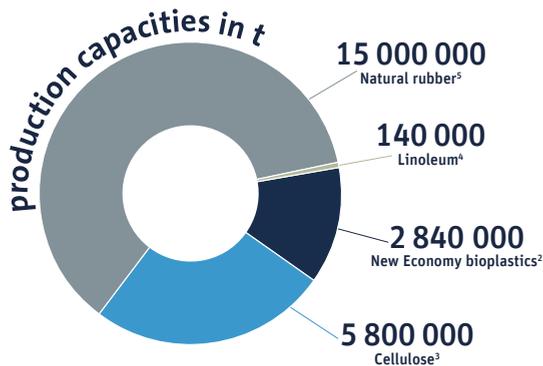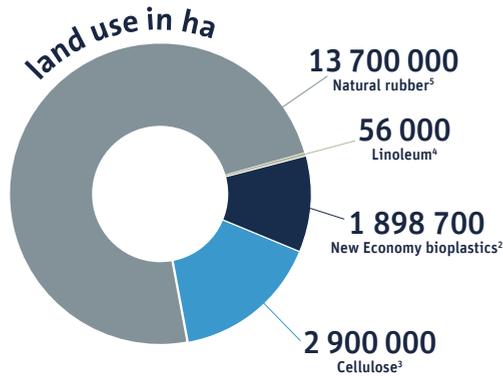

¹ Only bio-based share.


² PLA, PHA, PTT, PBAT, Starch blends, Drop-Ins (Bio-PE, Bio-PET, Bio-PA) and other.

³ Material use excl. paper industry.

⁴ Calculations include linseed oil only.

⁵ Cf. FAOSTAT 2022 Online Data.


3.1 Global production capacities of bioplastics¹

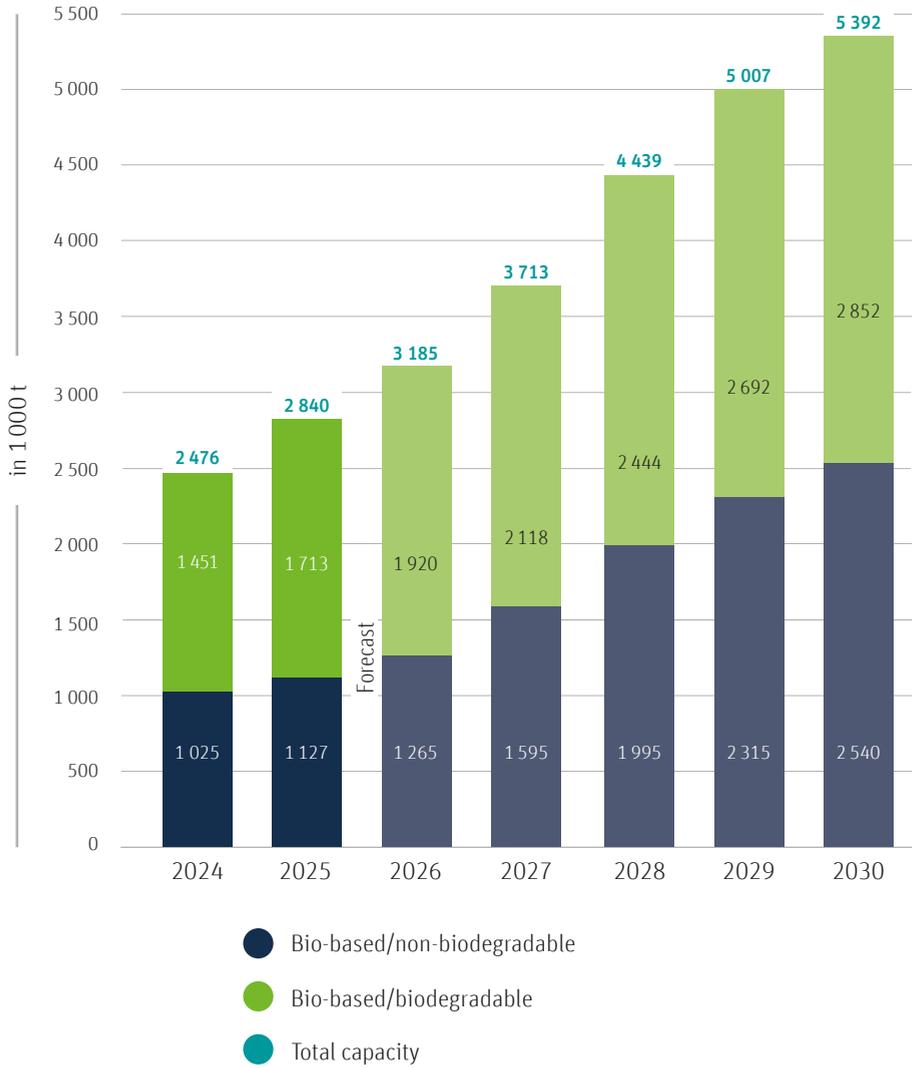

¹ Only bio-based share.


3.2 Global production capacities of bioplastics¹ (by material type)

2025

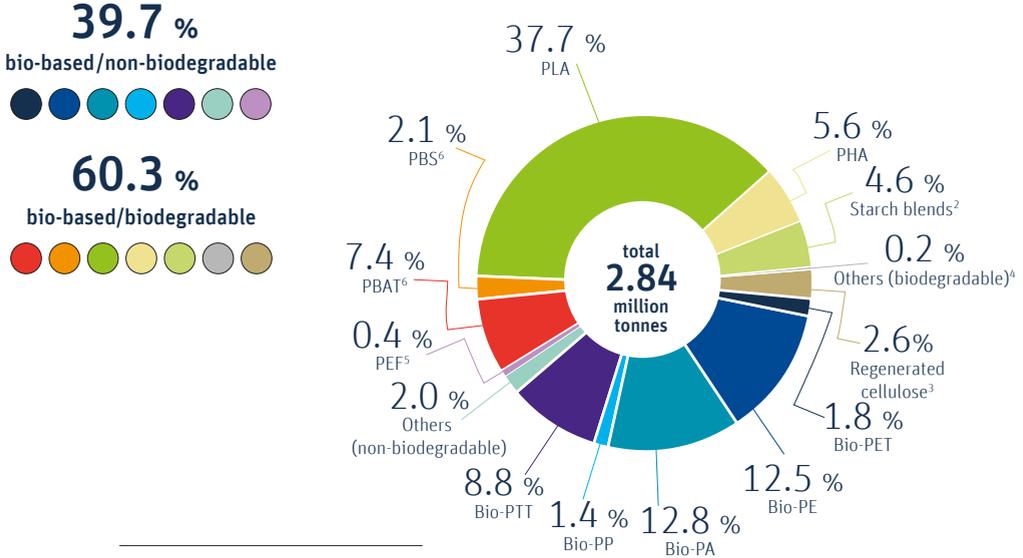

¹ Only bio-based share.
² Only contains the starch component. The average starch content is assumed to be 45 %.
³ Compostable hydrated cellulose foils.
⁴ Contains cellulose derivatives and PCL.
⁵ PEF commercially available as of 2024.
⁶ Only contains the share of bio-based or partly bio-based capacities.


2030

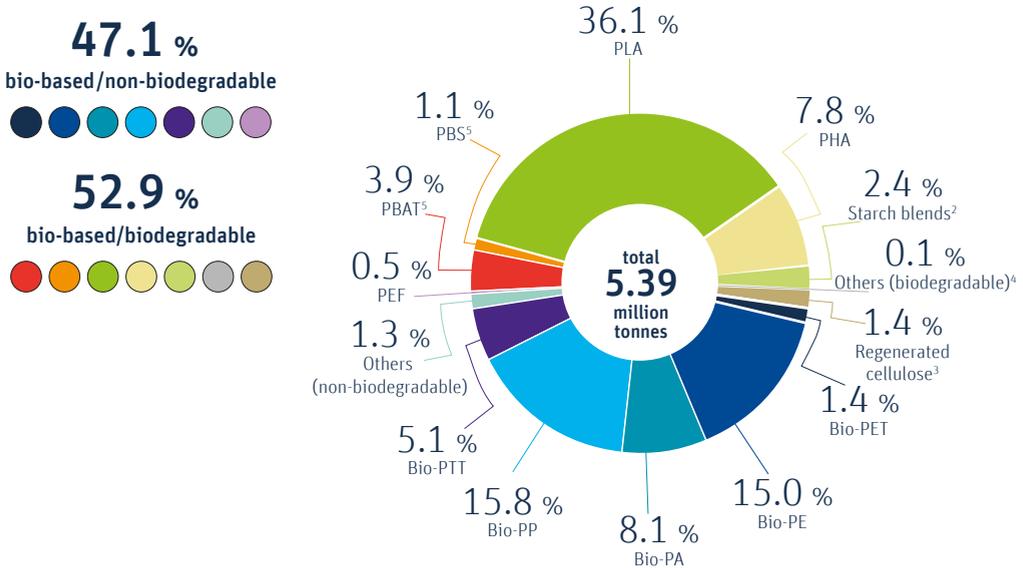

¹ Only bio-based share.
² Only contains the starch component. The average starch content is assumed to be 45 %.
³ Compostable hydrated cellulose foils.
⁴ Contains cellulose derivatives and PCL.
⁵ Only contains the share of bio-based or partly bio-based capacities.


3.3 Global production capacities of bioplastics¹ (by region)

2025

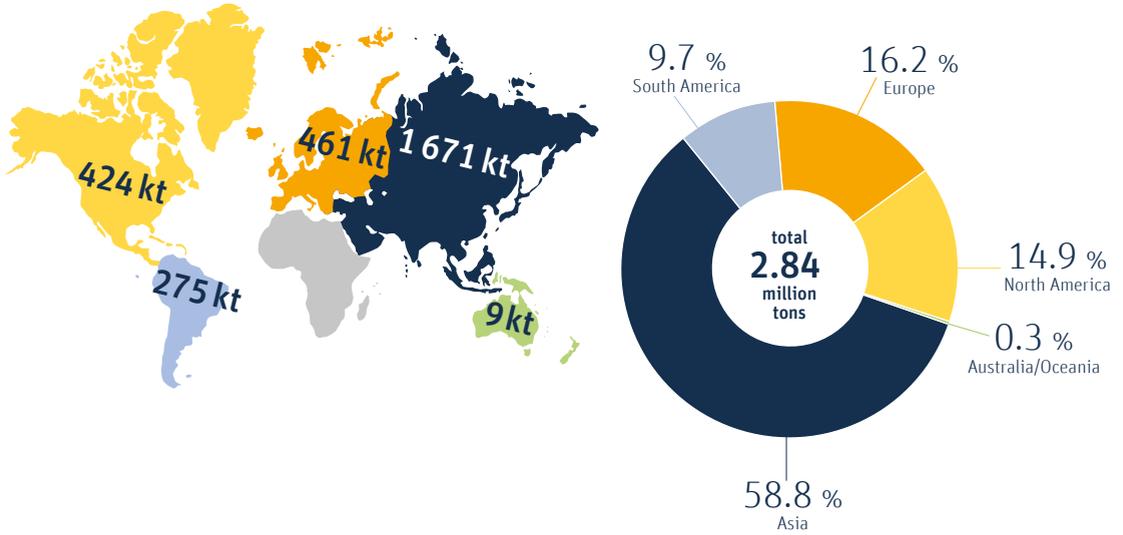

¹ Only bio-based share.


2030

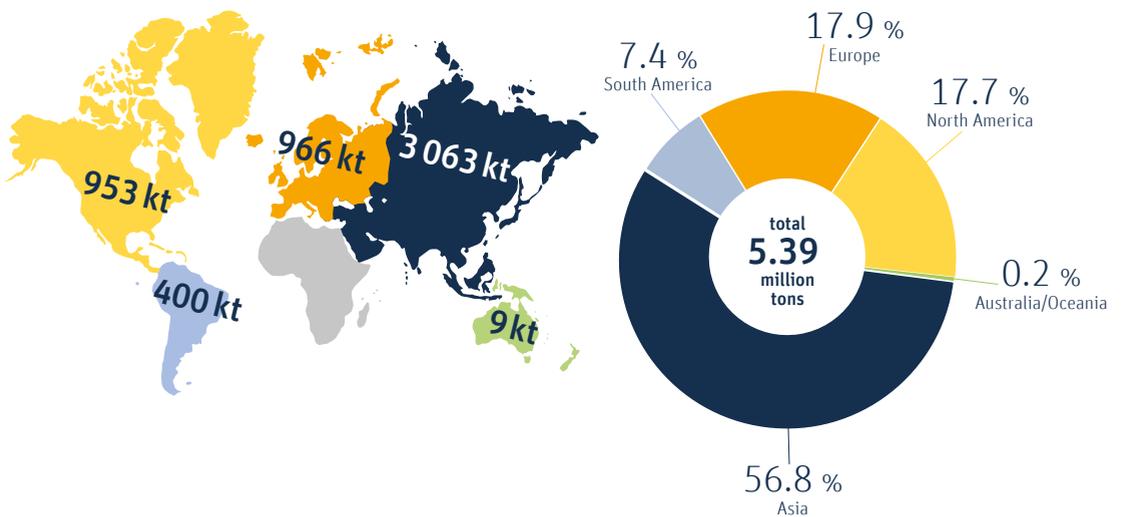


¹ Only bio-based share.

3.3 Global production capacities of bio-based/non-biodegradable plastics (by region)

2025

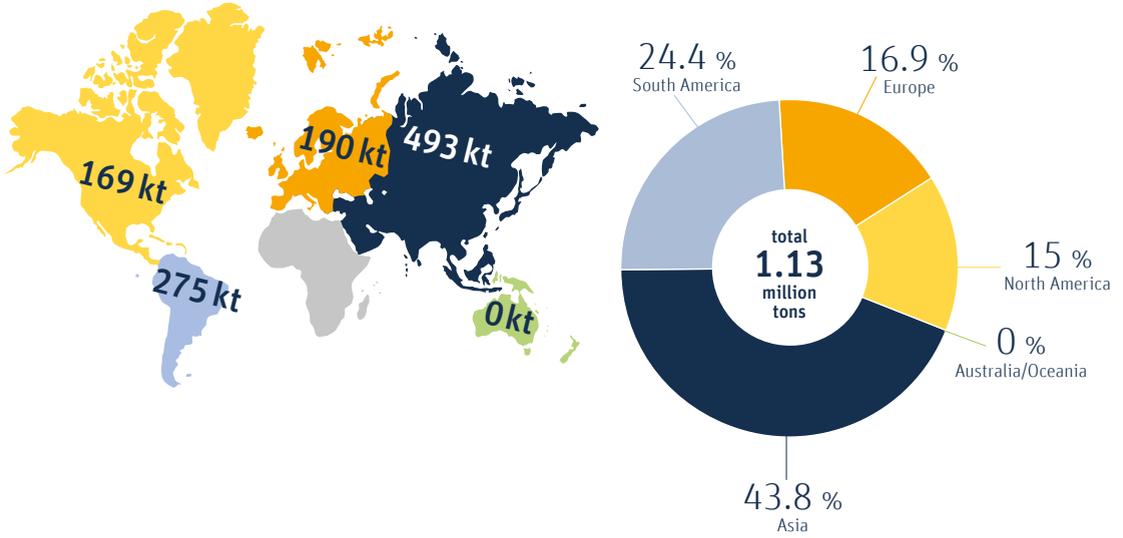


2030


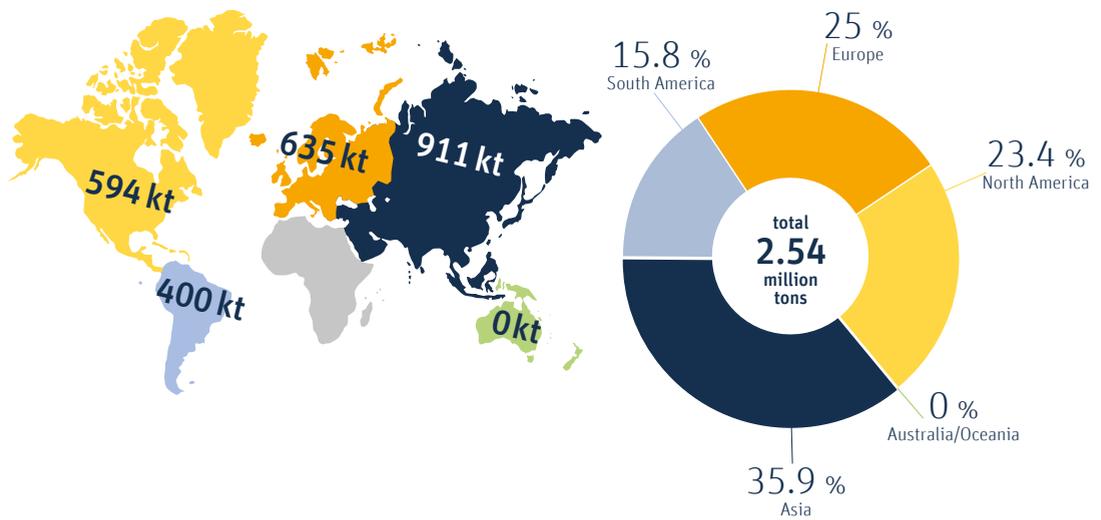


3.3 Global production capacities of bio-based/biodegradable plastics (by region)

2025

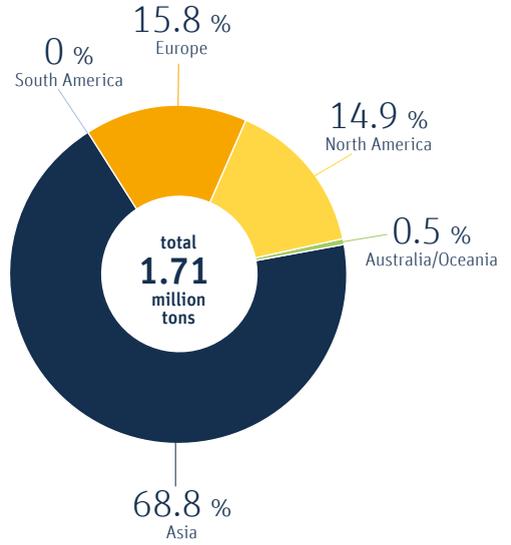


2030

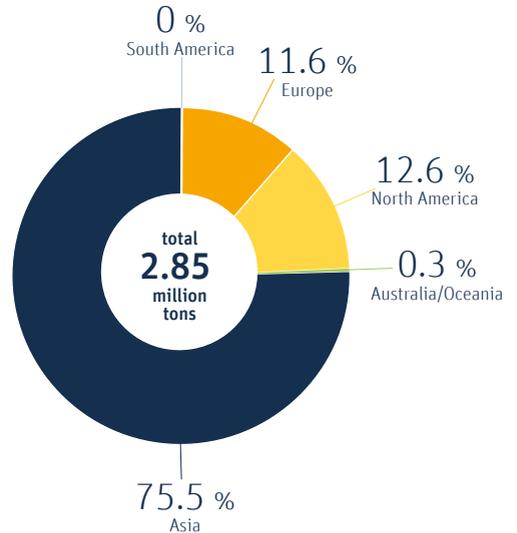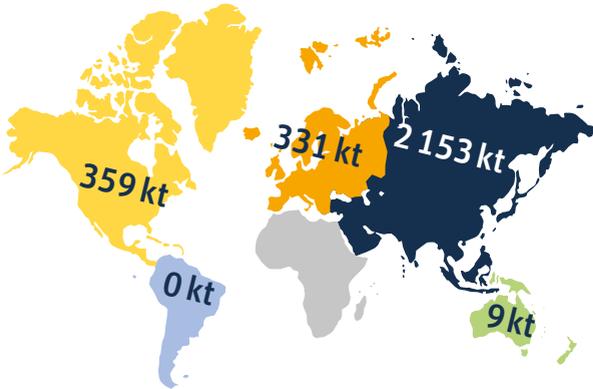


3.4 Global production capacities of bioplastics¹ (by market segment)

2025

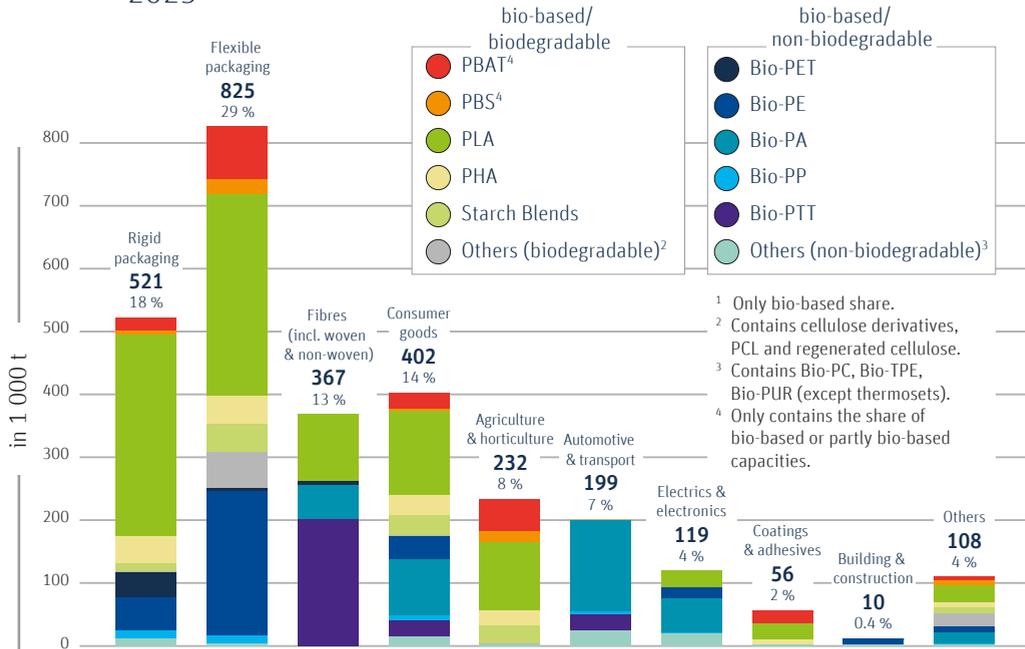


2030

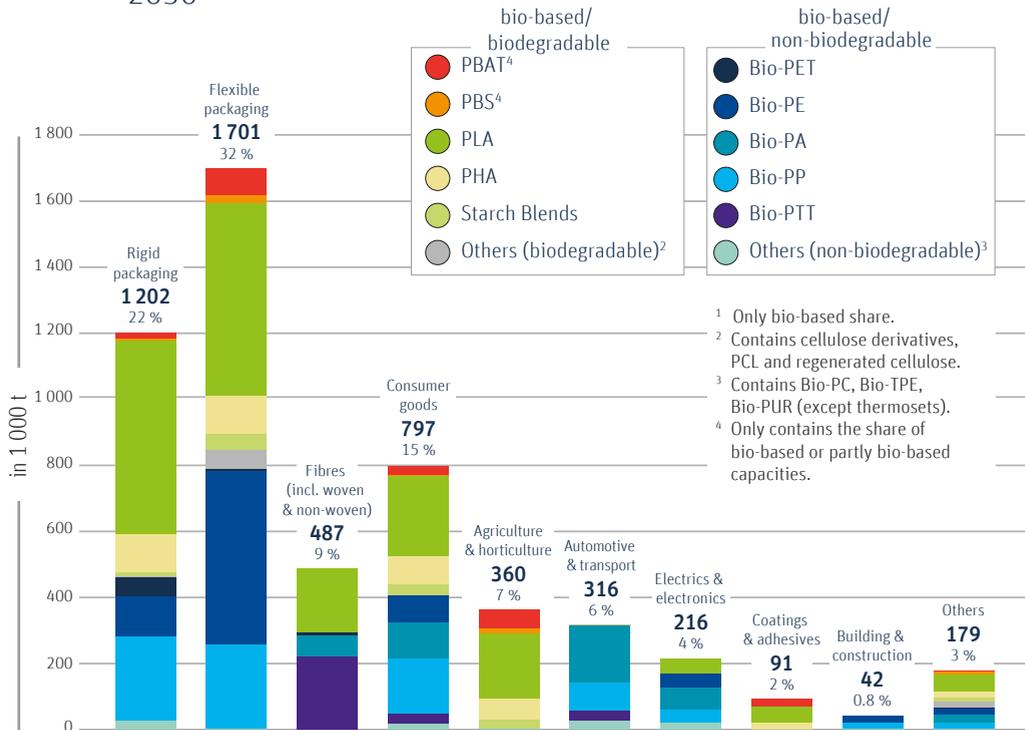


3.4 Global production capacities of bio-based/ non-biodegradable plastics (by market segment)

2025

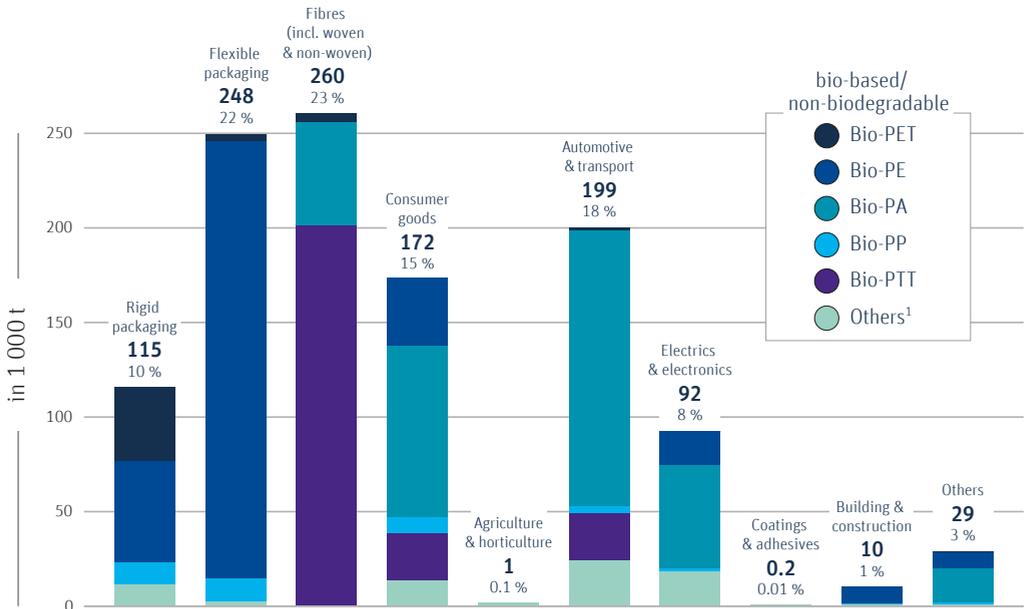

¹ Contains Bio-PC, Bio-TPE, Bio-PUR (except thermosets).


2030

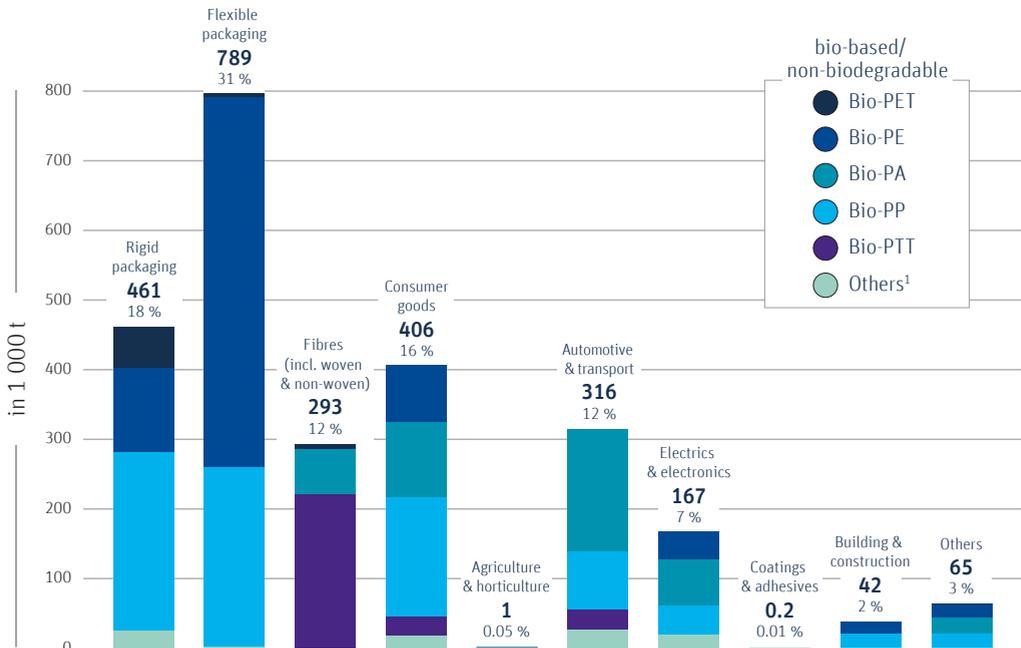

¹ Contains Bio-PC, Bio-TPE, Bio-PUR (except thermosets).

3.4 Global production capacities of bio-based/biodegradable plastics (by market segment)


2025

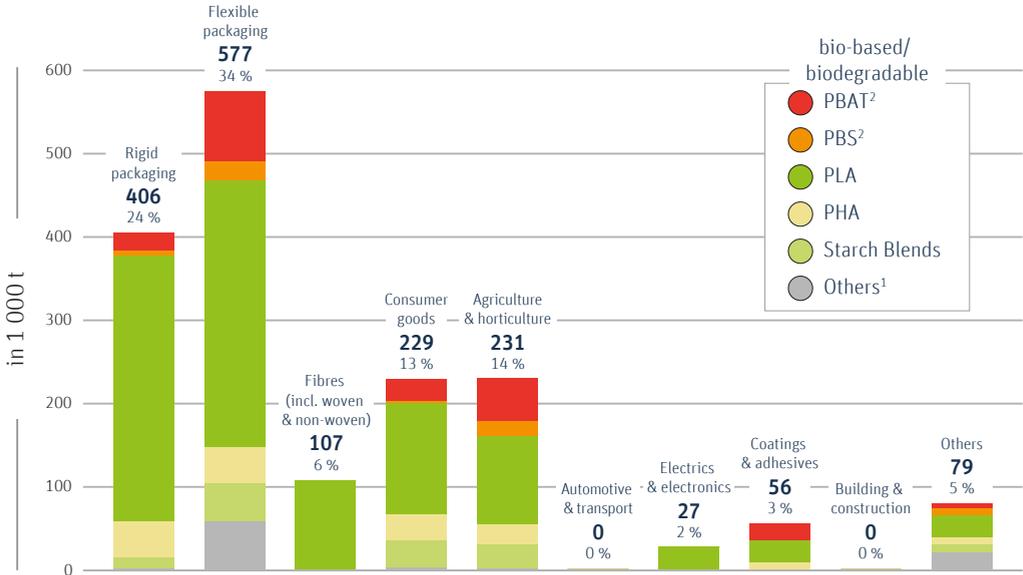

¹ Contains cellulose derivatives, PCL and regenerated cellulose.

² Only contains the share of bio-based or partly bio-based capacities.


2030

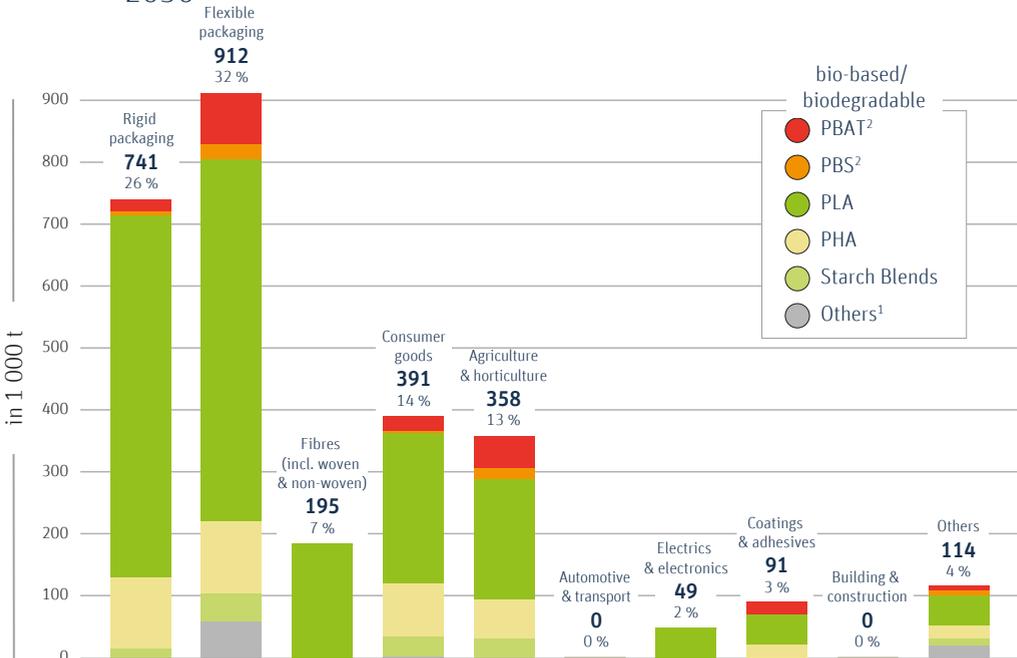

¹ Contains cellulose derivatives, PCL and regenerated cellulose.


² Only contains the share of bio-based or partly bio-based capacities.

3.5 Land use for bioplastics¹ 2025 and 2030

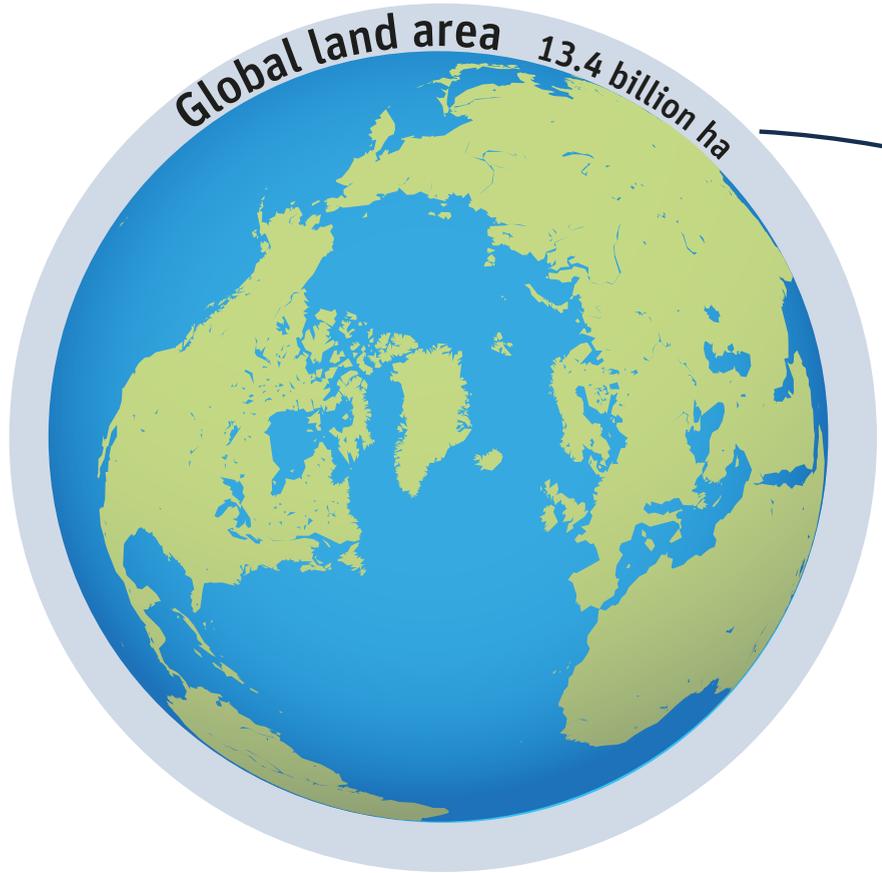

For final land use estimation only the most commonly used crop was taken into consideration. Yield data from FAO statistics served as a basis for calculation (global, weighted average over the past 10 years). To approximate land use in this bottom-up approach, the producer-specific production capacities of a type of bioplastics were multiplied by the output data of the corresponding process routes. In case a producer-specific feedstock type for was not known, the most commonly used crop for this bioplastic type was taken into calculation.

In all of the calculations no allocation was made, which means land use was fully, by 100 %, allocated to the raw materials for bioplastics and not split up between various parallel side products such as proteins or straw in wheat. So this approach leads to a rather conservative estimate.

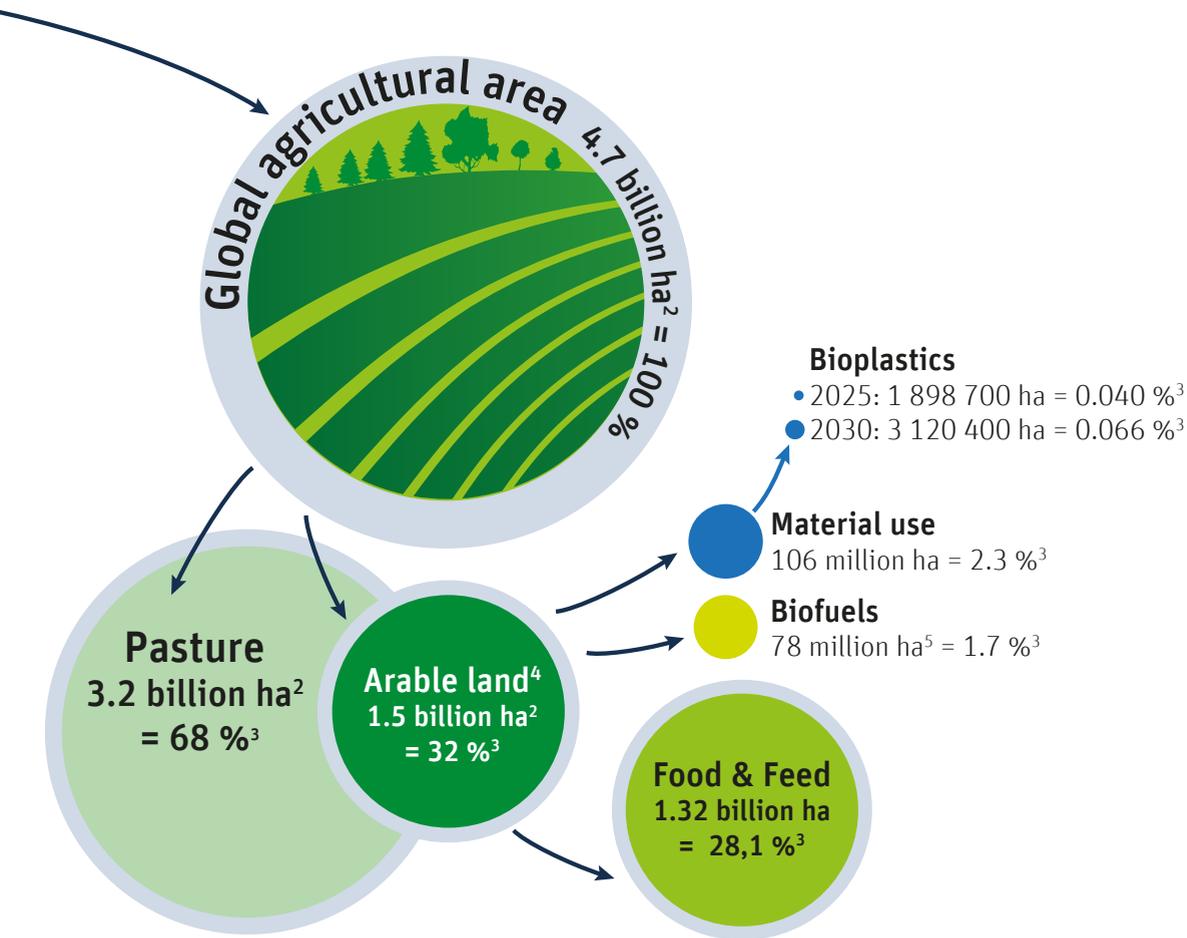

¹ Only bio-based share.

² Cf. FAO 2022. World Food and Agriculture – Statistical Yearbook 2022.

³ Percentage compared to global agricultural area.

⁴ Also includes area growing permanent crops as well as approx. 1 % fallow land. Abandoned land resulting from shifting cultivation is not included.

⁵ Cf. Rulli et al. 2016.

- Akanuma, Y., Selke, S., Auras, R.: A preliminary LCA case study: Comparison of different pathways to produce purified terephthalic acid suitable for synthesis of 100 % bio-based PET; in: *The International Journal of Life Cycle Assessment* 19 (2014), p. 1238-1246, DOI: 10.1007/s11367-014-0725-2.
- Alexander, A. G.: Sugarcane as a source of biomass; in: Sansoucy, R., Aaarts, G., Preston, T. R. (ed.): *Sugarcane as feed*, series FAO Animal Production and Health, vol. 72, Rome 1988, p. 46–60.
- Alvarenga, R. A. F., Dewulf, J., De Meester, S., Wathelet, A., Villers, J., Thommeret, R., Hruska, Z.: Life cycle assessment of bioethanol-based PVC; in: *Biofuels, Bioproducts and Biorefining* 7 (2013), p. 396-405, DOI: 10.1002/bbb.1398.
- Andreeßen, C., Steinbüchel, A.: Recent developments in non-biodegradable biopolymers: Precursors, production processes, and future perspectives; in: *Applied Microbiology and Biotechnology* 103 (2019), p. 143–157, DOI: 10.1007/s00253-018-9483-6.
- Anjani, K.: Castor genetic resources: A primary gene pool for exploitation; in: *Industrial Crops and Products* 35 (2012), p. 1–14, DOI: 10.1016/j.indcrop.2011.06.011.
- Barnicki, S. D.: *Synthetic Organic Chemicals*; in: Kent, J. A. (ed.): *Handbook of Industrial Chemistry and Biotechnology*, New York 2012, p. 423-530.
- BeMiller, J. N., Whistler, R. L.: *Starch: Chemistry and technology*, London 2009.
- Chen, G. G.-Q.: Industrial Production of PHA; in: Chen, G. G.-Q. (ed.): *Plastics from Bacteria: Natural Functions and Applications*, Microbiology Monographs, vol. 14, Berlin 2010, p. 121-132, DOI 10.1007/978-3-642-03287_5_6.
- Clark, J., Farmer, T., Hunt, A., Sherwood, J.: Opportunities for Bio-Based Solvents Created as Petrochemical and Fuel Products Transition towards Renewable Resources; in: *International Journal of Molecular Sciences* 16 (2015), p. 17101-17159, DOI: 10.3390/ijms160817101.
- Collias, D., Harris, A., Nagpal, V., Cottrell, I., Schultheis, M.: Biobased Terephthalic Acid Technologies: A Literature Review; in: *Industrial Biotechnology* 10 (2014), p. 91-105, DOI: 10.1089/ind.2014.0002.
- Devaux, J.-F., Lê, G., Pees, B.: Application of Eco-Profile Methodology to Polyamide 11, Colombes 2011.
- Diamond, M. J., Binder, R. G., Applewhite, T. H.: Alkaline cleavage of hydroxy unsaturated fatty acids. I. Ricinoleic acid and lesquerolic acid; in: *Journal of the American Oil Chemists' Society* 42 (1965), p. 882–884, DOI: 10.1007/BF02541184.
- Eerhart, A. J. J. E., Faaij, A. P. C., Patel, M. K.: Replacing fossil based PET with biobased PEF; process analysis, energy and GHG balance; in: *Energy & Environmental Science* 5 (2012), p. 6407-6422, DOI: 10.1039/c2ee02480b.
- Endres, H.-J., Siebert-Raths, A.: *Engineering Biopolymers*, München 2011.
- Food and Agriculture Organization of the United Nations (FAO): *Agribusiness Handbook*, vol. 4: Sugar Beet, White Sugar, Rome 1999, <http://www.fao.org/3/ae377e/ae377e.pdf> (09.07.2021).
- FAOSTAT 2022, Online Data, <https://www.fao.org/faostat/en/#data/QCL> (01.02.2024).
- FAO. 2022. *World Food and Agriculture – Statistical Yearbook 2022*, Rome 2022, DOI: 10.4060/cc2211en.
- Food and Agriculture Organization of the United Nations (FAO): *Definition and classification of commodities* (1994), <http://www.fao.org/es/faodef/fdef03e.htm> (09.07.2021).
- Frost, J.: Synthesis of caprolactam from lysine. Patent WO 2005/123669 A1, 29.12.2005, <https://patentimages.storage.googleapis.com/51/da/13/b0c9223b7bc928/WO2005123669A1.pdf> (09.07.2021).
- Hajid, M., Zhao, X., Liu, D.: Production of 2,5-furandicarboxylic acid (FDCA) from 5-hydroxymethyl furfural (HMF): A recent progress focusing on the chemical-catalytic routes; in: *Green Chemistry* 20 (2018), p. 5427-5453, DOI: 10.1039/C8GC02680G.
- Hoekstra, A. Y., Chapagain, A. K., Aldaya, M. M., Mekonnen, M. M.: *The water footprint assessment manual: setting the global standard*, Enschede 2011.
- Hulea, V.: Direct transformation of butenes or ethylene into propylene by cascade catalytic reactions; in: *Catalysis Science & Technology* 9 (2019), p. 4466-4477, DOI: 10.1039/c9cy00870e.
- Hwang, K. -R., Jeon, W., Lee, S., Kim, M. -S., Park, Y.-K.: Sustainable bioplastics: Recent progress in the production of bio-building blocks for the bio-based next-generation polymer PEF; in: *Chemical Engineering Journal* 390 (2020), p. 124636, DOI: 10.1016/j.cej.2020.124636.
- Iffland, K., Sherwood, J., Carus M., Raschka, A., Farmer, T., Clark, J.: Definition, Calculation and Comparison of the “Biomass Utilization Efficiency (BUE)” of Various Bio-based Chemicals, Polymers and Fuels, Hürth 2015.

- Jang, Y.-R., Lim, Y.-H., Kim, K.: Effect of Content of Potato Tuber Component and Potato Variety on the Bioethanol Production; in: *Korean Journal of Crop Science* 56 (2011), p. 273-278 DOI: 10.7740/kjcs.2011.56.3.273.
- Jian, J., Xiangbin, Z., Xianbo, H.: An overview on synthesis, properties and applications of poly(butylene-adipate-co-terephthalate)-PBAT; in: *Advanced Industrial and Engineering Polymer Research* 3 (2020), p. 19-26, DOI: 10.1016/j.aiepr.2020.01.001.
- Jiang, X., Bai, Y., Chen, X., Liu, W.: A review on raw materials, commercial production and properties of lyocell fiber; in: *Journal of Bioresources and Bioproducts* 5 (2020), p. 16-25, DOI: 10.1016/j.jobab.2020.03.002.
- Kawabe, K.: Development of Highly Selective Process for Mono-Ethylene Glycol Production from Ethylene Oxide via Ethylene Carbonate Using Phosphonium Salt Catalyst; in: *Catalysis Surveys from Asia* 14 (2010), p. 111-115, DOI:10.1007/s10563-010-9094-4.
- Kootstra, M., Elissen, H., Huurman, S.: PHA's (Polyhydroxyalkanoates): General information on structure and raw materials for their production, a running document for "kleinschalige bioraffinage WP9: PHA", Wageningen Plant Research report 727, ACRRES-Wageningen UR, Wageningen 2017.
- Kyulavskaja M., Toncheva-Moncheva N., Rydz J.: Biobased Polyamide Ecomaterials and Their Susceptibility to Biodegradation; in: Martínez L., Kharisova O., Kharisov B. (ed.): *Handbook of Ecomaterials*, Cham 2019, DOI: 10.1007/978-3-319-68255-6_126.
- Lebeau, J., Efromson, J. P., Lynch, M. D.: A Review of the Biotechnological Production of Methacrylic Acid; in: *Frontiers in Bioengineering and Biotechnology* 8 (2020), p. 207, DOI: 10.3389/fbioe.2020.00207.
- Li, Y., Yang, L.-T.: Sugarcane Agriculture and Sugar Industry in China; in: *Sugar Tech* 17 (2015), p. 1-8, DOI: 10.1007/s12355-014-0342-1.
- Mahdaviyani, S. H., Sidsvar D., Parvari, M.: Selective Ethylene Dimerization Toward 1-butene by a New Highly Efficient Catalyst System and Determination of Its Optimum Operating Conditions in a Buchi Reactor; in: *International Journal of Chemical Engineering and Applications* 1 (2010), p. 276-281.
- Mekonnen, M. M., Hoekstra, A. Y.: The green, blue and grey water footprint of crops and derived crop products; in: *Hydrology and Earth System Sciences* 15 (2011), p. 1577-1600, DOI: 10.5194/hess-15-1577-2011.
- Memmo, G., Newlon, J. C., Tang, X.: Process for Sustainably Sourced p-Xylene. Senior Design Reports (CBE) 2018, p. 108.
- Mohsenzadeh, A., Zamani, A., Taherzadeh, M. J.: Bioethylene Production from Ethanol: A Review and Techno-economical Evaluation; in: *ChemBioEng Reviews* 4 (2017), p. 75-91, DOI: 10.1002/cben.201600025.
- Mubofu, E.: Castor oil as a potential renewable resource for the production of functional materials; in: *Sustainable Chemical Processes*, 4, 11 (2016), p. 1-12, DOI: 10.1186/s40508-016-0055-8.
- Nakajima, H., Dijkstra, P., Loos, K.: The Recent Developments in Biobased Polymers toward General and Engineering Applications: Polymers that are Upgraded from Biodegradable Polymers, Analogous to Petroleum-Derived Polymers, and Newly Developed; in: *Polymers* 9 (2017), p. 523, DOI: 10.3390/polym9100523.
- Nessi, S., Sinkko, T., Bulgheroni, C., Garcia-Gutierrez, P., Giuntoli, J., Konti, A., Sanye-Mengual, E., Tonini, D., Pant, R., Marelli, L.: Comparative Life Cycle Assessment (LCA) of Alternative Feedstock for Plastics Production, Part 1: the Plastics LCAMethod, EUR 30725 EN, Publications Office of the European Union, Luxembourg 2021, DOI:10.2760/271095, JRC125046.
- Nghiem, P. N., Kleff, S., Schwegmann, S.: Succinic Acid: Technology Development and Commercialization; in: *Fermentation* 3, 26 (2017), DOI: 10.3390/fermentation3020026.
- Perez, R.: Sugar cane; in: *Perez, R.: Feeding pigs in the tropics*, vol. 132, Rome 1997, p. 131-238.
- Peters, M. W. T., Joshua, D., Jenni, M., Manzer, L. E., Henton, D. E.: Integrated process to selectively convert renewable isobutanol to p-xylene, Patent US20110087000A1, <https://patentimages.storage.googleapis.com/34/3c/ba/eccd552d8e73b6/US20110087000A1.pdf> (29.09.2021).
- Plastics Europe – Plastics the Facts 2025, https://plasticseurope.org/wp-content/uploads/2025/09/PE_TheFacts_25_digital-1pager-scrollable.pdf (10.02.2026)
- Putri, D., Sahlan, M., Montastruc, L., Meyer, M., Negny, S., Hermansyah, H.: Progress of fermentation methods for bio-succinic acid production using agro-industrial waste by *Actinobacillus succinogenes*; in: *Energy Reports* 6 (2020), p. 234-239, DOI: 10.1016/j.egy.2019.08.050.
- Radzik, P., Leszczynska, A., Pieliowski, K.: Modern biopolyamide-based materials: synthesis and modification; in: *Polymer Bulletin* 77 (2020), p. 501-528, DOI: 10.1007/s00289-019-02718-x.
- Rojas-Barros, P., de Haro, A., Muñoz, J., Fernández-Martínez, J. M.: Isolation of a Natural Mutant in Castor with High Oleic/Low Ricinoleic Acid Content in the Oil; in: *Crop Science* 44 (2004), p. 76-80, DOI: 10.2135/cropsci2004.7600.

- Rulli, M., Bellomi, D., Cazzoli, A. et al. The water-land-food nexus of first-generation biofuels. *Sci Rep* 6, 22521 (2016), DOI: 10.1038/srep22521.
- Ryan, C.: An overview of Gevo's bio-based isobutanol production process, Englewood 2019, https://gevo.com/wp-content/uploads/2019/11/Gevo-WP_Isobutanol.1.pdf (09.07.2021).
- Sayyed, A., Deshmukh, N., Pinjari, D.: A critical review of manufacturing processes used in regenerated cellulosic fibres: viscose, cellulose acetate, cuprammonium, LiCl/DMAc, ionic liquids, and NMMO based lyocell; in: *Cellulose* 26 (2019), p. 2913-2940, DOI: 10.1007/s10570-019-02318-y.
- Shen, K., Haufe, J., Patel, M. K.: Product Overview and Market Projection of Emerging Bio-Based Plastics, Final Report of Utrecht University to European Bioplastics, Utrecht 2009.
- Siracusa, V., Blanco, I.: Bio-Polyethylene (Bio-PE), Bio-Polypropylene (Bio-PP) and Bio-Poly(ethylene terephthalate) (Bio-PET): Recent Developments in Bio-Based Polymers Analogous to Petroleum-Derived Ones for Packaging and Engineering Applications; in: *Polymers* 12 (2020), p. 1641, DOI: 10.3390/polym12081641.
- Taffe, P.: Shell's Omega MEG process kicks off in South Korea, <https://web.archive.org/web/20081023133948/http://www.icis.com/Articles/2008/08/18/9148176/shells-omega-meg-process-kicks-off-in-south-korea.html> (29.09.2021).
- Türk, O.: Stoffliche Nutzung nachwachsender Rohstoffe, Wiesbaden 2014.
- Van Heerden, C. D., Nicol, W.: Continuous succinic acid fermentation by *Actinobacillus succinogenes*; in: *Biochemical Engineering Journal* 73 (2013), p. 5-11, DOI: 10.1016/j.bej.2013.01.015.
- Van Putten, R.-J., van der Waal, J. C., de Jong, E., Rasrendra, C. B., Heeres, E. J., de Vries, H. G.: Furan-based platform chemicals of the future. Dehydration of hexoses as biosustainable product route; in: *Chemical Review* 113 (2013), p. 1499-1597, DOI: 10.1021/cr300182k.
- Veith, C. I., Diot-Néant, F., Miller, S., Allais, F.: Synthesis and polymerization of bio-based acrylates: a review; in: *Polymer Chemistry* 11 (2020), p. 7452-7470, DOI: 10.1039/D0PY01222J.
- Vink, E. T. H., Davies, S.: Life Cycle Inventory and Impact Assessment Data for 2014 Ingeo™ Polylactide Production; in: *Industrial Biotechnology* 11/3 (2015), p. 167-180, DOI: 10.1089/ind.2015.0003.
- Wang, X., Fu, Z., Shi, Y., Shi, J., Chen, Y.: Synthesis of biodegradable poly(butylene adipate-co-butylene terephthalate) copolyester by direct esterification-polycondensation; in: *Petrochemical Technology* 39 (2010), p. 1273-1278.
- Winnacker, M., Rieger, B.: Biobased Polyamides: Recent Advances in Basic and Applied Research; in: *Macromolecular Rapid Communications* 37 (2016), p. 1391-1413, DOI: 10.1002/marc.201600181.
- Yeboah, A., Ying, S., Lu, J., Xie, Y., Amoanimaa-Dede, H., Boateng, K. G. A., Chen, M., Yin, X.: Castor oil (*Ricinus communis*): a review on the chemical composition and physico-chemical properties; in: *Food Science and Technology* 2020, p. 1-15, DOI: 10.1590/fst.19620.
- Yu, S., Cui, J., Zhong, C., Meng, J., Xue, T.: Green Process without Thinning Agents for Preparing Sebacic Acid via Solid-Phase Cleavage; in: *ACS Omega* 4 (2019), p. 6697-6702, DOI: 10.1021/acsomega.9b00577.
- Zou, G., Xu, Y., Zheng, J., Jiang, F., Liu, X.: Investigation on converting 1-butene and ethylene into propene via metathesis reaction over W-based catalysts; in: *RCD Advances* 15 (2018), p. 8372-8384, DOI: 10.1039/C7RA13776A.



IfBB

Institute for Bioplastics
and Biocomposites

A large amount of additional information
is also available at www.ifbb-hannover.de
and <https://biopolydat.ifbb-hannover.de>

ifbb-hannover.de



biopolydat



© Hochschule Hannover - University of Applied Sciences and Arts
IfBB – Institute for Bioplastics and Biocomposites

This document is licensed under a Creative Commons
Attribution 4.0 (CC BY ND 4.0):
<https://creativecommons.org/licenses/by-nd/4.0/>

Hochschule Hannover – University of Applied Sciences and Arts
IfBB - Institute for Bioplastics and Biocomposites
Heisterbergallee 10 A
30453 Hannover | Germany

E-mail: lisa.mundzeck@hs-hannover.de

Cite this document as follows: IfBB - Institute for Bioplastics and Biocomposites (ed.):
Biopolymers – Facts and statistics 2025, Hanover 2026.

ISSN (Print) 2363-8559

ISSN (Online) 2510-3431

EDITION 12-2026